

# **ANTAL KERPELY DOCTORAL SCHOOL OF MATERIALS SCIENCE & TECHNOLOGY**



## **Development of ceramic particle reinforced SAC305 lead-free solder composite material**

A Ph.D. dissertation submitted to Antal Kerpely Doctoral School for the degree of  
Doctor of Philosophy in the subject of Material Science and Technology

By

**Manoj Kumar Pal**

Supervisors

**Prof. Zoltán Gácsi (Professor)**

**Dr. Gergely Gréta (Associate Professor)**

Head of the Doctoral School

**Prof. Zoltán Gácsi**

Institute of Metallurgy, Metal Forming, and Nanotechnology

Faculty of Material Science and Engineering

University of Miskolc, Hungary-3515

2021

## List of abbreviation

The symbols are listed according to the order of appearance in the text.

Symbol	Description	Units
$t_o$	Spreading time	s
$E_a$	Activation energy	kJ/mol
$R$	Universal gas constant	J/molK
$T$	Absolute temperature	K
$\Gamma^k$	Amount of adsorption	cm <sup>3</sup>
$c$	Total concentration	mol/L
$\gamma^k$	Surface energy of molten solder k	N/m
$\rho$	Density	g/cm <sup>3</sup>
$g$	Weight	g
$P_c$	Contact perimeter	$\mu\text{m}$
$P_{nc}$	Non-contact perimeter	$\mu\text{m}$
$P_{RCP}$	Relative contact perimeter	$\mu\text{m}$
$\beta$	Skewness	
$q$	Total number of quadrats	
$N_{qi}$	Number of reinforcement particles in the $i^{\text{th}}$ quadrat ( $i = 1, 2, \dots, q$ ),	
$N_q^{\text{mean}}$	Mean number of reinforcement particles/ quadrat	
$\sigma$	Standard deviation	
$A$	Area of the IMCs	$\mu\text{m}^2$
$L$	Length	$\mu\text{m}$
$x_t$	IMCs layer thickness at time t	$\mu\text{m}$
$t$	Aging time	s
$x_o$	Initial layer thickness	$\mu\text{m}$
$D$	Diffusion coefficient	$\mu\text{m}^2/\text{s}$
$n$	Time exponent	
$F$	Applied force	g

$d$	Sample diameter	mm
$S_f$	Spread factor	
$h$	Sample height	mm
$S_r$	Spread ratio	
$\theta$	Contact angle	°

<b>1</b>	<b>CHAPTER 1: Introduction</b>	<b>6</b>
<b>2</b>	<b>CHAPTER 2: Literature review</b>	<b>8</b>
	<b>2.1 Composite solder material .....</b>	<b>8</b>
	2.1.1 <i>Type of reinforcements</i>	12
	<b>2.2 Fabrication of composite solders by PM (powder metallurgy) method.....</b>	<b>14</b>
	2.2.1 <i>Mixing method</i>	14
	2.2.2 <i>Mechanical mixing method (Powder metallurgy)</i>	15
	<b>2.3 Selection of Materials for Investigation .....</b>	<b>17</b>
	2.3.1 <i>Solder Matrix Material</i>	17
	2.3.2 <i>Reinforcement Materials</i>	17
	<b>2.4 Main problems in the composite solders studied.....</b>	<b>18</b>
	2.4.1 <i>Distribution of reinforcements in a solder matrix</i>	18
	2.4.2 <i>Reliability of the bonding between the solder matrices and the reinforcements</i>	18
	2.4.3 <i>Stability of the reinforcements and IMCs</i>	19
	2.4.4 <i>Poor wettability</i>	20
	(a) <i>Surface roughness:</i>	21
	(b) <i>Flux:</i>	21
	(c) <i>Temperature:</i>	21
	<b>2.5 Achievements with the composite solders developed .....</b>	<b>22</b>
	2.5.1 <i>Microstructural modification &amp; growth of IMC particles</i>	22
	2.5.2 <i>Variations in wettability</i>	22
	2.5.3 <i>Effect on the growth of IMC particles</i>	23
	2.5.4 <i>Enhancement of mechanical properties</i>	25
	<b>2.6 Research aims and objectives.....</b>	<b>26</b>
	2.6.1 <i>Knowledge gap</i>	26
	2.6.2 <i>Scientific goals</i>	27
<b>3</b>	<b>CHAPTER 3: Development of lead-free Sn–3.0Ag–0.5Cu/SiC and Sn–3.0Ag–0.5Cu/SiC(Ni) solder composite</b>	<b>28</b>
	<b>3.1 Introduction .....</b>	<b>28</b>
	3.1.1 <i>Synthesis of nickel-coated silicon carbide (SiC-Ni) particles by EP (Electroless plating) method</i>	28
	<b>3.2 Preparation of composite solders.....</b>	<b>30</b>
	<b>3.3 Results and discussion .....</b>	<b>31</b>

3.3.1 <i>Microstructural evolution of lead- free solder composite</i>	31
3.3.2 <i>Physical properties</i>	33
3.3.2.1 <i>Relative density</i>	33
3.3.2.2 <i>Porosity analysis</i>	35
3.3.3 <i>Compressive strength of the PM solder composite</i>	36
3.3.4 <i>Relative contact perimeter (RCP) of reinforcement and matrix</i>	37
3.3.5 <i>Average neighboring particles distance</i>	40
3.3.6 <i>Morphological mosaic analysis</i>	42
3.4 <b>Summary</b> .....	44
<b>4 CHAPTER 4: Morphology and IMCs of composite solders under reflow and thermal aging</b>	<b>45</b>
4.1 <b>Introduction</b> .....	<b>45</b>
4.2 <b>Experimental procedures</b> .....	<b>45</b>
4.2.1 <i>Preparation of samples for reflow and thermal aging</i>	45
4.3 <b>Results and discussion</b> .....	<b>48</b>
4.3.1 <i>Microstructural evolution in the solder matrix</i>	48
4.3.2 <i>Microstructural evolution at solder/Cu interface</i>	51
4.3.3 <i>Microhardness</i>	59
4.4 <b>Wetting behavior of composite solder</b> .....	<b>61</b>
4.4.1 <i>Contact angle (wettability) of composite solder</i>	62
4.4.2 <i>Spread ratio and spread factor</i>	63
4.5 <b>Interfacial reactions between Sn–Ag–Cu solder and Cu substrate</b> .....	<b>64</b>
4.5.1 <i>Calculation of activation energy</i>	74
4.6 <b>Summary</b> .....	<b>77</b>
<b>5 CHAPTER 5: Claims</b>	<b>78</b>
<b>Acknowledgements</b>	<b>81</b>
<b>References:</b>	<b>82</b>
<b>Author publications</b>	<b>99</b>
<b>Journal papers</b> .....	<b>99</b>
<b>Conference presentations</b> .....	<b>99</b>

## 1 CHAPTER 1: Introduction

Customer demand has shown the industry to progress for smaller, faster, and low-cost electronics products. People need always smaller and faster devices with good performance and integrity by utilizing minimum energy and materials. The manufacturer starts to produce smaller mechanical, optical, and electronic products and devices (for example mobile phones, chips, and computers). Thus, electronics miniaturization has challenged to fabricate materials, processing conditions, and reliability of the product. Cost and performance are important technological keys for product evaluation [1].

The execution of lead-free solders is generated remarkable new challenges in the microelectronics sector [2]. Soldering is a metallurgical process that is used to join two (or more) materials by using a third material, which is called solder alloy that has a lower melting temperature than materials to be joint. Solder alloys are usually eutectic (63Sn–37Pb) or near-eutectic (60Sn–40Pb) alloys consisting of an Sn matrix with reinforcements of one or more elements used to reach certain desired physical, mechanical, and chemical properties of the alloy [3].

However, in the 1950s, the United States Environmental Protection Agency (EPA) considered Pb to be one of the dangers that posed the greatest risk to humans and the environment [4]. When lead released into the atmosphere, the kidneys, brain, and nervous system directly affected it. Lead not only affects humans, but also the environment. Two types of risk (direct and indirect) are possible from the lead. The direct risk includes workers who are working in the electronics industry to whom solder fumes and fine lead-retaining particles are exposed during the manufacture of electronic components. The indirect risk is caused by the leaching of the electronic waste components by the effect of rain and groundwater contamination [2]. To prevent environmental pollution, the European Union (EU) banned Pb material after 2006 and it is proposed the Waste for Electronic and Electrical Equipment (WEEE) and the Restriction of Hazardous Substance (RoHS) directive in January 2008 [5-8]. The purpose of these directives is to reduce waste electrical and electronic equipment and to minimize the hazardous substances in electrical and electronic equipment. This directive stated that electronic products sold to European consumers must be Pb-free and this is called lead-free for electronics [9].

Sn-Pb solders require lead-free (green) replacement. Higher melting temperature (~ 220°C) and the cost of the metals are the main problems in the transformation to lead-free solders. High temperatures can propagate in lamination, low thermal fatigue, and crack formation in solder joints

[10-11]. For Pb-free soldering, several potential alloys have been developed, most of the alloys which contain Sn as the primary element. Sn-based solder alloys are a good choice because they have excellent wetting and spreading properties. Combining Sn with copper (Cu) and silver (Ag) looks like a probable Pb-free applicant [12].

New solders are usually Sn-based and the main benchmark for the selection of lead-free solder is that the alloy should be eutectic alloy close. The Sn-Ag-Cu (SAC) is the strongest opponent of Pb-free soldering because it is near to eutectic. NEMI (National Electronics Manufacturing Initiative), Japan Electronics and Information Technology Industries Association (JEITA) suggested an Ag rich composition Sn-3.9Ag-0.6Cu(SAC396), Sn-3.0Ag-0.5Cu(SAC305), and Sn-3.5Ag-0.7Cu(SAC357), and The European Consortium - BRITE-EURAM recommended 95.5wt%Sn-3.8wt%Ag-0.7wt%Cu; Sn-3.8Ag-0.7Cu(SAC387), etc. [13-14].

To improve dimensional stability and mechanical reliability of electronic interconnections, there were several attempts to incorporate suitable reinforcement (including metal, ceramic, IMCs, and carbon nanomaterials, etc.) into lead-free solder matrices to prepare the composite solders and its interconnection. The existence of different reinforcement added could refine the morphology of composite solders and its interfacial IMCs between solder joints and substrate. The added reinforcements could improve the wettability of the composite solder. The refinement of the IMCs greatly improves the reliability of the solder joint and mechanical properties of the solders it might also help to improve the creep resistance and mechanical properties of composite solder joints under harsh service conditions (including high temperature, large temperature gradient, and high current density) when compared with the plain solder joints.

The present dissertation is concentrated on the preparation and characterization of 96.5Sn-3Ag-0.5Cu(SAC305) composite solders containing reinforcement (SiC and SiC-Ni) and the investigation of the microstructural and mechanical properties of composite solder and its joints under the conditions of isothermal aging. The formation of IMCs in lead-free solders with weight variation during the reflow process due to lack of proven data. This research is examined the distribution of the reinforcement in the solder matrix, optimal reflow settings for lead-free solder, and the factor that influences the process are investigated.

## 2 CHAPTER 2: Literature review

### 2.1 Composite solder material

For many years, solder alloys containing the combinations of tin (Sn), lead (Pb), antimony (Sb), copper (Cu), silver (Ag), bismuth (Bi), indium (In), zinc (Zn), gold (Au), silicon (Si) and germanium (Ge) have been used in many industrial applications. Among these, tin-lead (Sn-Pb) solder alloys, particularly with compositions ranging between Sn95-Pb5 and Sn2-Pb98 (wt.%) have been attracted much attention due to their low cost and low/moderate melting temperatures (183 to 316°C) [4].

Even it has been already commercialized; the Sn-Ag-Cu alloy system has several problems to be solved. One of the major problems is the formation of large intermetallic compounds (IMC) in these alloys [15]. The presence of large IMCs greatly reduces the reliability of the solder joint. These IMCs act as stress concentrators and negatively affects the mechanical properties of the solders. Another problem is the poor wetting of the solder alloys. To have a reliable solder joint, there must be a strong bonding between the solder and the surfaces to be jointed. To achieve this strong bond with the smallest amount of solder volume, the solder alloy must wet the largest possible area. The importance of wetting of the solder alloy has increased vitally in the past decade since the sizes of the microelectronic devices have decreased drastically.

There are many different lead-free alloys available nowadays. A solder alloy that is being proposed for the replacement of the traditional Sn-Pb eutectic composition should have its melting point as close as possible to the tin-lead eutectic temperature. The selections are based on a variety of considerations, including toxicity, physical properties (melting temperature, surface tension, wettability, thermal and electrical conductivity), mechanical properties, microstructure characteristics, electrochemical properties (corrosion, oxidation and dross formation, and compatibility with non-clean fluxes), manufacturability, cost, and availability [3, 16-17]. The preference is given to the Sn-Ag-Cu (SAC) alloy family, followed by alloys containing, silver, copper, bismuth, antimony, indium, zinc, and aluminum.

Among all the requirements, wettability (bondability) and suitable melting temperature are the two basics. First, the solder must be capable of wet and bond which indicates that it should be able to form intermetallic compounds with Cu. Second, the melting temperature should be sufficiently low enough to be reflowed as a paste and high enough to avoid the defects due to operating temperatures. Currently, the replacement alloys candidates include ternary, binary, and some



quaternary alloys of Sn with Ag, Zn, In, Sb, Bi, and Cu [4]. Solder composites developed by other investigators have been summarized in **Table 2.1**.

*Table 2.1 Existing solder composites*

<b>Matrix</b>	<b>Reinforcement</b>	<b>Author</b>	<b>Conclusions</b>
Sn–3.5Ag–0.5Cu	ZnO	[18]	<ul style="list-style-type: none"> <li>The results showed a slightly increased melting temperature, increased the tensile strength, and inhibited the growth of the grain size as well as the IMCs Ag<sub>3</sub>Sn and Cu<sub>6</sub>Sn<sub>5</sub>.</li> </ul>
	ZrO <sub>2</sub>	[19]	<ul style="list-style-type: none"> <li>The results showed the improvement of the shear strength, hardness and IMC thickness layer.</li> </ul>
	Y <sub>2</sub> O <sub>3</sub>	[20]	<ul style="list-style-type: none"> <li>The results showed the refinement of the IMCs grains and improved the shear strength.</li> </ul>
	Al <sub>2</sub> O <sub>3</sub>	[21]	<ul style="list-style-type: none"> <li>The results showed exhibit lower density, CTE, refined the Ag<sub>3</sub>Sn, Increased the YS and UTS, increased ductility of the composite solders.</li> </ul>
		[22]	<ul style="list-style-type: none"> <li>The results indicated the refinement of the IMCs grains, improved shear strength and the thickness of the IMC layer increased continuously with increasing numbers of reflow cycles.</li> </ul>
		[23]	<ul style="list-style-type: none"> <li>The results displayed the refinement of the Ag<sub>3</sub>Sn, improved the microhardness and wetting behavior.</li> </ul>
Sn–3.7Ag–0.9Zn	SiC	[24]	<ul style="list-style-type: none"> <li>The results indicated the decrease of the β-Sn dendrites, IMCs, and increase the microhardness.</li> </ul>
Sn–3.5Ag–0.25Cu	TiO <sub>2</sub>	[25]	<ul style="list-style-type: none"> <li>The results showed the increase in the liquidus temperature, refine both the grain size and morphology of Ag<sub>3</sub>Sn, increase the microhardness, 0.2YS, and UTS of the composite solder.</li> </ul>
Sn–0.7Cu–0.05Ni	TiO <sub>2</sub>	[26]	<ul style="list-style-type: none"> <li>The results indicated the decrease of wetting properties, suppressing the growth of the Cu<sub>6</sub>Sn<sub>5</sub> IMC layer, improved the shear strength, and decreased the CTE value.</li> </ul>
Sn–1.0Ag–0.5Cu	Fe <sub>2</sub> O <sub>3</sub>	[27]	<ul style="list-style-type: none"> <li>The results showed the refinement of the β-Sn grain and reduce the CTE, the suppressing formation, and growth</li> </ul>

	SiC	[28] [29]	<p>of interfacial IMCs during reflowing and thermal cycling (TC), enhancing the shear strength of the solder joints.</p> <ul style="list-style-type: none"> <li>• The results showed the improvement of the plasticity and refinement of the primary <math>\beta</math>-Sn grain.</li> <li>• The results displayed smaller <math>\beta</math>-Sn sub-grains, refined IMCs with the greater eutectic area, an improvement in the 0.2 % YS and UTS, and decreased ductility.</li> </ul>
Sn-3.5Ag-0.7Cu	TiO <sub>2</sub>	[30]	<ul style="list-style-type: none"> <li>• The results displayed the suppression of the IMC layer and improved the wetting.</li> </ul>
Sn-3.5Ag	SnO <sub>2</sub>	[31] [32]	<ul style="list-style-type: none"> <li>• The results showed the improvement of the hardness and tensile strength.</li> <li>• The results showed the lower porosity, improvement of microhardness, higher 0.2% YS and UTS.</li> </ul>
Sn-3.8Ag-0.7Cu	SiC SWCNT	[33] [34]	<ul style="list-style-type: none"> <li>• The results displayed the lower melting, improvement of microhardness, and refined IMCs grains.</li> <li>• The results indicated an increase in tensile strength, hardness, better melting characteristics, and a slight decrement in elongation to failure.</li> </ul>
Sn-4In-4.1Ag-0.5Cu	Al <sub>2</sub> O <sub>3</sub>	[35]	<ul style="list-style-type: none"> <li>• The results showed lower density and CTE values and increasing both 0.2% YS and UTS.</li> </ul>
Sn-3.5Ag	ZrO <sub>2</sub>	[36]	<ul style="list-style-type: none"> <li>• The results showed the refinement of the IMCs grains and the improvement of the microhardness.</li> </ul>
Sn-9Zn	Al <sub>2</sub> O <sub>3</sub>	[37]	<ul style="list-style-type: none"> <li>• The results indicated the improvement of the microhardness and the shear strength.</li> </ul>
Sn-3.0Ag-0.5Cu	SiO <sub>2</sub> ZnO CeO <sub>2</sub> SrTiO <sub>3</sub>	[38] [39] [40] [41] [42]	<ul style="list-style-type: none"> <li>• The results displayed improved the wettability and refined microstructure.</li> <li>• The results showed the refinement of the <math>\beta</math>-Sn, improvement of the shear strength, and microhardness.</li> <li>• The results showed the improvement of the wettability, behavior, and reduction of the thickness of IMCs layers.</li> <li>• The results indicated the reduction of the IMCs layer thickness.</li> <li>• The results indicated the improvement of the shear strength and the reduction of the IMCs layer thickness.</li> </ul>

	TiO <sub>2</sub>	[43]	<ul style="list-style-type: none"> <li>The results showed the refinement of the microstructure and the reduction of the IMCs layer.</li> </ul>
	TiC	[44]	<ul style="list-style-type: none"> <li>The results displayed the lower CTE value, improved the wettability, and the reduction of the IMCs' growth.</li> </ul>
	La <sub>2</sub> O <sub>3</sub>	[45]	<ul style="list-style-type: none"> <li>The results showed improved Wettability, refined microstructure.</li> </ul>
	NiO	[46]	<ul style="list-style-type: none"> <li>The results displayed the reduction of the IMCs layer thickness, improved hardness, and refined morphology.</li> </ul>
	Fe <sub>2</sub> NiO <sub>4</sub>	[47]	<ul style="list-style-type: none"> <li>The results showed the improved hardness and the reduction of the IMC thickness.</li> </ul>
	SiC	[48]	<ul style="list-style-type: none"> <li>The results showed the refined IMCs grains, slightly decrement of the melting temperature, and improvement of the tensile strength.</li> </ul>
	Ni-coated GNS	[49]	<ul style="list-style-type: none"> <li>The results displayed the improvement of the hardness and shear strength.</li> </ul>
Sn-3.5Ag	NiTi Shape memory alloy	[50]	<ul style="list-style-type: none"> <li>The results indicated a significant reduction of the creep rates and strain ranges.</li> </ul>
Sn-3.5Ag-0.7Cu	TiB <sub>2</sub>	[51]	<ul style="list-style-type: none"> <li>The results indicated an improvement in wettability, 0.2% YS, UTS, and reduction in ductility.</li> </ul>
	MWCNT	[52]	<ul style="list-style-type: none"> <li>The results showed an improvement in wettability, 0.2% YS, UTS, and reduction in ductility.</li> </ul>
Sn-3.5Ag-0.7Cu	ZrO <sub>2</sub> + 8 mol. % Y <sub>2</sub> O <sub>3</sub>	[53]	<ul style="list-style-type: none"> <li>The results showed the lower density and ductility improved, however, improved the 0.2% YS, UTS, and CTE values.</li> </ul>
Sn-0.7Cu	Al <sub>2</sub> O <sub>3</sub>	[54]	<ul style="list-style-type: none"> <li>The results indicated the improvement of the microhardness, 0.2% YS and UTS, an increasing number of pores, pore size, and irregularity.</li> </ul>
	Geopolymer Ceramic	[55]	<ul style="list-style-type: none"> <li>The results showed the improvement of the hardness and the compressive strength.</li> </ul>
Sn-58Bi	Y <sub>2</sub> O <sub>3</sub>	[56]	<ul style="list-style-type: none"> <li>The results indicated the improvement of the wetting properties, the shear strength; however, the growth rate of the IMC layer decreases slightly.</li> </ul>
Sn-Ag	CeO <sub>2</sub>	[57]	<ul style="list-style-type: none"> <li>The results showed the improvement of the wear, friction resistance, and microhardness.</li> </ul>

According to **Table 2.1**, various researchers have used the ceramics reinforcements in the lead-free solder matrix and prepared the different types of solder composites. Ceramic reinforcements have some favorable properties (ex. chemical stability, abrasion and wear resistance, high strength, hardness, high melting point (thus high-temperature capability), low density) which makes a promising candidate for the reinforcements. Apart from this, they have poor wetting behavior due to the brittle nature, high hardness, resistance to creep, and high strength, conventional machining methods are difficult to perform because of cracks, brittle fractures, and edge chipping.

### 2.1.1 Type of reinforcements

Due to the reactive properties of reinforcement and molten solder, it can be divided into three parts: (1) non-reactive (2) reactive, and (3) hybrid reinforcement. The advantages and disadvantages of reinforcement are listed in **Table 2.2**.

Table 2.2: Type of reinforcements

Type	Materials	Reinforcement	Advantages	Disadvantages
Non-reactive	Oxide	Al <sub>2</sub> O <sub>3</sub> , TiO <sub>2</sub> , Fe <sub>2</sub> O <sub>3</sub> , ZnO [18, 21, 23, 26-27, 37, 39-40, 43, 58-59]	Stable physical and Chemical properties during the reflow process	Poor wetting
	Carbide	TiC, SiC [29, 44]		
	Carbon-based nano-materials	CNT, GNS [34, 60-62]		
Reactive	Metals	Ag, Cu, Fe, Ni, Al, Cr, Mn, Co [63-70]	Good wetting	Corrosive, Coarsening during reflow and aging
Hybrids	Metal/X	Ni-coated CNT, Ag-coated GNS [61, 71-72]	Good dispersibility	Potential risk on reliability; high cost

Carbon-based materials, Metal oxide, carbide, and nonmetallic elements are non-reactive reinforcements because they do not react with the solder matrix during the aging and reflow process, and they do not coarsen during their service life. However, such types of reinforcements

can not be wetted by the molten solder, during the reflow process generally reveals that they are expelled from the molten solder [49, 73].

The reactive reinforcement, which is mainly metal (or alloy) materials and IMCs. This type of reinforcements is easily reacted with molten solder during the reflow process and preserved in the solder joint in the form of IMCs layers. Reactive reinforcement is likely to be coarsening during service life, resulting in a decreasing reinforcing effect. Recently, L. Ma et al. [74] produced novel reinforcement (polyhedral oligomeric silsesquioxanes polyhedral oligomeric silsesquioxane (POSS)) and composite reinforcement; these types of reinforcements were shown good stability in a soldering process. However, the relatively poor thermal and electrical conductivity of such reinforcement can affect the electrical performance of the solder joint. Also, complexity, high energy consumption, and high costs have limited the practical progress of such reinforcement.

SiC is used because of its low cost and the wide range of sizes and grades available. The addition of SiC increases Young's modulus and tensile strength of the composite materials and it is also increased in wear resistance [75]. Aqeeli et al. [75] reported that SiC can help transfer the shear load at the matrix/reinforcement interface, strengthen the matrix and at the same time retain some ductility. However, while the yield and ultimate strength of the matrix increase with increasing concentration of ceramic particles, the ductility of the composites deteriorate significantly at higher concentrations. SiC has the self-organized dispersive systems property and it can help to formation of the heterogeneous nucleation, thereby distributing stress homogeneously in the solder joints [76]. The addition of SiC particles can also improve the sinterability of processed powders. Woo and Zhang [77] investigated the SiC-reinforced Al-7Si-0.4Mg composite powders and an increase in the sintering rate of the composite powder was reported due to the increased diffusion rate.

Some researchers [24, 29, 33, 48] are prepared for the lead-free solder composites (SAC105/SiC, SAC305/SiC, Sn-3.7Ag-0.9Zn/SiC and SAC387/SiC) with the addition of SiC by mechanically mixing. SiC particles were found to provide additional nucleation places for the formation of the primary  $\beta$ -Sn phase and Ag<sub>3</sub>Sn IMCs. The strengthening effect of the composite solders is dependent on the reinforcements and the refined IMCs because these prevent dislocation slipping. Tsao and Chang [78] produced Sn-3.5Ag-90.25Cu composite solders with the addition of *x*-TiO<sub>2</sub> nanoparticles; it shows that 1wt.% TiO<sub>2</sub> is the best composition and significant improvements in the mechanical properties. Nai et al. [32] also produced the Sn-0.7Cu/Al<sub>2</sub>O<sub>3</sub> and Sn-3.5Ag/SnO<sub>2</sub> lead-free solders composites and evaluated mechanical and physical properties; however, the best

results are obtained on the 1.5vol%  $\text{Al}_2\text{O}_3$  and 0.7vol%  $\text{SnO}_2$ , which are better than the Sn–Pb solder. They have also investigated the microstructure of the pores because it is most that the morphology of pores was observed to be one of the most influencing factors which can affect the strength of composite solder.

As mentioned above, non–reactive reinforcements are evicted from the molten solder during reflow, so it needs to form a bridge between solder and matrix. Au and Ni are considered ideal bridge materials because they are capable to react with Sn-based soldered alloys to form IMCs in a soldering process [49]. Mokhtari et al. [79] and Yang et al. [80–81] produced the solder composite with the addition of Au coated Silica and Ni–coated carbon nanotubes (Ni–CNT); Their experimental results showed that the addition of coated reinforcements provided to the improvement of the microstructure, mechanical properties and wetting behavior of the solder alloys.

## 2.2 Fabrication of composite solders by PM (powder metallurgy) method

### 2.2.1 Mixing method

In the current literature, researchers have described several processing methods for synthesizing complex composite solders. These methods can be broadly divided into two parts: (i) powder metallurgy technique and (ii) liquid metallurgy technique. The powder metallurgy technique was applied in the present work. In the mechanical mixing process, reinforcement particles are added as reinforcement to a solder powder, solder paste, or molten solder alloys to produce composite solders. **Figure 2.1a** shows a schematic diagram of the reinforcement and matrix powder mixture and **Figure 2.1b** the homogeneous distribution.

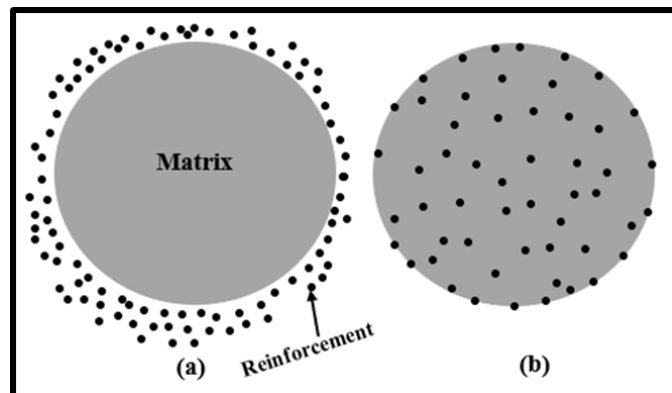


Figure 2.1 Schematic diagram of reinforcement and matrix powder (modified): (a) before milling (zero-hour milling) and (b) after milling (homogeneous distribution) [82]

However, it is not easy to achieve a homogeneous and fine dispersion by the liquid metallurgy method due to the dispersion of the oxide particles is uneven due to the counter diffusion of alloying elements towards the surface and sometimes, large oxide particles precipitate at the grain boundaries leading to degradation in the mechanical properties of the composite.

However, this method also has some advantages. Because the particles formed in this method are thermodynamically stable, the matrix–particle surfaces are generally clean, free of adsorbed gases, oxide films, and harmful reaction products, and thus much stronger. From the above discussion, it becomes clear that composites are difficult to produce by liquid processing methods, and therefore solid–state processing methods are the most suitable for this purpose [83]. The advantages of the solid-state processing method are reduced pollution, low costs, and simplicity in process and handling. Also, these factors are especially important in the industry. Parts can be made from a variety of compositions. It is therefore much easy to have parts of desired mechanical and physical properties like density, hardness toughness, stiffness, damping, and specific electrical or magnetic properties. However, this method has some limitations such as the high cost of metal powders compared to the cost of raw material used for casting or forging a component. A few powders are even difficult to store without some deterioration. Large or complex shaped parts are difficult to produce by the solid-state process.

### **2.2.2 Mechanical mixing method (Powder metallurgy)**

Powder metallurgy (PM) is the most popular manufacturing process. In general, Metal powders are used in the PM process with the specific characteristics of size and shape and then changes it into strong, accurate, and high–performance finished products. There are three main steps to this approach, mixing, compressing, and sintering.

The three main steps (mixing, compacting, and sintering) in the powder metallurgy process are illustrated in **Figure 2.2**. The process employs automated operations with low relative energy consumption, high material consumption, and low cost of capital. The PM method can cost–effectively synthesize complex components, such as automotive components. Accuracy and cost are very important in the casting process; however, the casting process poses several issues such as segregation, machining, and maintaining accuracy. Alloy powders can be fabricated below the melting temperature, segregation and other defects can be eliminated. PM technique can be used

to produce porous metals, oxide dispersion alloys, ceramic–metal composites, and cemented carbides. The powder metallurgy technique is popular because all processes can be performed in the solid-state and microstructural damage caused by elevated temperatures can be avoided. The important properties which lead to the continued development of the PM method are given below [83-85]:

- I. Production of high-quality precision structural and complex parts.
- II. Production of difficult-to-process materials where fully dense, high-performance alloys can be produced with uniform microstructure.
- III. Economical consolidation of high-performance materials including composites containing mixed/non-equilibrium phases.
- IV. Synthesis of non-equilibrium materials such as amorphous, microcrystalline, or metastable alloys.

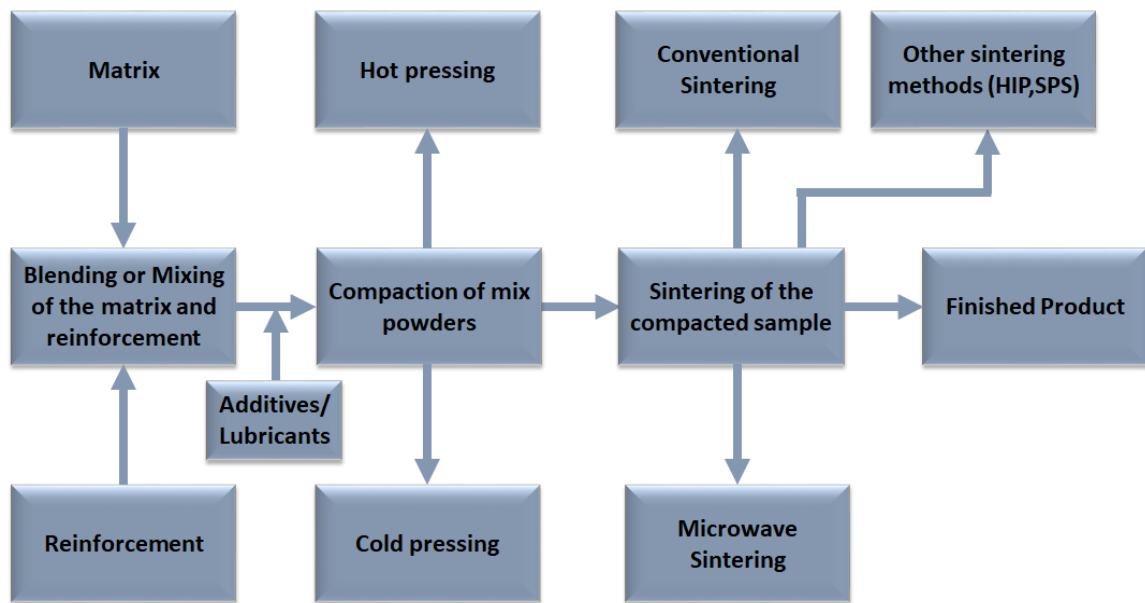


Figure 2.2 Process of powder metallurgy technique

A more efficient method is to mix each particle (reinforcements and matrix) by solid-state processing methods, such as mechanical grinding of a mixture of metal particles and ceramic nanoparticles. Sintering is an important step in the PM method in which densification and bond formation takes place. Sintering can be done by conventional heating methods, such as resistance heating, or by microwaves or by plasma, etc. [86-88].



## 2.3 Selection of Materials for Investigation

### 2.3.1 Solder Matrix Material

As discussed in section 2.1, Sn-3.0Ag-0.5Cu has superior mechanical properties compared to the other lead-free solders and particularly conventional eutectic Sn-Pb, Therefore, commercial lead-free solder alloy, Sn-3.0Ag-0.5Cu (SAC305) was selected as a matrix material.

### 2.3.2 Reinforcement Materials

In comparison to other ceramic reinforcing particles, SiC is also a typical ceramic material with excellent chemical stability, low density (3.21 g/cm<sup>3</sup>), and high melting temperature (2,730 °C); it also exhibits good mechanical properties. Additionally, it has also high electrical and thermal conductivity; so for this reason, SiC a potential reinforcement for composite solders without affecting significantly their performance. SiC is supported to form self-organized dispersive systems that can help to formation of the heterogeneous nucleation so that stress can be distributed homogeneously in the solder joints. SiC particles were found to provide additional nucleation places for the formation of the primary  $\beta$ -Sn phase and Ag<sub>3</sub>Sn IMCS. The strengthening effect of the composite solders is dependent on the reinforcements and the refined IMCs because these prevent dislocation slipping [24, 29, 33, 48]. Table 2.3 shows the advantages of SiC ceramic reinforcement.

Table 2.3 Advantages of the SiC ceramic reinforcement

<b>Reinforcement</b>	<b>Advantages</b>	<b>Reference</b>
<b>SiC</b>	<ul style="list-style-type: none"> <li>• Low cost and a wide range of sizes and grades available.</li> <li>• It increases Young's modulus, tensile, and wear resistance.</li> <li>• It can be helped the transfer the shear load at the matrix/reinforcement interface,</li> <li>• Strengthen the matrix and at the same time retain some ductility.</li> <li>• It has a self-organized dispersive systems property.</li> <li>• It can help to formation of the heterogeneous nucleation.</li> <li>• It can improve the sinterability of processed powders.</li> </ul>	<p>[75]</p> <p>[24, 33, 76-77]</p>

## **2.4 Main problems in the composite solders studied**

### **2.4.1 Distribution of reinforcements in a solder matrix**

Generally, the reinforcements are found at the grain boundaries of solder alloys and enhance the mechanical properties of the solder and joint. However, the addition of excessive reinforcement is probably to accumulate and agglomerated in the solder matrices, which can reduce the mechanical strength of composite solders. Therefore, the reinforcement must be homogeneously distributed in the matrix during the mixing process.

However, it is practically difficult to make a composite solder with homogeneously distributed reinforcements. The mixtures (solder powder and reinforcement particles) are milled for a long period and agglomeration is formed in the composite solder matrices. Some researchers have been used the mechanically mixing method to solve this problem and this method is provided a relatively uniform distribution of reinforcement particles in the matrix; however, some fractures are developed at the surface between reinforcement and the matrix due to plastic deformation during a long time mixing [89-90]. Various researchers have been successfully fabricated a composite solder with a uniform distribution of reinforcement particles [28, 36, 55, 82, 91].

In their experiments, an inert gas was used to remove the oxidation of the molten alloy. Due to different densities of reinforcement and solder matrix, the contact of the reinforcement particles will cause the non-uniform distribution in the solidification. Hence, to obtain a homogeneous distribution of the reinforcement within the composite solder, the composite alloy needs to be mixed in a proper method. The powder metallurgy technique would be a better option for the homogeneous distribution of the reinforcing particles in the solder matrix since the reinforcing particles can be formed by the precipitation of the IMC phase particles during the melting process. These reinforcing particles are homogeneously distributed in the solder matrix or at the interface of solder/copper without agglomeration.

### **2.4.2 Reliability of the bonding between the solder matrices and the reinforcements**

To enhance the performance of the solder, it is needed the strong bonding between reinforcement and solder matrix particles during the soldering process. If the bonding will be poor between the solder matrices and reinforcement particles, pores, cracks, and other impurities will easily be existed at the surface of particles during melting.

Also, cracks, pores, poor bonds, and interfacial strength will be normally developed due to mechanical deformation and it is directly affected the performance of the composite solder. Metallic and IMC particles have a strong bond with the solder matrix because these are the reactive reinforcement and it can be easy to react with the solder matrix and form a strong bond during the melting process. However, inert particles (ceramics and carbon-based materials) are non-reactive material and these do not react with the solder matrix and form a reliable bonding. Therefore, wetting or reaction of non-reactive particles and soldered alloy matrices is a very serious concern. It should be noted that reinforcement must be successfully embedded and homogeneously distributed into the solder matrices, most of the researchers studied that non-reactive reinforcement particles were expelled from the solder matrix during the soldering process. To solve this problem, the coating of the Au and Ni has been used by some researchers because these are formed a bridge between solder and non-reactive reinforcements and it can be easily reached with the solder particles during the melting process [49].

#### **2.4.3 Stability of the reinforcements and IMCs**

Another important problem is the stability of the reinforcement in the reflow and aging process. Non-reactive reinforcement particles will not be coarsened in the solder alloy. The same problem happens with the metal reinforcement particles; however, they usually coarsen at high temperatures.

It is very important to define the morphology of the composite solder before and after melting. Some researchers explained that  $\text{Ag}_3\text{Sn}$  IMC particles formed in the solder matrix after solidification will not be nano-sized particles but in the form of platelet shapes [92-93]. Due to the brittle properties of the IMCs, they can directly influence the mechanical properties of the solder joints. Hwang et al. [93] reported that the  $\text{Cu}_6\text{Sn}_5$  IMC particles were homogeneously distributed in the bulk area but did not re-melted during reflow because the melting temperature of these IMC particles was higher than the reflow temperature. In the general case, most nano-sized IMC particles dissolve in the solder matrix during reflow and coarsen after aging. However, when using solid-state bonding techniques, these IMC particles can be kept in the solder matrix with initial size and it can affect directly the strength of the solder. Therefore, further research on new solid-state bonding techniques is required to solve this issue.

#### 2.4.4 Poor wettability

The soldering process and the strength of the joint depend on the contact and the formation of the bond between the liquid material and the solid substrate material. Wettability tends to spread the liquid on a solid substrate and is generally considered by the contact angle. A liquid that spreads on a substrate and does not react by the substrate material is called non-reactive wetting, while the wetting process affected by the reaction between the spreading liquid and the substrate is called reactive wetting [94]. Young's equation gives the contact angle concerning the triple point. Young's equation provides the contact angle in terms of the interfacial energy or interfacial tensions occurring at the three-point interface. Several factors (For example system conditions, liquid properties, roughness, heterogeneity of the surface, atmospheric conditions, and substrate properties) can be influenced by the wetting property. On the other hand, the reactive wetting process is influenced by a few more factors, such as soldering temperature, flux, the addition of impurities, etc. However, the correct mechanism which can control the kinetics of wetting is very difficult to predict because reactive wetting is influenced by a lot of the factors, such as interfacial reactions, chemical reaction, diffusion of components, dissolution of the substrate, etc. Whenever the solidified liquid is spread on the solid substrate interface, the various condition of the solidified liquid as shown in **Figure 2.3**.

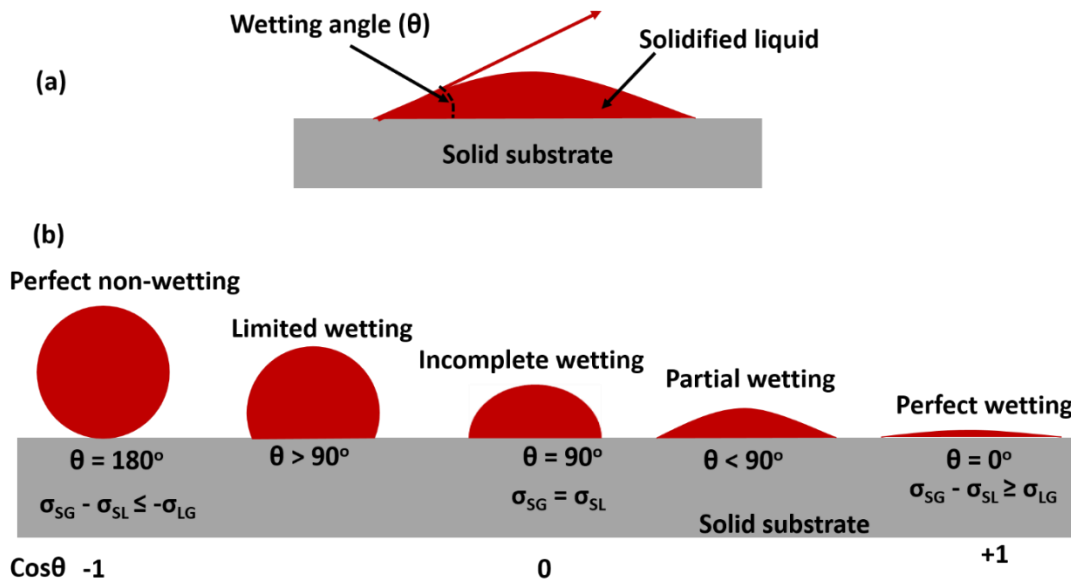


Figure 2.3 Schematic diagram of different wetting phases on the solid substrate

- (a) **Surface roughness:** The rough surface can create the new surface area for the solidified liquid and the actual contact angle would be different from the nominal contact angle. The new surface area is given by the rough surface and it increases the surface energy. Surface cleanliness is an important parameter that can affect the wettability property of the composite solder. Surface roughness is unavoidable because of the impurities on the surface of the substrate. Rough surfaces create a metastable state of equilibrium for the joints and it provides multiple contact angles [94].
- (b) **Flux:** The key role of the flux is to overcome the oxidation in the solidification process. The reduction of the oxide layer can obtain the real wetting on the solid substrate and it can change the interfacial properties of the solder joint. It can provide oxidize-free surface and help the solder particles to wet on the solid substrate. It can also protect from re-oxidation and directly affect the surface tension of the solidified solder in the direction of solder spreading [95].
- (c) **Temperature:** Temperature plays a key role in the solidification process and it can affect the solidified liquid as well as a solid substrate. Oxidation behavior, reaction rate, surface tension, and viscosity are influenced by temperature. It is a general phenomenon that the viscosity and surface tension of a liquid decrease with increasing temperature. Therefore, wettability in all systems should improve with increasing temperature [96]. The diffusion rate increases with increasing temperature in reactive wetting. However, in some cases, it may be attributed to adverse effects because of oxidation, changes in reactivity, and phase changes. As a result, this kind of trend is often noticed during the solidification of solders in the existence of flux at different temperatures. Lopez and Kennedy [97] reported that the wetting process is showed a temperature dependence and it is followed by the spreading time and temperature dependence Arrhenius eq. (2.1).

$$\frac{1}{t_0} = K \exp\left(\frac{-E_a}{RT}\right) \quad Eq. (2.1)$$

Where,  $t_0$  = Spreading time (s),  $K$  = Pre-exponential factor,  $E_a$  = Activation energy (kJ/mol),  $R$  = Universal gas constant (J/molK) and,  $T$  = Absolute temperature (K)

$E_a$  can be calculated by plotting the graph between  $\ln(1/t_o)$  vs  $1/T$  and slope of the graph achieved as activation energy. On other hand, the activation energy of the spread liquid can also be obtained by applying the base radius, contact angle, and the height of the solidified liquid.

## 2.5 Achievements with the composite solders developed

### 2.5.1 Microstructural modification & growth of IMC particles

In recent studies, most of the added reinforcement particles may have changed the microstructure of the solder matrices, and these variations have generally been positive and have contributed to improving the mechanical properties of the composite [33, 36, 48, 51-52, 98-99]. This theory was based on the added reinforcement, because this is helped to the reduction of the particle size of the solder matrices and improved the strength of the solder alloy according to the Hall–Petch relationship [100].

Kumar et al. [34] described the refinement of the  $\text{Cu}_6\text{Sn}_5$  and  $\text{Ag}_3\text{Sn}$  in the lead-free solder matrix. It was about 3.75 to 4.25  $\mu\text{m}$  and 0.5 to 0.8  $\mu\text{m}$  with (1wt% SWCNT) and without reinforcement. Various researchers have reported similar results with the addition of reinforcements into the lead-free solder matrix [28, 33, 36, 89, 98, 101-103]. Lin et al. [98] investigated, the addition of  $\text{TiO}_2$  nanoparticles in the lead-free solder has formed some agglomeration due to different microstructure than the conventional lead-based solder. In this research, Sn–3.0Ag–0.5Cu solder alloy, two types of IMCs ( $\text{Ag}_3\text{Sn}$  and  $\text{Cu}_6\text{Sn}_5$ ) were observed, and SiC and Ni-coated SiC dispersed homogeneously in the  $\beta$ -Sn matrix.

### 2.5.2 Variations in wettability

Sharma et al. [6, 45, 104] reported that wetting behavior enhanced with the addition of  $\text{La}_2\text{O}_3$ , Graphene Nano-platelets, and Copper–Coated Carbon Nanofibers in the SAC305 and Sn–3.5Ag solder alloy. Lee et al. [105] also reported the wettability of an Sn–0.7Cu solder with the addition of 0.5% Ag nano-particles and it found the better wettability than the monolithic solder. Ni and  $\text{Ni}_3\text{Sn}_4$  reinforced composite solder showed an enhanced wettability when compared with the unreinforced solder paste [93]. The addition of an appropriate amount of MWCNT improved the wettability of Sn–Ag–Cu composite solders [52, 106]. However, Nai et al. [51] found the maximum contact angle on the 1.5vol.% of  $\text{TiB}_2$  in then Sn–Ag–Cu composite solders and on the 5vol.% of  $\text{TiB}_2$ , the wettability was degraded. This phenomenon was attributed to the amount of

reinforcement in the matrix, the presence of too many reinforcement particles repressed the flow of molten solders by increasing its viscosity, and further reducing the spread-ability of the solder on the substrate. Sharma et al. [45] reported that the reinforcement of the  $\text{La}_2\text{O}_3$  into the matrix reduces the interfacial energy and thus achieves better wetting because the wettability depends on the surface tension and the surface tension depends on the surface energy of the material.

However, it is not clear an exact mechanism for the variations of wettability between molten solder alloys and substrates with the addition of minor alloying elements. Therefore, further research is needed to explain the mechanism of wetting change.

### **2.5.3 Effect on the growth of IMC particles**

The growth of IMCs grains and the IMCs layers in solder matrices (bulk area) and at the interface has been studied by many authors [6, 28, 33, 36, 45, 52, 89, 98, 101-104, 106]. IMC phases are formed between the grains and IMCs layers are developed due to interfacial and chemical reaction between the solder and substrate

According to the current literature, most of the ceramics and carbon nanomaterials [33-34, 44, 48, 51-52, 58, 61-62, 98, 102, 106-113] have been shown that these are very useful in suppressing the growth of IMC phases in solder matrices and interfaces during reflow or the thermal aging process. Some researchers have studied the growth of the IMCs on the lead-free solder by using metal reinforcement particles (Co, P, Cu, In, Sb, Pt, Al, Zn, Ge, Ni, Ag, and Au). Amagai [114] indicated that Ni, Co, and Pt nano-particles were very beneficial in refining the growth of IMCs grains and layers because these are reactive reinforcements and it can be reacted easily with the lead-free solder particles. The microstructural analysis of the IMCs layers between Sn–3.5Ag and Sn–3.5Ag–0.7Cu and pure Cu and Ni substrates were investigated by Yu et al. [115]. It was found that during solidification,  $\text{Ag}_3\text{Sn}$  nanoparticles were presented on the surface of the IMC layer, which would reduce the interfacial energy and suppress the excessive growth of the IMC layer. Shen et al. [36], Liu et al. [33], and El-Daly et al. [116] added  $\text{ZrO}_2$  and SiC nanoparticles into an Sn–Ag and Sn–Ag–Cu lead-free solder and found the refinement of the IMCs.

Problems are developed with inert particles (non-reactive particles) because they do not react with the solder material (metallic elements) and it is agglomerated at the grain boundaries or IMC layers in the solder alloys. Surface absorption theory can be helped to describe the mechanism of refinement (suppression) of the growth of IMCs in the solder during the reflow and aging process.

According to the surfactant adsorption theory, the amount of absorption of reinforcement particles on the molten solder  $k$  is explained as follows Eq. (2.2) [113, 117-118]:

$$\Gamma^k = \frac{-c d\gamma^k}{RT dc} \quad Eq. (2.2)$$

Where,  $\Gamma^k$  is the amount of adsorption of reinforcement particles on molten solder  $k$ ,  $c$  is the total concentration of reinforcement particles in the solder,  $R$  is the ideal gas constant,  $T$  is the absolute temperature and  $\gamma^k$  is the surface energy of molten solder  $k$  without reinforcement particles.

When molten solder  $k$  adsorbed a layer of ceramic particles, the surface tension can be explained from the integral of the Eq. (2.3):

$$\sum_k \gamma_{(c)}^k A_k = \sum_k \left( \gamma_0^k - RT \int_0^c \frac{\Gamma^k}{c} dc \right) A_k \quad Eq. (2.3)$$

Here,  $A_k$  is the area of the crystal planes  $k$ ,  $\gamma_0^k$  is the surface tension of the initial crystal planes  $k$  without adsorption,  $\gamma_{(c)}^k$  is the surface tension of crystal planes  $k$  with adsorption,  $\Gamma^k$  is the adsorption of surface-active material at crystal planes  $k$ ,  $c$  is the concentration of the surface-active material,  $T$  is the absolute temperature,  $R$  is the gas constant. If the crystal volume is constant; the surface energy of the crystal planes can be kept to a minimum in the equilibrium state. As shown in Eq. (2.4):

$$\sum_k \gamma_{(0)}^k A_k - RT \sum_k A_k \int_0^c \frac{\Gamma^k}{c} dc \rightarrow \min. \quad Eq. (2.4)$$

Where,  $\sum_k \gamma_{(0)}^k A_k$  is assumed to be constant because of the independence of the concentration of surface-active materials. So  $RT \sum_k A_k \int_0^c \frac{\Gamma^k}{c} dc$  should be maximized, which means the effect of the crystal plane with the maximum amount of adsorption, is most active.

In general, the crystal plane with maximum surface energy increases rapidly while the adsorption amount of surfactant is maximized. However, reinforcement particles, which are considered to be effective surfactants, can significantly reduce the surface energy of the crystal and therefore reduce the growth rate of the crystal plane. In this regard, this nano or micron-sized reinforcement can be adsorbed on the surface of the IMC particles or IMC layers to suppress their uncontrolled growth. The development of the IMCs involves various theories, including volume diffusion, grain boundary diffusion, dissolution, and coarsening into the solder [119]. Hence, these elements need to be seriously investigated to recognize how the reinforcements are influenced by the solder



matrix. Gain et al. [118] and Liu et al. [33] reported that TiO<sub>2</sub> and SiC particles suppress the Ag<sub>3</sub>Sn and Cu<sub>6</sub>Sn<sub>5</sub> phase because adsorption of TiO<sub>2</sub> and SiC nanoparticles reduces the surface energy of primary Ag<sub>3</sub>Sn crystals. So, SiC and TiO<sub>2</sub> is a powerful surface-active agent that can be absorbed on the surface of IMCs particles and refine excessive growth.

#### **2.5.4 Enhancement of mechanical properties**

Most of the researchers are reported that reinforcement (metal, ceramic, IMC nanoparticles and carbon nanomaterials (such as carbon nanotube and graphene) or the reinforcement particles increased the mechanical properties of the solder composites and it has shown the desirable performance (such as high hardness, high tensile strength, and high shear strength) compared with monolithic solders. El-Daly et al. [28] and Liu et al. [33] and reported that the tensile and yield strength of solder joints enhanced with SiC nanoparticles addition than that of monolithic SAC solder joints. Other researchers also investigated the addition of ceramic nanoparticles, such as ZrO<sub>2</sub> [36], Al<sub>2</sub>O<sub>3</sub> [35, 58, 120-121], TiO<sub>2</sub> [26, 98, 122], Copper-Coated Carbon Nanofibers [6], Ag-coated MWCNT [123], Ag coated graphene [72], Ni coated CNTs [61, 71, 81, 124-125], Ni-coated graphene nanosheets [126], Ag-decorated MWCNT [127-128], Ni-coated graphene nanosheets [129] that these particles significantly enhanced the hardness, tensile strength and creep resistance of nano-composite solders. However, CNTs added composite solders disclosed that the reinforcement of MWCNTs and SWCNTs in solder matrices increased the yield strength (YS) ultimate tensile strength (UTS), and micro-hardness of solder joints while the ductility of composite solders decreased significantly [34, 52, 99, 106].

Also, MWCNTs and SWCNTs were established dimensionally stable in the lead-free solder due to the low coefficient of thermal expansion (CTE). According to the classical theory of strengthening dispersion [130], the improvement of the mechanical properties of composite solders depends on the distribution of reinforcement particles in the solder matrices and at the grain boundaries. These reinforcement particles try to change deformation by preventing the grain-boundary sliding as well as obstructing dislocation movement in the solder matrix [130-131]. To understand the dependency of the size and mechanical properties, Shi et al. [103] studied the result of the reinforcement particle size scale on the mechanical properties of the solders. They investigated the thermal creep resistance with the addition of Cu and Ag particles in the Sn-Pb, and Sn-Cu solder alloys, and results show that tensile shear strength with the addition of nano-

size particles are higher than the micro-size particles; however, micro-sized particles have shown better creep strength than the nanoparticles. The reason for this improvement was that nano-sized particles refine the alloy grains and the fine grain size causes a decrease of the creep strength, which was more effective than the increase of creep resistance by impeding grain boundaries sliding.

However, to produce composite solders with high overall properties, more in-depth studies are needed to understand the optimal size of the reinforcing particles for solder alloys of different compositions and structures.

## **2.6 Research aims and objectives**

Several studies have demonstrated that the SAC series is the most promising alternative for the lead-free solder alloy due to its excellent overall properties [132-134]. Although some studies have indicated that the mechanical properties and microstructural defects of the SAC solder under different experimental conditions, further work is needed to eliminate these disadvantages. Sn-3.0Ag-0.5Cu (SAC305) was selected for the current study because it is a widely used Pb-free solder in the assembly of electronic devices. Unfortunately, SAC solder has lower reliability and mechanical properties than the Pb-solders. The joint strength of the SAC305 solder alloy can be improved with various modifications of reinforcement and the solder contents. Hence, optimal composition and process condition must be consider during soldering process [135].

### **2.6.1 Knowledge gap**

Most of the previous and recent investigations are preliminary studies to identify mechanical properties and interfacial microstructures of composite interconnect with the addition of alloying elements under thermal aging and reflow condition.

Just a few studies investigated the distribution of the reinforcement particles, optimum composition, and connection between the reinforcement matrix particles. There is a gap in understanding the effect of the connection between the reinforcement and matrix particles. The knowledge is also missing in the systematic qualitative examination of average neighboring particles distance and morphological mosaic analysis of the ceramic reinforcement in the solder matrix.

In addition to this, IMCs layer growth was confirmed with various reflow, aging time, and temperature. The development of the IMCs layer is due to the higher diffusion of the Cu atoms. However, some literature is provided that the growth of the IMCs layers is surpassed with an increase in temperature. There is a need to clarify the behavior of the IMCs layer of the Different time and temperature under reflow and aging condition.

### **2.6.2 Scientific goals**

Based on these, the present dissertation is emphasized on the preparation and characterization of Sn–3.0Ag–0.5Cu (SAC305) composite solder with various content (0.5, and 1.5 wt. %) of SiC and Ni-coated SiC reinforcements and the examination of physical, microstructural and hardness of a lead-free solder Sn–3.0Ag–0.5Cu. After careful literature review and finding of the knowledge gap, the following scientific aims have been defined:

- (1) Identify the optimum composition of the reinforcement in the solder matrix.
- (2) Investigate the relative contact perimeter between the reinforcement and lead-free solder particles.
- (3) To investigate the average neighboring particle distance and morphological mosaic analysis of the ceramic reinforcement in the solder matrix.
- (4) Observe the change in the thickness of the IMCs layer at the Cu–Sn interface and establish the relation between the growth thickness, time, and temperature under reflow and aging condition.
- (5) How does the SiC and nickel-coated SiC reinforcements affect the microstructural evolution?
- (6) How does the SiC affect the wettability and how does the nickel coating change this?
- (7) What effect does increasing the amount of SiC have on wettability and hardness as well as on microstructure?
- (8) What changes occur in the microstructure as a result of aging in the case of the composites?
- (9) Does nickel coating matter for aging?
- (10) What kind of processes takes place during reflow and aging?
- (11) How does the thickness of the IMC layer change as a function of time and temperature during reflow and aging?

### 3 CHAPTER 3: Development of lead-free Sn–3.0Ag–0.5Cu/SiC and Sn–3.0Ag–0.5Cu/SiC(Ni) solder composite

#### 3.1 Introduction

The recent research trends in lead-free solders moved in the direction of reinforcement by a fourth alloying element in the ternary solder alloy. This is devised to improve their mechanical properties, electrical properties, and improve the microstructural stability. Tsao et al. [22] investigated the mechanical properties of SAC solder reinforced by ceramic particles like TiO<sub>2</sub> and Al<sub>2</sub>O<sub>3</sub> nanoparticles. They found an improvement in the mechanical properties of the quaternary solder. Rare earth oxides were used as reinforcing particles with a marked improvement in obtained microstructure and properties of SAC solders [136]. However, the scientific community moved towards reinforcing carbide-based reinforcement owing to its low cost and ease of production. Some researchers have shown the reinforcement of SiC has significantly improved the microstructure, mechanical properties, and wetting behavior of the SAC solder alloy [24, 33, 116, 137-138].

Fathian et al. [82], Chellvarajoo et al. [47], and El-daly et al. [116] concluded that the best way to prepare the solder composite is the powder metallurgy method. They stated that this method gives the best distribution of the reinforcement in the matrix. SAC305 lead-free solder powder was purchased as prepared from Cobar Europe B.V., Breda, the Netherland with an average particle size of 20–24 µm and SiC particles used in this study were procured as prepared from SIKATECH (Switzerland) with an average particle size of 1–3 µm.

##### 3.1.1 Synthesis of nickel-coated silicon carbide (SiC-Ni) particles by EP (Electroless plating) method

The electroless plating method is employed here for the coating of Ni on to SiC particles for the simplicity and non-hassle freedom associated with the process. Metallic Ni is obtained from the EN method by reduction of the nickel sulphate solution using a reducing agent. The entire process is carried out in presence of SiC particles being used as carriers.

As stated above, the SiC particles are preferred as carriers for Ni electroless plating. Vaezi et al. [139], Pal et al. [140], Pavlatou et al. [141], Zimmerman et al. [142], Gyökér et al. [143], Czagány et al. [144], Pázmán et al. [145], Kretz et al. [146], and Ahmad [147] studied the effects of co-precipitation and co-deposition mechanisms involving SiC. As stated, Ni is reduced from its salt solution by using Sodium hypophosphite as a reducing agent [147]. The three-step used in the

research work for the deposition of Ni onto SiC using EN plating method is shown below in **Figure 3.1**. The steps contain (i) ultrasonic cleaning, (ii) acidic pre-treatment (sensitization and activation), and (iii) EN plating.

The first step was purified the SiC in an acetone bath for about 30 min. The concentration of SiC particles with acetone was used 4g/100 ml during this study. In the second step, dried SiC powders were mixed with the solution of Sodium hypophosphite (60g/l), Lactic acid 98% (40ml), and distilled water, and this process was accomplished with a magnetic stirring speed of 300 rpm at 85°C for 40 min. After that, the solution was dried in the furnace at 120°C. In the third step, the solution was prepared for 56g/l nickel sulfate ( $\text{NiSO}_4 \cdot 7\text{H}_2\text{O}$ ), 60g/l sodium hypophosphite ( $\text{NaH}_2\text{PO}_2 \cdot \text{H}_2\text{O}$ ), 40ml lactic acid 98% ( $\text{C}_3\text{H}_6\text{O}_3$ ), and distilled water. The solution was stirred at the temperature of 85°C for 40min, and the pH value of the solution was adjusted at 4-5. One hour later, the solution was washed/rinsed with distilled water four to five times. Finally, the solution was dried at room temperature in the air. Complexing agents are added to prevent nickel oxidation and pH control. Thus, Ni coating on SiC particles was achieved before imparting them into the solder matrix.

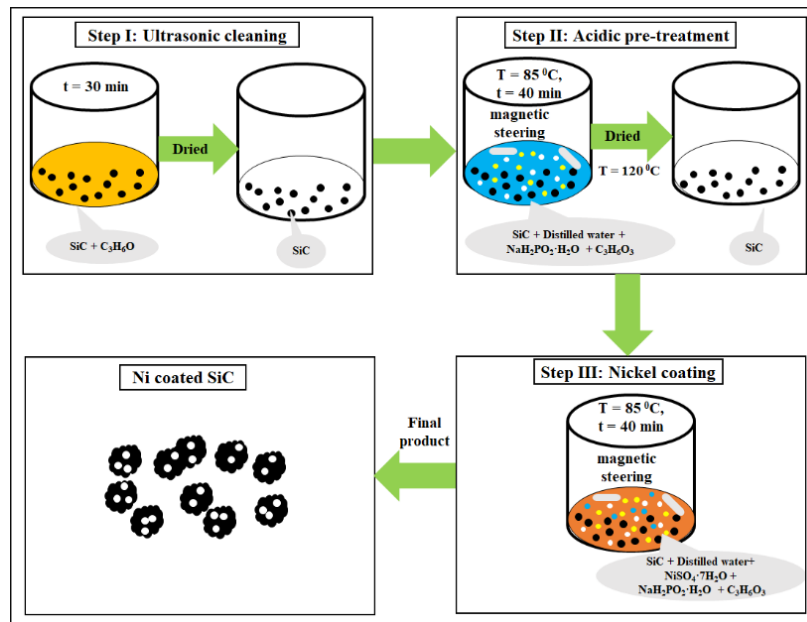


Figure 3.1 Schematic diagram for Ni-coated SiC process

**Figure 3.2(a-d)** shows an SEM image of Ni-coated SiC and the corresponding elemental maps, and the elemental maps were confirmed that nickel particles were deposited on the surface of SiC. However, the existence of Si, Ni, O, and P was determined by EDS (**Figure 3.3**) analysis.

The main reason for Ni-coated SiC is to avoid unnecessary reactions between ceramic SiC reinforcement and SAC solder matrix. Jiaqiang, Gao et al. [148] reported that reaction temperature was dependent on the size of the SiC particle because nickel atoms easily diffuse on the surface of the SiC particles. During electroless plating, firstly, nickel atoms are deposited as a form of clusters on the SiC particles surface. During the heating process, Ni atoms diffuse on the interface of the silicon carbide particle because clusters of the Ni atom are thermodynamically metastable.

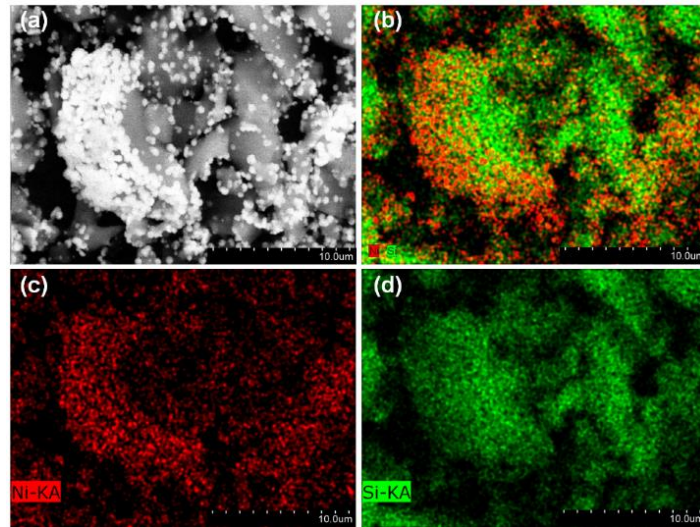


Figure 3.2 (a) SEM image of Ni-coated SiC and corresponding elemental maps (b) Ni and Si (c) Ni (d) Si

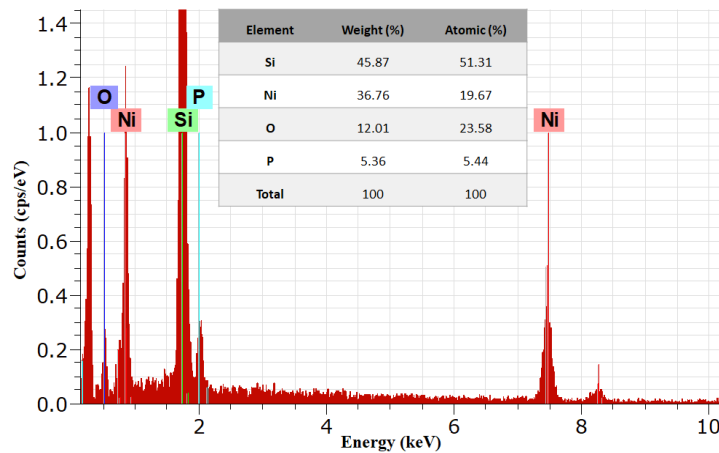


Figure 3.3 EDS analysis of the SiC(Ni)

### 3.2 Preparation of composite solders

Once the SiC particles are coated with Ni particles, the next logical step is to reinforce these particles into the lead-free SAC305 solder matrix. For this purpose, the powder metallurgy method

was chosen. The SAC305 powder is blended with SiC and SiC(Ni) powders at various weight fractions. The composite lead-free solders from here on would be marked as SAC- $x$ %SiC(Ni), where  $x$  stands for 0, 0.5, 1, and 1.5wt% for SiC and SiC(Ni). As stated above, we employed a powder metallurgy route for its consistency and homogeneous distribution of the reinforcements in the matrix. The SAC305 powder and reinforcements (SiC and SiC-Ni) powder particles were pre-weighed and put in a milling jar. They are mixed to achieve homogenization in a planetary ball mill for 1 hour. The rotational speed of the milling process was 200rpm and the ball to powder ratio is 10:1 (BPR). The steel balls used in this process were 3mm in diameter. Ethanol was used as milling media (40 ml). **Figure 3.4(a) and Figure 3.4 (b)** indicate the schematic view of the ball milling process and SEM picture of SAC305/SiC after 60 min of ball milling. Once this process is completed, we get a homogenously mixed SiC/SAC305 and SiC(Ni)/SAC305 powder. This powder is then compacted under a pressure of 200MPa in a cylindrical die of 15mm diameter. Oil lubricant was used to make the ejection and densification of the post process sample smoother. Following the compaction, the substrate was sintered in a furnace for 3 hours at 200°C under Ar inert gas environment.

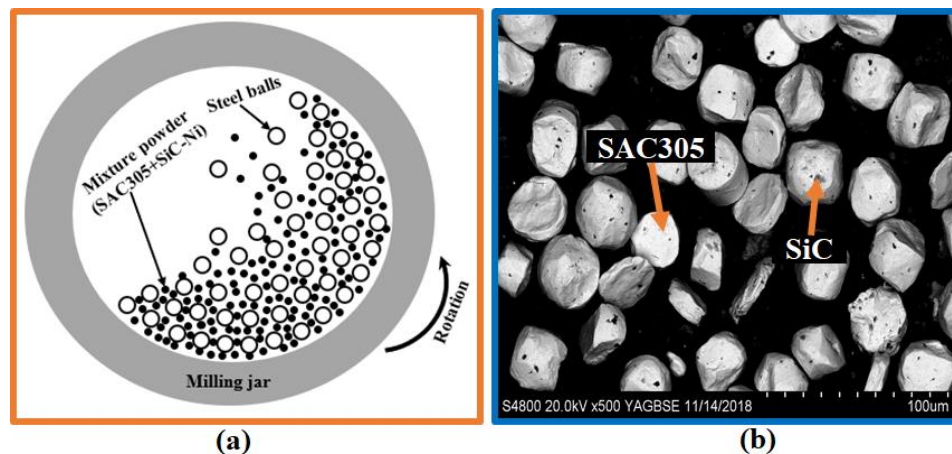



Figure 3.4 (a) Schematic diagram of ball milling with mixture powder (matrix and reinforcement) [149] (b) SEM micrograph of SAC305/SiC after ball milling

### 3.3 Results and discussion

#### 3.3.1 Microstructural evolution of lead-free solder composite

Post-processing and experimentation on coating Ni on SiC particles and reinforcing the SiC and SiC(Ni) into SAC305 solder matrix and mounting, the microstructural examinations were

conducted by using SEM. The first investigation is the microstructure of the SiC reinforced SAC305 matrix. **Figure 3.5 (a–b)** shows the distribution of the SiC in the SAC305 solder matrix at lower and higher magnification; however, EDS analysis confirmed the presence of the SiC in the matrix.

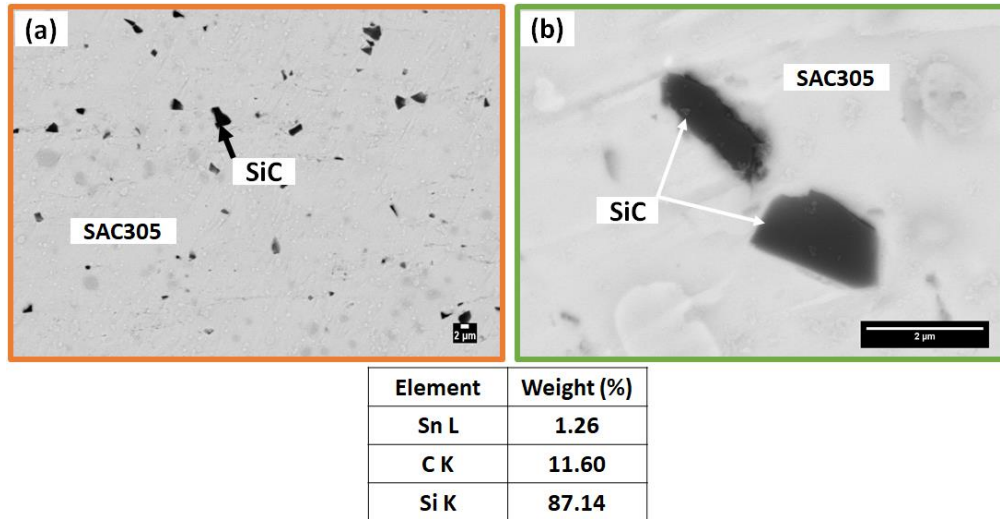

*Figure 3.5 Distribution of SiC in the SAC305 solder matrix (a) lower magnification (b) higher magnification (c) EDS data*

**Figure 3.6 (a–d)** shows the SEM micrograph of the SAC305 solder composite with addition of 0, 0.5, 1.0 and 1.5% SiC(Ni). The SAC matrix with 0 wt% SiC showed no defects or cracks. However, with the inclusion of ceramic SiC particles, cracks, and defects are developed in the solder matrix. Pores and agglomerates of SiC reinforcements were noticed in the matrix which did not join completely with SAC particles. As the concentration of SiC increased in the matrix, more pores, more agglomerates, and thicker grain boundaries are visible due to the SiC agglomeration. The first observation from microstructural examinations shows that by increasing the content of SiC(Ni) above a certain limit in the matrix, the bonding between the lead-free solder and reinforcement particles decreases which would have adverse effects on the final mechanical properties of the composite. **Figure 3.6 (b–d)** attached below, shows the composite microstructure with pores associated with the SiC(Ni) reinforcements. Porosity is of significant interest for research as the mechanical properties depend directly on the porosity in the matrix. The least amount of defects were found in the pore lead-free solder (**Figure 3.6 (a)**).



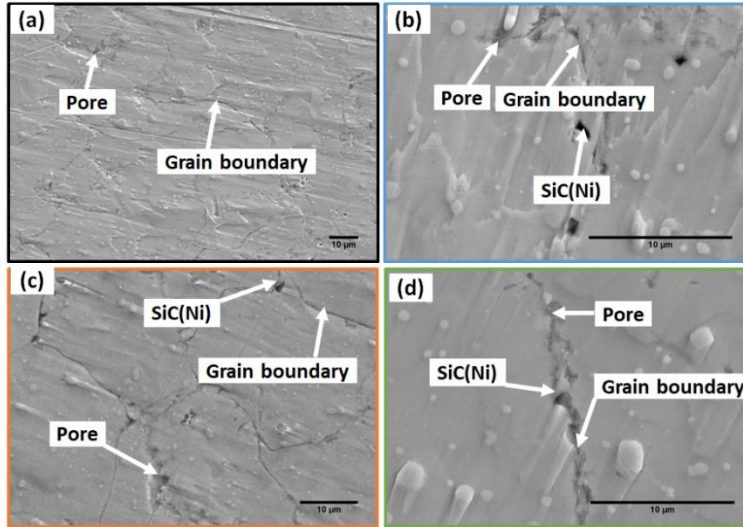


Figure 3.6 SEM micrographs of SAC305 solder with addition of (a) 0 (b) 0.5 (c) 1.0 and (d) 1.5 wt% of SiC(Ni)

### 3.3.2 Physical properties

#### 3.3.2.1 Relative density

Density is an important parameter to be considered while selecting a solder material. Hence, it is considered before carrying on further investigations with ceramic reinforced lead-free solders. The particles come into contact, a neck growth develops, and the neck then becomes larger in the early stages of heating the sintering process. As the sintering time is extended, the particles are completely merged to form larger particle grains that are about 1.26 times larger than the diameter of the original particles. Also, the pores that are initially trapped between the particles are reduced during sintering [150].

**Figure 3.7 and Figure 3.8** shows the relative density of SAC305 PM composite samples with varying composition of Sic and SiC(Ni). The following equation is used for the calculation, Eq. (3.1).

$$\rho = \frac{(g_2 - g_1) - (g_3 - g_4)}{(g_2 - g_1) \cdot \left(\frac{1}{\rho_f} - 0.0012\right)} \quad \text{Eq. (3.1)}$$

Where,  $g_1$  (g) is the weight of hook in air,  $g_2$  (g) is the total weight (weight of hook and weight of sample) in the air,  $g_3$  (g) is the total weight (weight of hook and weight of sample) in the water and  $g_4$  (g) is the weight of hook in the water,  $\rho_f$  ( $g/cm^3$ ) is the density of water.

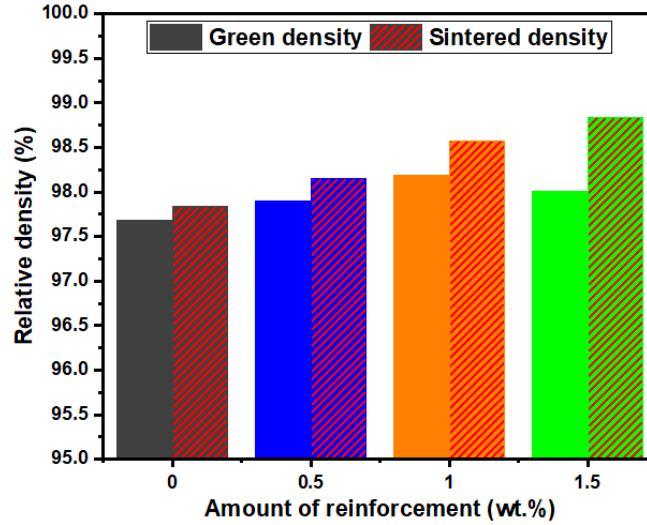


Figure 3.7 Relative density of SAC305 lead-free solder PM composite samples with the addition of SiC

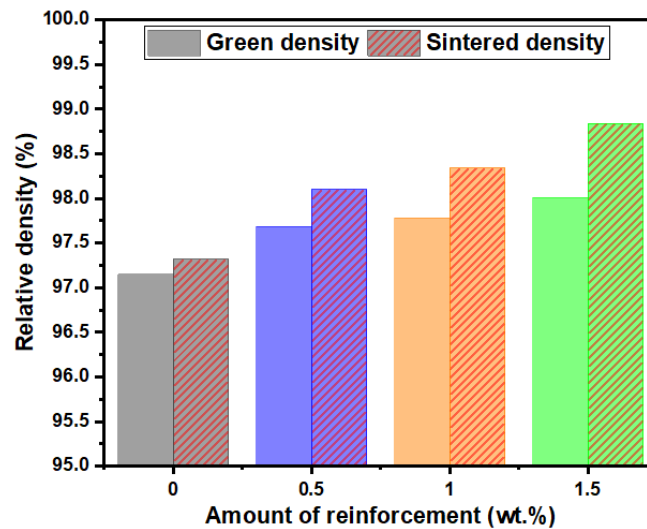


Figure 3.8 Relative density of SAC305 lead-free PM solder composite samples with the addition of Ni coated SiC

Monolithic lead-free solder (0wt.%SiC or Ni-coated SiC) shows a small difference of relative density between green and sintered lead-free solder as shown in **Figure 3.7** and **Figure 3.8**. In other compositions (0.5%, 1%, and 1.5%) of lead-free solder composites, the relative densities were varied with the weight percentage of reinforcement. The green density is affected by its micro-porosity. The sintered density can be increased by adding much smaller particles (reinforcement) providing the gap between the larger ones. In general, the sintered density increases with the range of particle size distribution, and this trend is more pronounced in more

densely arrangements than in loosely packaged ones [151]. Ni-coated SiC is more homogeneously distributed in the lead-free solder matrix than the SiC reinforcement and it filled the gap more than the SiC particles due to metallic bonding. All samples are pressed at 200 MPa and provide high-density values (both green and sintered) and indicate the higher relative density in all compositions [152].

### 3.3.2.2 Porosity analysis

As mentioned in the above sections, porosity is a really important parameter in the fabrication of lead-free solders as it directly affects the mechanical properties. Porosity depends on the grain refinement of the matrix and hence we assume naturally that porosity would have a negative effect on grain refinement [153]. The pores are understood to form as a result of the non-uniform distribution of SiC particles in the SAC305 powder matrix.

In addition, the pores that are initially trapped between the particles are reduced during sintering. The porosity reduction during sintering where the pores between the grain boundaries are reduced, resulting in a denser sintered material. These initial large pores become spherical and smaller after sintering [150]. Hence, after a series of careful trial and error run of experiments, the reinforcement composition was limited to 1wt% of both SiC or SiC(Ni) particles.

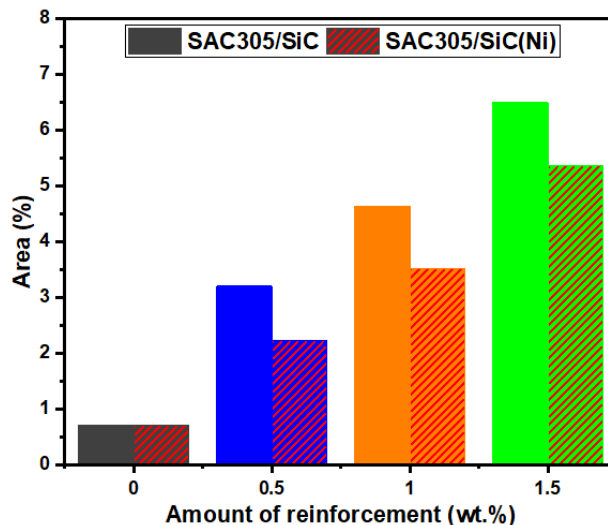


Figure 3.9 Porosity analysis of the SAC305 solder composite with the addition of SiC and SiC(Ni)

We can observe higher porosity for the samples at 1.5wt% reinforcement (**Figure 3.9**). We can also observe the trend that the larger the content of reinforcement, the greater is the pore size (avg).

The increasing number of reinforcement particles leads to a higher irregularity of pores [54]. In the present work, **Figure 3.9** which has 1.5wt%SiC(Ni) reinforcement in SAC305 solder showed the highest ratio of porosity. All other samples show pores and agglomerates of SiC(Ni) particles in between the SAC305 matrix. There is no complete bond between these agglomerates and matrix particles. The percentage of pores in composite increase with an increase in the amount of reinforcements and monolithic lead-free solder is showing the least amount of agglomerates and porosity and 1.5wt.% reinforced SAC305 solder composite showing the highest amount of agglomerates and porosity. Fine microstructure and reduces the porosity which may translate into increased solder reliability. SiC is a ceramic bonded material and it is not contacted directly to the lead-free solder material, however, Ni is a metallic material and it is easily contacted to the lead-free solder particles during the sintering process and fill the gap between the reinforcement and the matrix.

### **3.3.3 Compressive strength of the PM solder composite**

Compressive strength is another mechanical property that needs measurement to effectively determine the solder composite strength. Homogeneous distribution of reinforcement particles means more refined phases which inhibit mechanical deformation more effectively.

The compressive strength of SiC and Ni-coated SiC reinforced lead-free solder composite are shown in **Figure 3.10**. The increase in reinforcement content increased the strength of the solder composite under compression. The maximum value for SiC and Ni-coated SiC addition was obtained at 1.0wt.% but beyond this, the compressive strength decreased again. The average compressive strength for monolithic SAC305 (0wt.%SiC or Ni-coated SiC) solder was 34.21MPa while for 1wt% reinforced composite the compressive strength was 42.75MPa for SiC and 45.29MPa for Ni-coated SiC.

Strength is increased due to the addition of ceramic particles because ceramic particles have a higher hardness. In general, the strength of metal matrix composites increases due to the decrease in elongation [82]. However, the strength is still higher than the monolithic sample. For a 1% added reinforcement sample, the strength decreased compared to 1.5% by weight because of the presumed increased porosity.

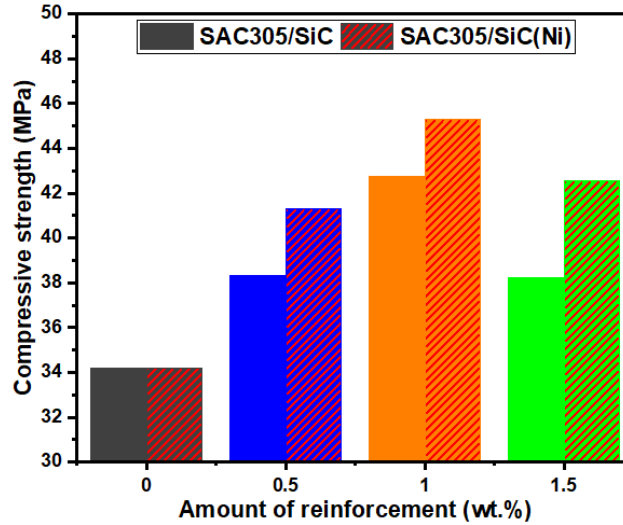


Figure 3.10 Compressive strength of the SAC305 lead-free solder composite with the addition of SiC and SiC(Ni)

However, the addition of reinforcement particles has some negative effects, including increased porosity in liquid processes. On the other hand, it has been reported that in powder metallurgy methods, the addition of reinforcement particles should not exceed a certain limit, otherwise the properties will decrease because of the increased number of reinforced particles may increase the number of micro-pores. In this study in 1wt.% reinforced sample has the optimum compressive strength. Microscopic pores determine the strength because these are potential zones of crack initiation that ultimately lead to failure [51, 82, 106].

### 3.3.4 Relative contact perimeter (RCP) of reinforcement and matrix

Contact perimeter is defined as a contact surface between metallic solder and ceramic reinforcement particles. Some reinforcement particles are not fully connected with the surface of the metallic solder i.e non-contact perimeter. The contact and non-contact perimeter of SiC and SiC(Ni) particles are determined by ImageJ software. In **Figure 3.11(a)**, the black line indicated the non-contact perimeter, and the rest of the portion is the contact perimeter. Following these analyses carried out for all the samples, the relative contact perimeter follows from following Eq. (3.2).

$$RCP = \frac{P_c}{P_c + P_{nc}} \cdot 100 \quad Eq. (3.2)$$

Where, RCP is relative contact perimeter,  $P_c$  ( $\mu\text{m}$ ), and  $P_{nc}$  ( $\mu\text{m}$ ) are contact and non-contact perimeter respectively. The maximum RCP was found at 1.5wt.% of reinforcement while the minimum RCP was found for 0.5wt.% SiC reinforcement. **Figure 3.11(a)** shows the RCP of the matrix and the reinforcement particle. **Figure 3.11(b-c)** shows the SEM micrograph of lead-free solder composite with contact and non-contact interfaces between the matrix and reinforcement.

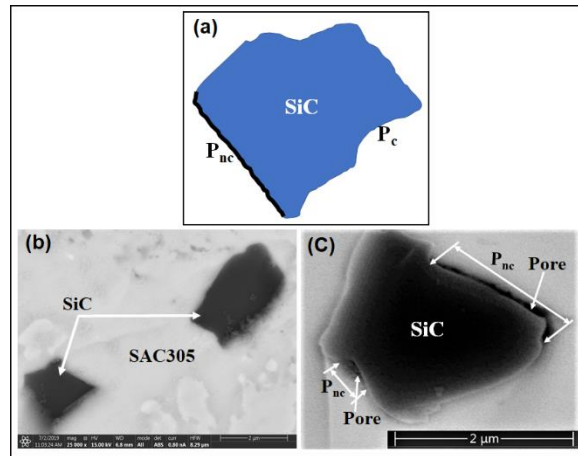


Figure 3.11 (a) Schematic diagram of contact and non-contact perimeter analysis (b) SEM image of SAC305/SiC composite solder (c) SEM micrograph of SAC305 solder composite with contact and non-contact interface

**Figure 3.12(a)** shows the SEM micrograph of the lead-free solder composite with the reinforcement (SiC or Ni-SiC) particle and **Figure 3.12(b)** indicates the segmented reinforcement particles in the matrix, which was measured the RCP. The process of evaluating the RCP is shown in **Figure 3.13**.

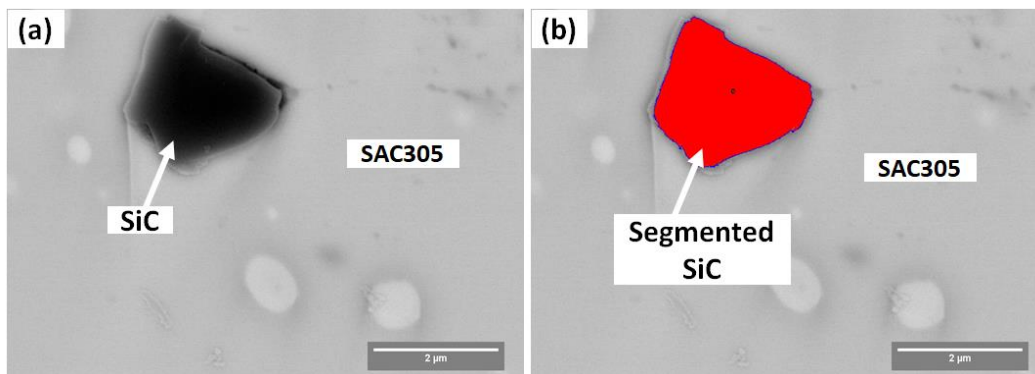


Figure 3.12 (a) SEM micrograph of the SAC305 lead-free solder with the addition of SiC particle (b) Segmented SiC particle in the solder matrix

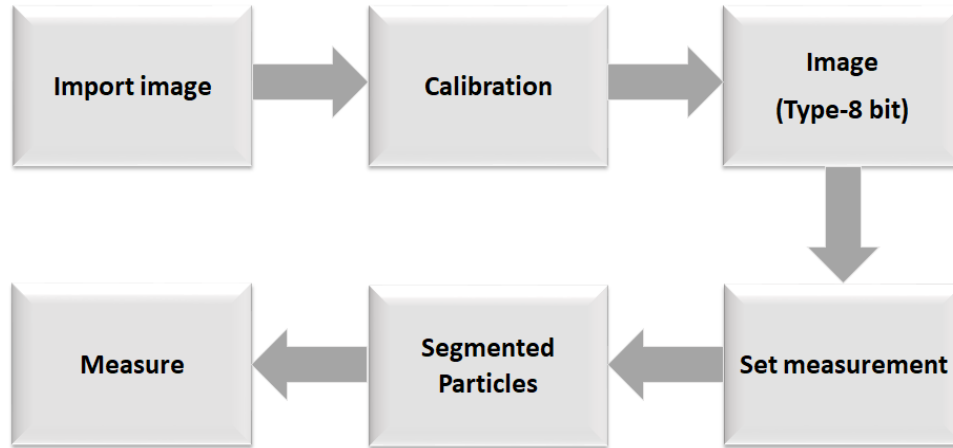


Figure 3.13 Process of measurement of the RCP of the reinforcement particles

**Figure 3.14** shows the results of the RCP of lead-free solder composites at a different weight fraction of SiC and SiC(Ni). The interface of SiC and SAC305 has poor mechanical bonding which is a direct effect on the result of weak adhesion and additionally agglomeration of SiC particles was also observed. To reduce the agglomeration and to improve the adhesion between SiC and SAC305, the coating of SiC with Ni was carried. Some portion of the reinforcement (SiC and SiC-Ni) was found not to be in complete contact with the lead-free solder i.e. loss of adhesion (deadhesion). Compared to SiC reinforcement, SiC(Ni) reinforcement has shown improved adhesion with SAC305.

During this study, Ni surface coating was applied on SiC to overcome the weak bonding between lead-free solder and SiC particles. Silicon carbide consists of two types of atoms, the first is silicon atoms and the second is tetrahedral carbon atoms which have strong bonds in the crystal structure. Silicon carbide is a ceramic material with a covalent bond and has stable chemical properties. Ni is a metallic bonded material and it has good wetting characteristics with Sn-based solder because SAC solder has also metallic bonding. In these solder composites, SiC(Ni) is reacted with the SAC305 solder and forms a strong metallic-metallic bond at the interface between reinforcement and solder matrix [140].

**Figure 3.11(c)** shows that the matrix particle was not filled between the two SiC particles. Therefore, it is concluded that stress concentration has existed between the two particles easily under external load, which reduces the interfacial bond strength of the composite. The result of **Figure 3.14** shows that the SiC content decreases the contact between the particles and Ni appears at the appropriate position. It is presumed that the Ni particles promote the RCP of SiC in the

solder matrix and avoids direct contact between two or more SiC particles due to metallic bonding. Therefore, micropore formation and agglomeration are significantly reduced. The highest RCP was measured in SiC(Ni) reinforced samples (1.5wt%), while the lowest is in the case of 0.5wt% SiC reinforcement. It is also observed that with the addition of Ni-coated silicon carbide, the relative contact perimeter of composite solders increased drastically.

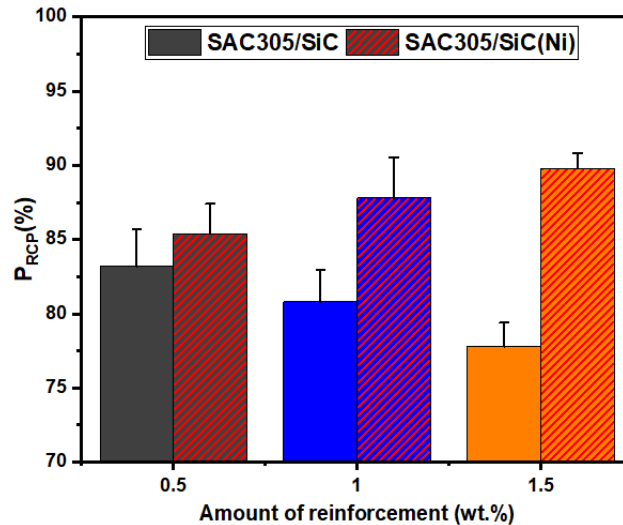


Figure 3.14 Relative contact perimeter of SAC305 lead-free solder composite with the addition of SiC and SiC(Ni)

### 3.3.5 Average neighboring particles distance

The strength of the interface between reinforcement particles and the matrix particles can be defined by the average neighbor's particle distance. Thakur et al. [154] studied that the percent of particles contacting, and the inter-particle distance sufficiently describe the agglomeration and dispersion of reinforcement particles in the matrix. The poor dispersion of the particles is due to the agglomeration of the particles in the matrix and may lead to the weakening of the mechanical properties.

The average neighbor's particle distance,  $d_{mn}$ , is defined as the distance between the centers of gravity between neighboring particles in a matrix. It is not analogous with the mean free path between the particles and closest neighbor distance. In estimating the impact on the matrix of the reinforced particles, the distribution of both SiC and SiC(Ni) reinforcement particles were analyzed by Cprob. **Figure 3.15 (a)** demonstrates a schematic outline of estimating the average



neighbor's particle distance and **Figure 3.15 (b)** shows the average neighbor's particle distance image generated by software Cprob.

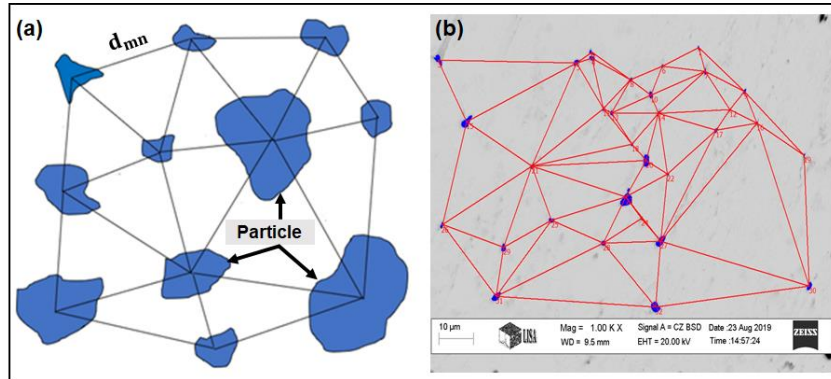


Figure 3.15 (a) Schematic diagram of the neighbor's particle distance (b) Average neighbor's particle distance image generated by software (Cprob)

**Figure 3.16 (a)** depicts the variation in average neighbor particle distance,  $d_{mn}$  between the reinforcement and matrix particles for various weight fractions. Overall, the distribution of  $d_{mn}$  values suggests a consistent pattern with processing. The parameter  $d_{mn}$  is used to distinguish the different MMC. Thus, it is an identifier for measuring the dispersion of the reinforcement in the solder matrix. However, a useful technique average neighbor particle distance has proven, it has certain drawbacks. For instance, if the neighbor's particle distance technique is applied to a composite system in which the particles are bunched together in gatherings of at least two, the subsequent closest neighbor's distance tends to the particle diameter, erroneously indicating best clustering, if the second, third, fourth, and so on neighbor's distances are considered [155-157].

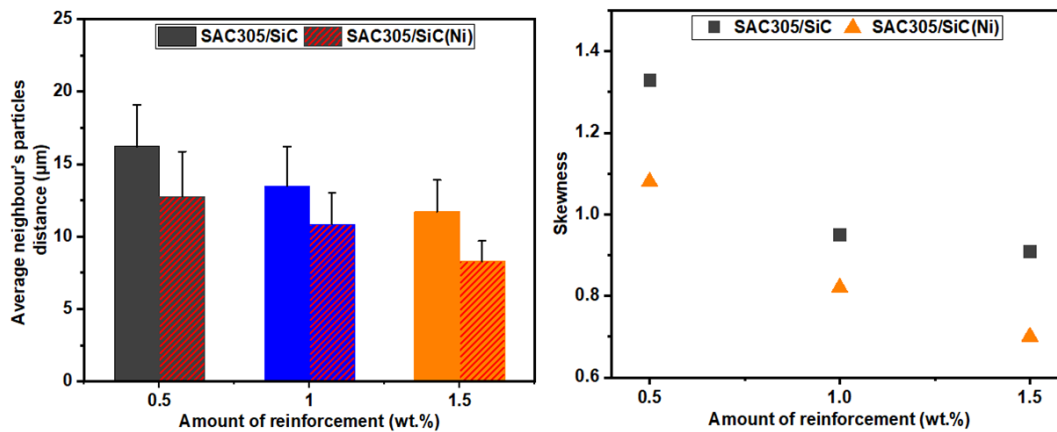


Figure 3.16 (a) Average neighbor's particle distance of SAC305 solder composites with the addition of SiC and SiC(Ni) (b) Skewness of SAC305 solder composites

Where,  $d_{mn}$  is the distance between neighbor's particles, m is the first particle, and n is the neighbour's particle. Higher average inter-particle distance inside the matrix might affect the mechanical properties of the composite. The quadrat analysis of the lead-free solder composite is shown as a skewness diagram of the number of SiC & SiC(Ni) particles/quadrant,  $N_q$  in **Figure 3.16 (b)**. Skewness diagram reveals that the overall shape of the  $N_q$  distribution varies significantly with the degree of clustering. An increase in the amount of reinforcement particle clusters has skewed the  $N_q$  distribution further. Skewness ( $\beta$ ) indicates the degree of asymmetry in the statistical distribution, which is represented by the Eq. (3.3) below [155].

$$\beta = \frac{(q)}{[(q-1)(q-2)]} \sum \left[ \frac{(N_{qi} - N_q^{mean})}{(\sigma)} \right]^3 \quad \text{Eq. (3.3)}$$

Where,  $\beta$  = Skewness

$q$  = Total number of quadrats studied,

$N_{qi}$  = Number of SiC or SiC(Ni) particles in the  $i^{\text{th}}$  quadrat ( $i = 1, 2, \dots, q$ ),

$N_q^{mean}$  = Mean number of SiC or SiC(Ni) particles per quadrat, and

$\sigma$  = Standard deviation of the  $N_q$  distribution

An increase in  $\beta$  indicates the increase in reinforcement clusters [155, 157]. **Figure 3.16 (b)** shows a variation in  $\beta$  with the varying weight fraction of SiC and SiC(Ni). The skewness ranges between 1.3 to 0.91 for SAC305/SiC composite and between 1.08 to 0.7 for SAC305/SiC(Ni) composite. We see the skewness for SAC305/SiC(Ni) is much broader compared to SAC305/SiC composite solder, which is in agreement with the dissemination of reinforcement particles in lead-free solder. Exact statistical relation can be utilized comfortably for determining the cluster distribution using the quadrant analysis. In conclusion, the analysis of reinforcement distribution is an important factor because it is improved the dispersion of reinforcement particles in the MMCs. In both reinforcements, it is small changes in skewness i.e. impact of Ni coated SiC is more than SiC.

### 3.3.6 Morphological mosaic analysis

The general definition of a mosaic picture is a segmented picture of a plane. Each class of the segment has a mark. Segments are usually produced under object-oriented image coding where the image is partitioned into homogenous zones. The clustering of particles in the matrix is demonstrated by cell size appropriation and the segmented binary was investigated further.

Another technique is the morphological mosaic analysis. Under this method, there arises the issue of characteristic point and it generally overlooks object form. This method requires a constant dilation of the objects, tessellation based on the size and state of the object. However, analyzing the size of the cell carrying from mosaic would reveal the cluster of objects.

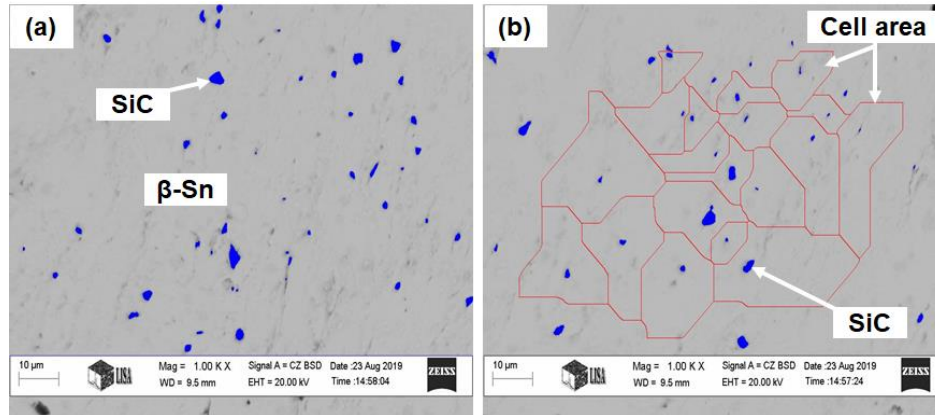


Figure 3.17 (a) Analyzed segmented SEM micrograph of SAC305 solder with the reinforcement (b) Morphological mosaic of the image.

FIB-SEM micrographs are taken from the polished samples of the inspected tests of SAC305 solder with the addition of SiC and Ni-coated SiC. The blue colored particles belong to reinforcements (SiC and Ni-SiC) in the micrograph. The cells in which the reinforcement's particles are distributed are visible in **Figure 3.17(a)** and **Figure 3.17(b)**. Larger and smaller mosaic structures can be seen. In this manner, the size (region) dissemination of the cells is considered and the size (area) distribution of cells is studied. **Figure 3.18(a)** shows the larger effect in SAC305/Ni-SiC solder composite. The average cell area of both composite solders seen to increase as the weight fraction of reinforcement increased, **Figure 3.18(b)** shows the skewness variation of both composites and Ni-coated SiC reinforced composite skewness is much lower than SiC composites i.e. Ni is very effective in the distribution of the particles in the SAC305 solder matrix [157].

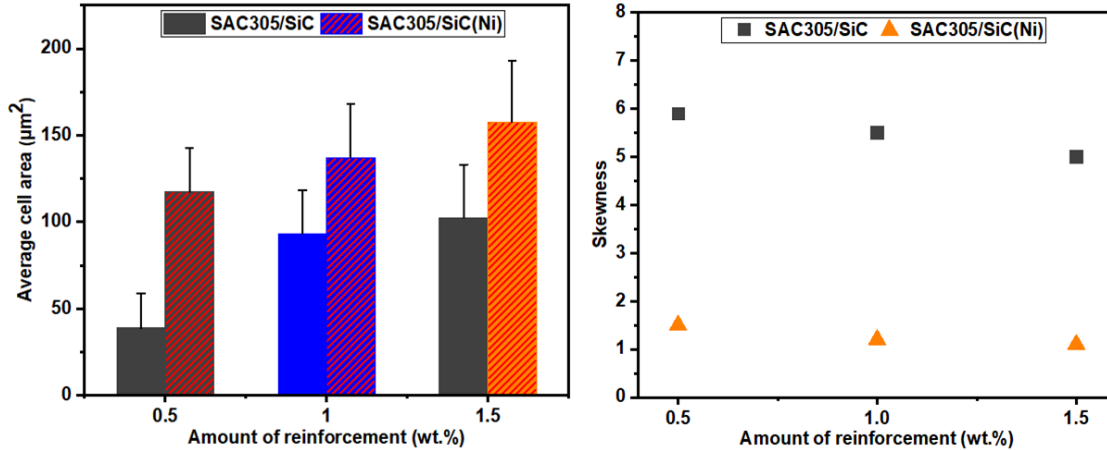


Figure 3.18(a) Average cell area of SAC305 solder composites with the addition of SiC and Ni-coated SiC (b) Skewness of SAC305 solder composites

### 3.4 Summary

The homogeneous distribution of the reinforcements in the matrix is very important for the composite material because it is directly affected the mechanical properties of the composite. It was achieved by the powder metallurgy method, Ni-coated silicon carbide (SiC-Ni) are synthesized by EN (Electroless nickel) method, and PM composites were fabricated. Microstructural analysis, physical and mechanical properties were comparatively studied of lead-free solder composite. RCP (relative contact perimeter), average neighboring particles distance, and morphological mosaic are investigated by the Cprob and ImageJ software. SiC particles were perfectly coated with Ni particles by electroless nickel plating method (Figure 3.2) and SiC and SiC(Ni) particles were homogeneously distributed in lead-free solder matrix by ball milling (Figure 3.5). The relative density of sintered and green samples was increased with the increase of the reinforcement composition, however, Ni-coated SiC composite solder samples have higher relative density than SiC reinforced samples. Ni-coated SiC reinforced composite solder has a lower porosity than SAC305/SiC composites and porosity was increased with an increase of composition. SAC305/SiC(Ni) solder composite has higher compressive strength than the SAC305/SiC and the maximum is shown at 1% composition. RCP (relative contact perimeter) was increased with an increase of Ni-coated SiC reinforcement in the solder, however, in the case of SiC reinforcement, it was decreased with an increase of composition. The average neighbour's particle was decreased with the addition of reinforcements.

## 4 CHAPTER 4: Morphology and IMCs of composite solders under reflow and thermal aging

### 4.1 Introduction

Thermal aging and reflow testing at low and high temperatures are the main approaches to evaluate the reliability of solder joints, as the microstructure and mechanical properties of solder joints deteriorate at relatively high operating temperatures. In this chapter, we evaluated and discussed morphology (including solder matrices and interfacial IMCs) and microhardness as a mechanical property to understand the performance of composite solders fabricated under reflow and isothermal aging conditions.

### 4.2 Experimental procedures

#### 4.2.1 Preparation of samples for reflow and thermal aging

To perform the reflow and thermal aging test, a cylindrical sample (3:3 mm in diameter and height) containing two different reinforcements with different compositions were soldered on the Cu substrate. These two types of composite solders were SAC/SiC and SAC/SiC(Ni). **Figure 4.1** shows the top and front view of the specified tool, which was used for preparing the samples. This tool was specifically designed and fabricated by the Institute of Physical Metallurgy, Metal forming, and Nanotechnology, University of Miskolc. The weight of the powder and the compaction pressure was 0.1g and 200MPa. (SAC305) $_{100-x}$ (SiC) solder powder was uniaxially compacted in a die (cold pressing at room temperature) to form a cylindrical bar of 3 mm in diameter. The base/substrate was a square copper plate (15 × 15mm) was grinded from sandpaper to achieve a smooth surface for the measurement of contact angle ( $\theta$ ), spread factor ( $S_f$ ), and spread ratio ( $S_r$ ) of the solder, 2mm thick copper sheet. Acetone was used to clean and polish the copper plate. A small amount (0.02g) of activated rosin (RA) flux was used on the surface of the sample and in between the solder sample and the Cu substrate. The main objective of the flux is to eliminate oxidation and other contaminants before and during the melting process.

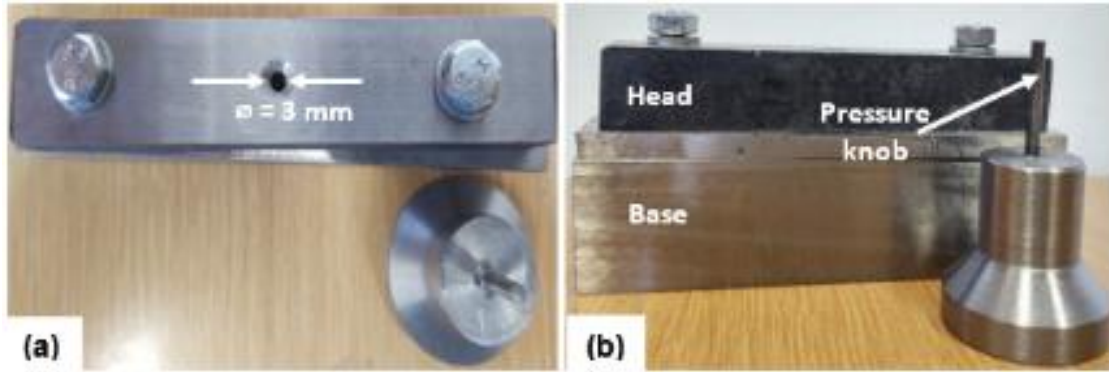


Figure 4.1 Specific tool for preparation of samples (a) top view (b) front view

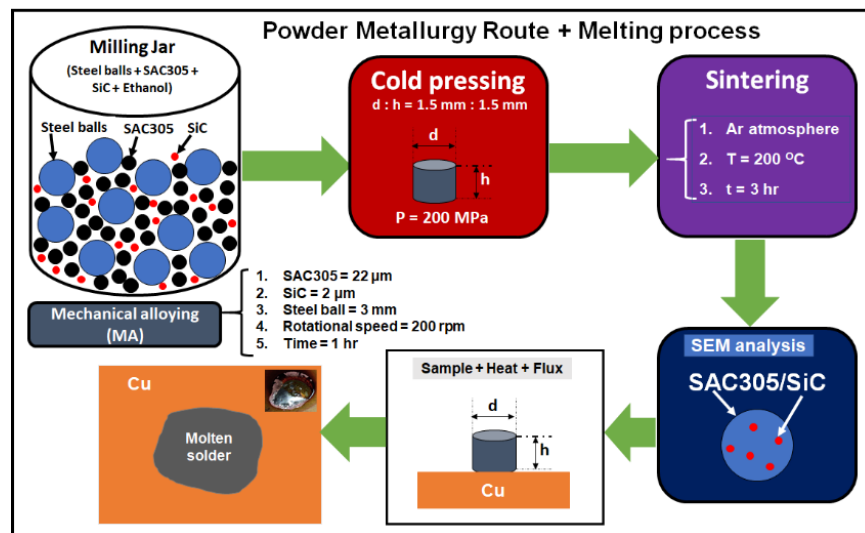


Figure 4.2 The schematic diagram of the powder metallurgy and melting process of the composite solder

**Figure 4.2** depicts the schematic diagram of the powder metallurgy and melting process of the composite solder. The solder sample was put on the center of the copper substrate and then the reflow process was conducted. Then, the samples were put in the furnace for melting. In chapter 2, it is proven that 1%SiC composition is optimal as compared to other weight percentages (0, 0.5, 1, and 1.5). SAC305/1%SiC is melted at various reflow temperature (240°C, 260°C, 280°C, and 300°C) at different time (30, 60, 90, & 120min.). When performing the thermal aging test, the thermal aging temperature was set to 140°C, 150°C, 160°C, and 170°C, while the thermal aging times were 0, 25, 50, 75, and 100h. Different samples that perform at different thermal aging times were studied concerning the evolution and hardness of their microstructure. The detail of experimental conditions can be seen in **Table 4.1**, **Table 4.2**, and **Table 4.3**

Table 4.1 Experimental analysis of SAC305/SiC and SAC305/ SiC(Ni) composite solder

Composite solder	Atmosphere	Reflow temperature (°C)/Time (min.)	Aging temperature (°C)/Time (h)	Results
SAC305/xSiC, x = 0, 0.5, 1 & 1.5	Room temperature	260, 30	140, 100	<ul style="list-style-type: none"> <li>• Microstructures (Fig. 4.3 and Fig. 4.4)</li> <li>• Microstructures at interfaces (fig.4.6-Fig. 4.8)</li> <li>• IMCs layer thickness (fig. 4.11-Fig. 4.13) (Table 4.4 and Table 4.5)</li> <li>• Hardness (Fig. 4.15)</li> <li>• Contact angle (wettability) (Fig. 4.17)</li> <li>• Spread ratio, spread factor (Fig. 4.18 and Fig. 4.19)</li> </ul>
SAC305/xSiC(Ni), x = 0, 0.5, 1 & 1.5				

Table 4.2 Experimental analysis of SAC305/1%SiC composite solder at different reflow time and temperature

Composite solder	Atmosphere	Reflow temperature (°C)	Reflow time (min.)	Aim
SAC305/1% SiC	Room temperature	240°C	30, 60, 90, & 120	<ul style="list-style-type: none"> <li>• Microstructures at interfaces (Fig.4.21)</li> <li>• IMCs layer thickness [multiple reflows (Fig. 4.22 and Table 4.6)]</li> <li>• IMCs layer thickness (Table 4.7, Fig. 4.23-Fig.4.25)</li> <li>• The activation energy (Table 10 and Fig. 4.31)</li> </ul>
		260°C		
		280°C		
		300°C		

Table 4.3 Experimental analysis of SAC305/1%SiC composite solder at different aging time and temperature

Composite solder	Atmosphere	Aging temperature (°C)	Aging time (h)	Aim
SAC305/1%SiC	Room temperature	140°C	25, 50, 75, & 100	• Microstructures at interfaces (Fig. 4.26)
		150°C		
		160°C		

		170°C		<ul style="list-style-type: none"> <li>• IMCs layer thickness (Table 4.8, Fig. 4.27-Fig.4.29 )</li> <li>• The activation energy (Table 11 and Fig. 4.32)</li> </ul>
--	--	-------	--	---

### 4.3 Results and discussion

#### 4.3.1 Microstructural evolution in the solder matrix

For microstructural observation, all samples were first mounted in epoxy before being grinding and polishing after different reflow and aging process. All polished samples were etched with etching reagent; the metallographic etching reagent consists of a mixture of ethanol and hydrochloric acid. The morphologies of the solder matrix and solder joints at the solder/Cu interface were examined using a FIB–SEM (Focus ion beam-scanning electron microscope).

All the composite solders with different composition (0, 0.5, 1, and 1.5%) reinforcement and 100h aging at 140°C were determined for a comparative study of the microstructural examination of the solder matrix; the morphology of the matrix structures of the different solder with the addition of SiC and SiC(Ni) are shown in **Figure 4.3** and **Figure 4.4**.

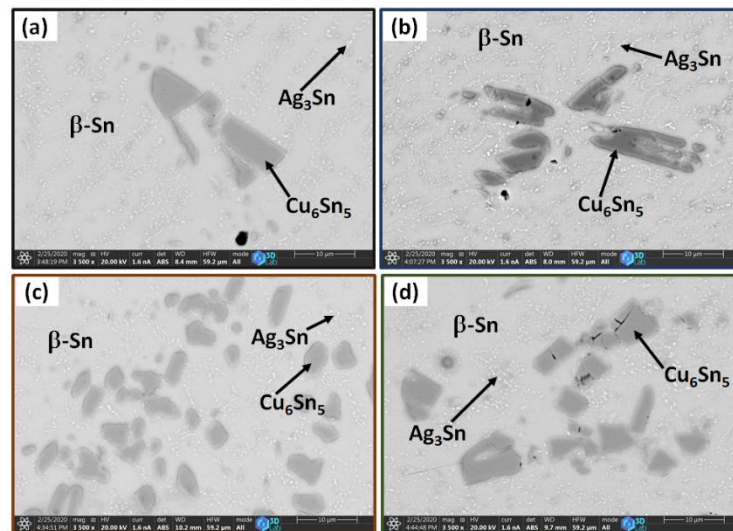


Figure 4.3 Microstructure of SAC305/xSiC solder composites after 100 h aging (a) monolithic SAC305 (b) 0.5% (c) 1.0% (d) 1.5%

After 100h aging, it can be observed that the grain boundary of the  $\beta$ -Sn phase disappeared, while the  $\text{Ag}_3\text{Sn}$  IMC showed coarsening and  $\text{Cu}_6\text{Sn}_5$  has a rod-like structure in the monolithic SAC305



(0wt.%SiC or Ni-coated SiC) solder matrix. It can be seen that after the addition of SiC and Ni-coated SiC, the size of  $\text{Ag}_3\text{Sn}$  IMC and  $\text{Cu}_6\text{Sn}_5$  IMC decreased significantly compared to monolithic SAC305 solder. As discussed in the literature [9] that the added reinforcement particles tend to adsorb to the IMC surface during the melting process; interatomic diffusion is thus reduced. After 100h of aging, the grain boundary of the  $\beta$ -Sn phase also becomes disappeared in the SAC305/1.0%SiC matrix; however, the total size of the IMCs range was smaller than for monolithic SAC305 alloy. In addition, the size of  $\text{Ag}_3\text{Sn}$  and  $\text{Cu}_6\text{Sn}_5$  IMCs showed an increasing trend in the aged composite solder matrix; however, the rate of increase was smaller than that of the monolithic SAC305 sample. In the SAC305/1.0%SiC matrix, it was also observed that the growth of  $\text{Ag}_3\text{Sn}$  and  $\text{Cu}_6\text{Sn}_5$  IMC was suppressed and their size was smaller than that of the monolithic SAC305 solder. In the case of SAC/SiC(Ni), the most obvious phenomenon is that after 100h of aging, abundant bulky  $(\text{Ni}, \text{Cu})_6\text{Sn}_5$  IMCs were formed in the solder matrix. This may be due to nickel atoms that were not fully reacted in the solder matrix in the reflow process and some atoms are continued to participate in the inter-diffusion reaction with the copper substrate and tin atoms in the aging process, thereby  $(\text{Ni}, \text{Cu})_6\text{Sn}_5$  IMC layers were formed.

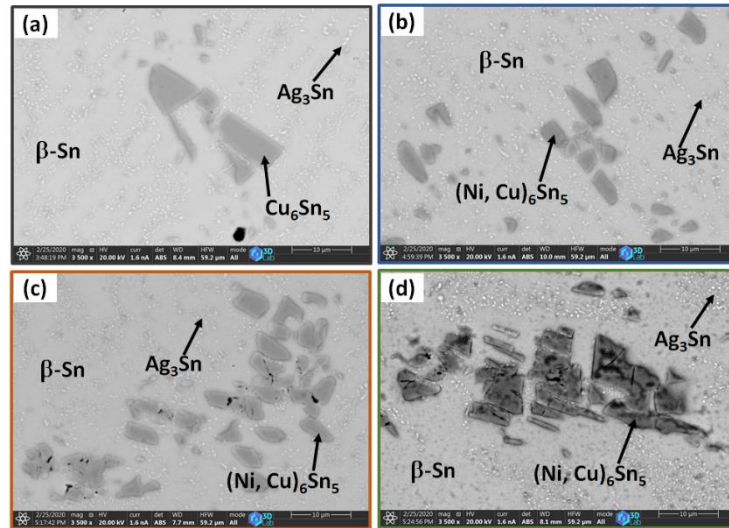


Figure 4.4 Microstructure of SAC305/xSiC(Ni) solder composites after 100h aging (a) monolithic SAC305 (b) 0.5% (c)1.0% (d) 1.5%

The reinforcement of SiC and SiC(Ni) particles affects the growth and size of the IMC in the solder matrix. Compared to the monolithic solder, the IMC size of the solder composite is smaller carrying 0.5wt.% and 1.0wt.%SiC and SiC(Ni) particles. Lin et al. [98] reported similar results in

the refinement of IMCs growth. However, for the other composition (1.5%) of the solder composites, the IMCs size have homogeneous and it did not reduce with increasing of SiC and SiC(Ni). The refinement of the grain size can be attributed to the segregation and agglomeration of SiC and SiC(Ni) particles in bulk solder because the van der Waals forces cause the reinforcement particles to connect with each other. The morphology and size of the IMCs are a very important parameter to investigate the influence of the reinforcement in the solder composite. The IMCs were refined with the addition of the SiC and SiC(Ni) particles to the SAC305 solder.

**Figure 4.3** and **Figure 4.4** shows the SEM image of the composite solder with the addition of the SiC and SiC(Ni); however, the development of the  $\text{Cu}_6\text{Sn}_5$  (gray),  $\text{Cu}_3\text{Sn}$ ,  $\text{Ag}_3\text{Sn}$ , and  $(\text{Ni,Cu})_6\text{Sn}_5$  (dark) IMCs are analyzed by EDS. The IMCs size is analyzed by ImageJ software and approximately 100 particles are considered. The average size of  $\text{Ag}_3\text{Sn}$  and  $\text{Cu}_6\text{Sn}_5$  IMCs particles were identified as 1.0 to 2.5  $\mu\text{m}$  and 2 to 4  $\mu\text{m}$  in the SAC305/SiC lead-free composite solder. SiC particles were coated with nickel because the presence of IMCs in the SAC305/SiC alloy is not sufficient to provide alloy strength. The addition of small amounts (1%) of SiC(Ni) particles in the SAC305 solder alloys shows that the average size of IMCs [ $\text{Ag}_3\text{Sn}$  and  $(\text{Ni,Cu})_6\text{Sn}_5$ ] grains were reduced and this is due to the strong adsorption effect of the reinforcing particles [36]. Decreasing the IMCs are followed by the theory of heterogeneous nucleation and adsorption effect [24, 28]. Ni has a higher adsorption effect and it decreases the surface energy and therefore decreases the growth velocity of IMCs .

The reduction of IMCs grains in the composite solders also indicates the grain refining effect is caused only by the addition of nickel-coated silicon carbide. The average size of  $\text{Ag}_3\text{Sn}$  and  $\text{Cu}_6\text{Sn}_5$  grains were identified as 0.5 to 1.5 $\mu\text{m}$  and 1 to 2.5 $\mu\text{m}$  in the SAC305/SiC(Ni) lead-free composite solder. SiC particles provide the supplementary nucleation sites for the development of refined IMCs ( $\text{Ag}_3\text{Sn}$  and  $\text{Cu}_6\text{Sn}_5$ ) and it was observed that SiC particles and IMCs prevent dislocation slippage and thus helped to a strong strengthening effect in composite solder. Such IMCs are played a key role in the matrix since IMCs provide the strength of the matrix  $\beta\text{-Sn}$  [29, 33].

It is observed that the best morphology of the SAC305/SiC and SAC305/Ni-SiC are achieved at 1.0wt.% of reinforcements because it shows the fine refinement of the IMCs in the solder composites, after that the particle size of the IMCs are increased by 1.5wt.% (**Figure 4.3(c)** and **Figure 4.4(c)**). The SiC and Ni-coated SiC particles have been observed to be present in agglomerated form, causing cracks and pores to form in the composite, as shown by the enclosed

areas. This can be related to the high amount of SiC and SiC(Ni) in the molten matrix (1.5wt.%), the distance between the particles decreases, and the particles get closer to the formation of agglomerates and are easily segregated.

#### 4.3.2 Microstructural evolution at solder/Cu interface

The morphology of the interfacial IMCs is an important factor that significantly affects the reliability of the solder joint [158]. The formation of  $\text{Cu}_6\text{Sn}_5$  on the interface in the solder joint is required to build a strong metallurgical bond and this is due to the interfacial reaction between Sn and Cu substrate during reflow. Several researchers [159-164] reported that the  $\text{Cu}_3\text{Sn}$  would originate between  $\text{Cu}_6\text{Sn}_5$  and Cu substrate during higher temperature and long term aging process. The excessive growth of IMCs can weaken the strength of the solder joint during the reflow and aging process due to the brittle nature of IMCs [165-167]. Thus, the kinetics of the interfacial reaction between the solder and the Cu substrate is an important issue in evaluating the reliability of the solder.

Very few literature have reported on the played role of SiC reinforcements in lead-free solder played during the growth of IMCs in the solder matrix. It is known that SiC cannot react with the Cu because SiC is a non-reactive reinforcement but Ni is reactive and forms a  $(\text{Ni,Cu})_6\text{Sn}_5$  phase on the Cu–Sn interface. In general, the thickness of the interfacial IMCs increases continuously during thermal aging; however, interfacial IMCs mostly consists of a brittle nature, the large-scale growth of interfacial IMCs would serious problem for the reliability of solder joints. The development and growth of the IMCs ( $\text{Cu}_6\text{Sn}_5$  and  $\text{Cu}_3\text{Sn}$ ) layers in microstructural characterization were described after the reflow and aging process as shown in **Figure 4.5**. **Figure 4.6** represents the SEM micrograph of the solidified SAC305 solder with distribution of SiC.

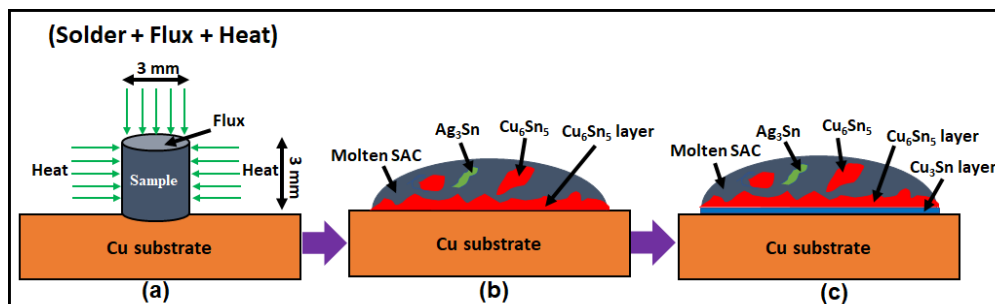


Figure 4.5 Schematic diagram of the IMCs layers growth (a) solid SAC305 sample on the Cu substrate (b) diffusion of the SAC305 molten solder on substrate and formation of the  $\text{Cu}_6\text{Sn}_5$  IMC after reflow (c) formation of the  $\text{Cu}_3\text{Sn}$  (sandwich structure) layer exists between  $\text{Cu}_6\text{Sn}_5/\text{Cu}$  interfaces after aging

**Figure 4.7** and **Figure 4.9** show the SEM images of the Sn–3.0Ag–0.5Cu composite solder of the joint interface with the addition of SiC and SiC(Ni) after 100h aging. After aging, IMCs [ $\text{Cu}_6\text{Sn}_5$ ,  $(\text{Ni,Cu})_6\text{Sn}_5$  and  $\text{Cu}_3\text{Sn}$ ] layers are developed at the Sn-Cu interface. **Figure 4.8** is confirmed the  $\text{Cu}_6\text{Sn}_5$  and  $\text{Cu}_3\text{Sn}$  layers; however, **Figure 4.10** shows the presence of  $(\text{Ni,Cu})_6\text{Sn}_5$  and  $\text{Cu}_3\text{Sn}$  layers at the Cu–Sn interface.

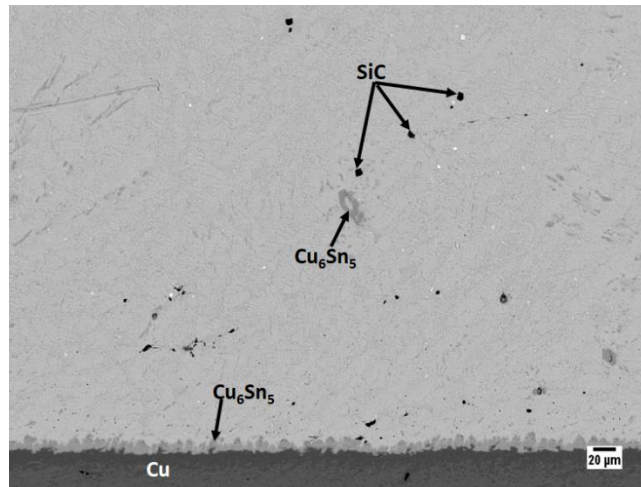


Figure 4.6 SEM micrograph of the solidified SAC305 solder with addition of SiC

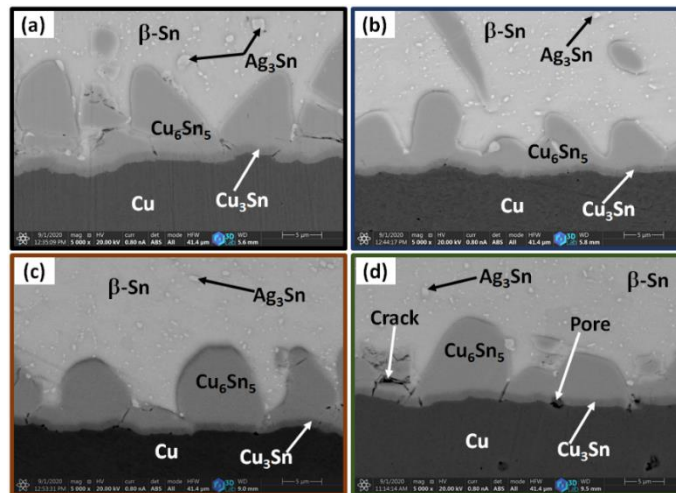


Figure 4.7 SEM micrographs of SAC305/xSiC lead-free solder composites after 100h aging at 140 °C (a) monolithic SAC305 (b) 0.5% (c) 1.0% (d) 1.5%

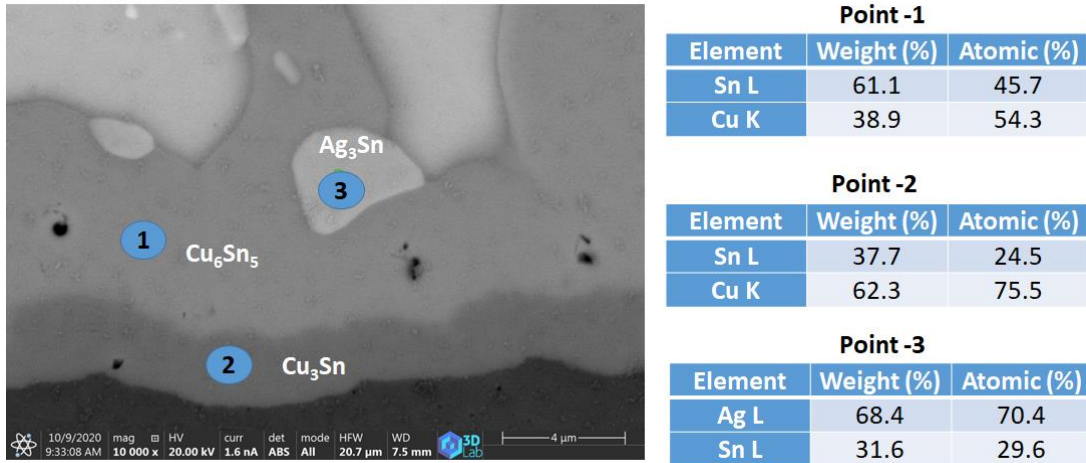


Figure 4.8 Verification of the IMCs in the SAC305 solder composite with the addition of SiC

**Figure 4.9** shows that the added Ni particles reacted with the solder after aging. In the case of SAC305 composite solder, the IMC containing Ni was formed at the interface. The Cu atom was joined with the Ni when the solder was melted after reinforcement of SiC(Ni) and the Ni particle absorbed some of the Cu and formed (Ni, Cu)<sub>6</sub>Sn<sub>5</sub> IMC to the interface of the substrate. On the other hand, (Ni, Cu)<sub>6</sub>Sn<sub>5</sub> developed in SAC305 soldering precipitated during the solidification process. With the reinforcement of SiC(Ni) particles, the (Ni, Cu)<sub>6</sub>Sn<sub>5</sub> phase became thermodynamically more stable than Cu<sub>6</sub>Sn<sub>5</sub> [168-169]. The diffusion driving force of Cu atoms in the (Ni, Cu)<sub>6</sub>Sn<sub>5</sub> phase was higher than in the Cu<sub>6</sub>Sn<sub>5</sub> phase, and the diffusion pathway of Cu atoms from the Cu substrate was obstructed by the diffusion mechanism [170-171]. Therefore, the number of Cu atoms was reduced and the growth rate of (Ni, Cu)<sub>6</sub>Sn<sub>5</sub> decreased. When the number of reinforcement increases in the solder alloy, more Ni atoms diffused onto the solder surface of the liquid SAC305 and then reacted with Sn and Cu to form the (Ni, Cu)<sub>6</sub>Sn<sub>5</sub> phase, which affected the growth of IMC. The structure of Cu<sub>6</sub>Sn<sub>5</sub> or (Ni, Cu)<sub>6</sub>Sn<sub>5</sub> can be changed from scallop-like to irregular with increased aging time and this due to the Gibbs free energy barrier of the liquid–solid interface was lower than the solid–solid interface. Therefore, the interfacial reaction between the substrate and the solder favored increasing the Gibbs free barrier during aging and to change the structure of IMCs from scallop to planar [18, 172].

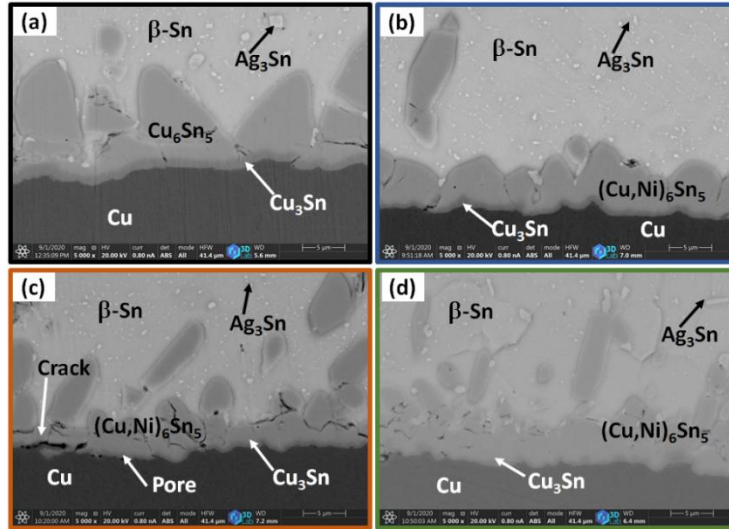


Figure 4.9 SEM micrographs of SAC305/xSiC(Ni) lead-free solder composites after 100h aging at 140°C (a) monolithic SAC305 (b) 0.5% (c) 1.0% (d) 1.5%

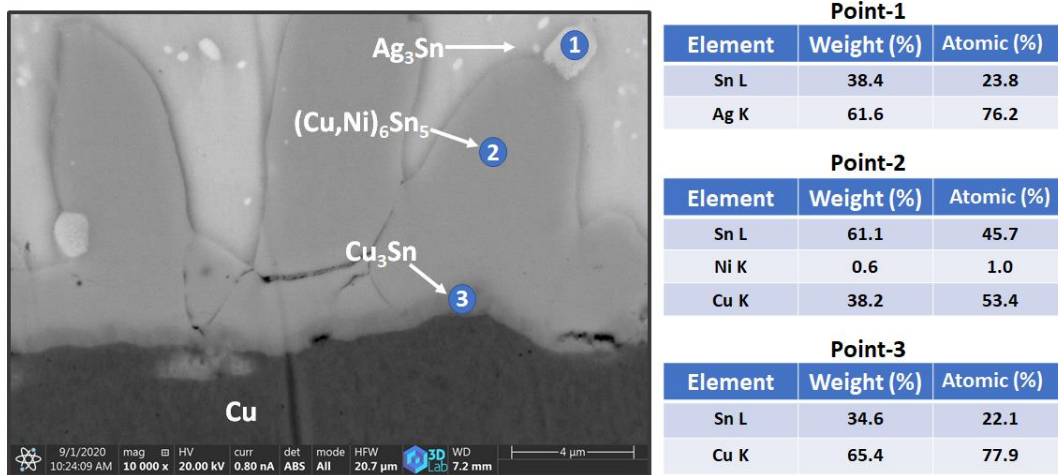


Figure 4.10 Verification of the IMCs in the SAC305 solder composite with the addition of SiC(Ni)

The average thickness of IMCs layers in the Sn–Cu interface in different conditions were determined by the SEM images. The irregular shape of  $\text{Cu}_6\text{Sn}_5$  layer and thick plate-like  $\text{Cu}_3\text{Sn}$  layer on the surface of the Cu as shown in schematic **Figure 4.11** and IMC thickness is measured by the “ImageJ” software. The average thickness ( $x_t$ ) was calculated by the total area ( $A$ ) of the individual IMC divided by the total length ( $L$ ) of the layer, as shown in **Eq. (4.1)**:

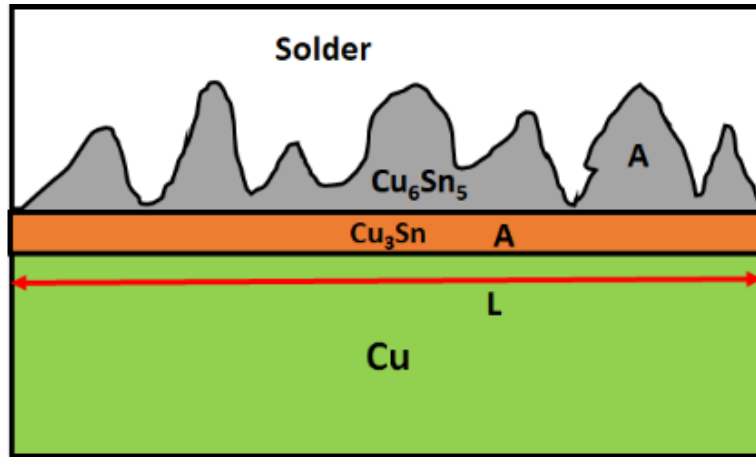


Figure 4.11 Schematic diagram of interfacial microstructure on Cu substrate

$$x_t = \frac{A}{L} \quad \text{Eq. (4.1)}$$

Where,  $x_t$  = Average thickness ( $\mu\text{m}$ ),

$A$  = Total area of the individual IMCs ( $\mu\text{m}^2$ ),

$L$  = Total length of the IMCs layer ( $\mu\text{m}$ )

ImageJ is used for the analysis of the  $\text{Cu}_6\text{Sn}_5$  and  $\text{Cu}_3\text{Sn}$  layer thickness. **Figure 4.12 (a–c)** displays the segmented area of the  $\text{Cu}_3\text{Sn}$ ,  $\text{Cu}_6\text{Sn}_5$ , and total layer ( $\text{Cu}_3\text{Sn} + \text{Cu}_6\text{Sn}_5$ ). The thickness of the IMCs layer is calculated from these areas of the IMCs divided by the length of the image.


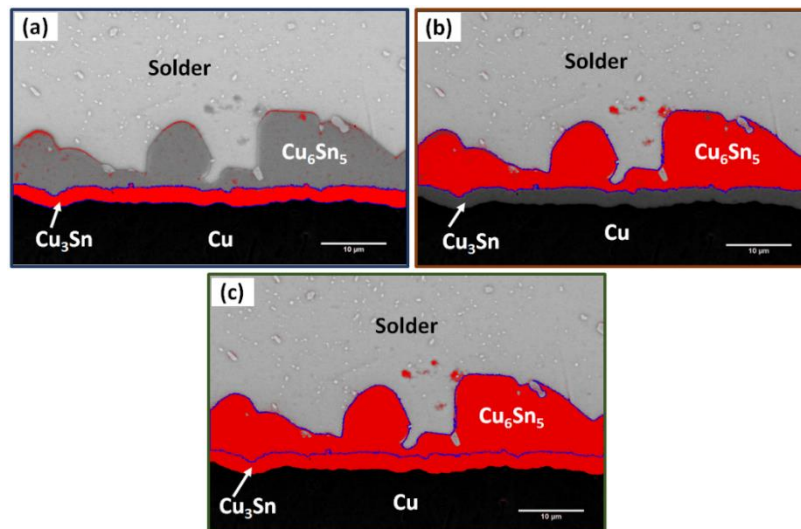


Figure 4.12 Thickness analysis of the IMCs layer by ImageJ (a) segmented area of  $\text{Cu}_3\text{Sn}$  (b) segmented area of  $\text{Cu}_6\text{Sn}_5$  (c) total area of the IMCs

The thickness results for all composite (SAC305/SiC and SAC305/SiC–Ni) solders are shown in **Table 4.4** and **Table 4.5** respectively.

*Table 4.4 Average thickness of  $Cu_6Sn_5$  and  $Cu_3Sn$  in lead-free solder composites with the addition of SiC*

Composite solder	Aging temperature (°C)	Aging time (h)	IMC thickness layer ( $\mu\text{m}$ )		
			$Cu_6Sn_5$	$Cu_3Sn$	Total
SAC305	140	100	7.57	1.21	8.78
SAC305/0.5SiC			6.08	1.01	7.09
SAC305/1.0SiC			4.24	0.73	4.97
SAC305/1.5SiC			5.27	0.96	6.23

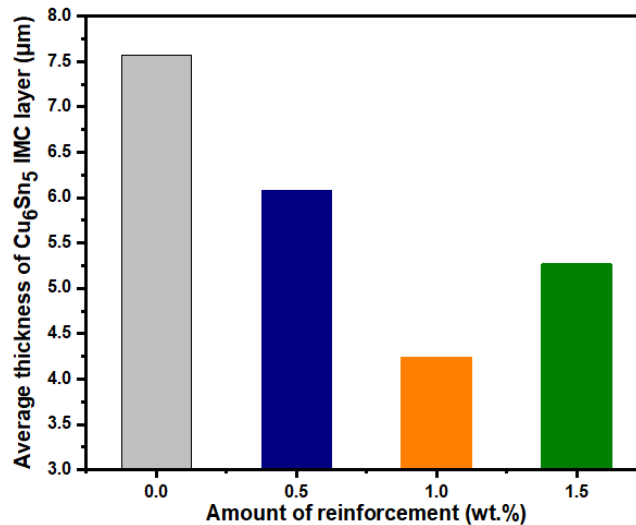

*Figure 4.13 Variation of  $Cu_6Sn_5$  thickness in the SAC305 lead-free solder with the addition of SiC*

In the monolithic solder, the almost intermittent IMC morphology became smaller in size after the addition of different amounts of SiC and Ni-coated SiC particles. However, the almost intermittent IMC structures became thin and continuous after reinforcing particles were added to the SAC305. Most of the added particles are involved in the formation of the IMCs. The chemical reaction between SAC305 and the Cu substrate also induced the growth of a thin layer of the  $Cu_3Sn$  phase. The growth of  $Cu_6Sn_5$ ,  $(Ni, Cu)_6Sn_5$  and  $Cu_3Sn$  layer thickness on the Cu substrate was suppressed by the addition of different amounts of reinforcement (SiC and Ni-coated SiC) particles in the solder matrix after 100h aging, as shown in **Figure 4.13**, **Figure 4.14**, and **Figure 4.15**. It was



noticed that the minimum thickness of the IMC layer was obtained by the addition of 1% by weight of SiC and Ni-coated SiC particles. This was due to the added reinforcement particles in the solder matrix which were inhibited the Cu atom. Most of the Cu atoms came from the Cu substrate; however, a few percent came from the solder matrix [19]. This pathway of Cu atoms was retarded due to the formation of the Sn-Cu phase between molten solder and the Cu substrate during the reflow process.

During the reflowing process, the SiC particles are absorbed in the liquid because it do not melt on the Cu surface due to the high melting point (2730 °C). The SiC particles can behave as a barrier to the diffusion of Cu atoms from the substrate. The formation of the IMCs layers is mainly due to the diffusion of atoms from the substrate into the solder matrix. Liu et al. [56] reported that the size and the thickness of the  $\text{Cu}_6\text{Sn}_5$  IMC layer are decreased due to declines the grain boundary activation energy. A similar results were also reported by Nai et al. [52, 173]. According to Tsao [174], the large amounts of  $\text{Ag}_3\text{Sn}$  particles were found on the IMC surface of  $\text{Cu}_6\text{Sn}_5$  during the solidification process and these particles are reduce surface energy and inhibit the growth of  $\text{Cu}_6\text{Sn}_5$  IMC.

Table 4.5 Average thickness of  $(\text{Ni,Cu})_6\text{Sn}_5$  and  $\text{Cu}_3\text{Sn}$  in SAC305 composites with the addition of SiC(Ni)

Composite solder	Aging temperature (°C)	Aging time (h)	IMC thickness layer ( $\mu\text{m}$ )		
			$(\text{Ni, Cu})_6\text{Sn}_5$	$\text{Cu}_3\text{Sn}$	Total
SAC305	140	100	7.57	1.21	8.78
SAC305/0.5%SiC(Ni)			5.44	0.85	6.29
SAC305/1.0%SiC(Ni)			3.78	0.53	4.31
SAC305/1.5%SiC(Ni)			4.95	0.80	5.75

The thickness of the  $\text{Cu}_6\text{Sn}_5$  and  $\text{Cu}_3\text{Sn}$  IMCs layer was decreased by 43.8% and 39.6% in the SAC/1%SiC; however,  $(\text{Ni,Cu})_6\text{Sn}_5$  and  $\text{Cu}_3\text{Sn}$  IMCs layer was reduced by 50.06% and 56.19% in the SAC/1%SiC(Ni) composite solder. The outcome shows that the development of the  $\text{Cu}_6\text{Sn}_5$ ,  $(\text{Ni,Cu})_6\text{Sn}_5$  and  $\text{Cu}_3\text{Sn}$  IMC layer on the Sn-Cu interface was suppressed by a small addition of SiC and SiC(Ni) particles. These reinforcement particles reduce the surface energy and inhibit the growth of IMC layers. Tang et al. [43] reported that  $\text{TiO}_2$  particles are behaved as a heterogeneous nucleating agent and it can affect the formation of the IMC layer. Min Qu et al. [40] studied the

SAC305-ZnO solder joints and reported that ZnO particles are aggregated at the interface due to higher specific surface energy and it can prevent the diffusion of the Cu atoms from the substrate. Therefore, the diffusion of Cu atoms from the substrate is obstructed and the growth of the IMCs layer are reduced. Other researchers reported the same trend after using different types of reinforcements in the lead-free solders [22, 26, 47, 56, 59, 110, 173-178].

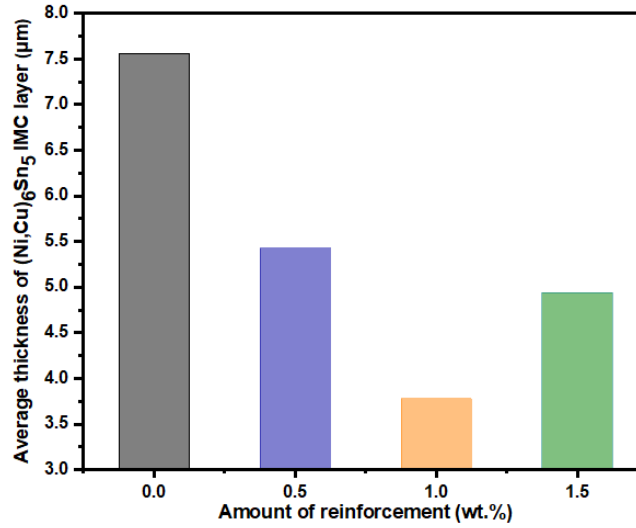


Figure 4.14 Variation of  $(Ni,Cu)_6Sn_5$  thickness in the SAC305 lead-free solder with the addition of SiC(Ni)

However, with the reinforcement of 1.5wt%SiC and SiC(Ni) (Figure 4.3d and Figure 4.4d), coarse scallop type  $Cu_6Sn_5$  particles were developed on the interfacial layer and the number of  $Ag_3Sn$  IMC was not increased in the solder composite solder. Furthermore, the reduction of the IMCs layer thickness was lesser than the other composition (Figure 4.13, Figure 4.14, and Figure 4.15) and this is due to the agglomeration and segregation of the reinforcement particles in the bulk solder. The segregation and agglomeration are happened due to the van der Waals forces and this force is entangled of the reinforcement particles as used of more amount (1.5%), therefore IMCs layer thickness and number of  $Ag_3Sn$  grains are decreased [175]. Similar research is reported for the morphology of the bulk solder with the addition of SiC by Liu [33].

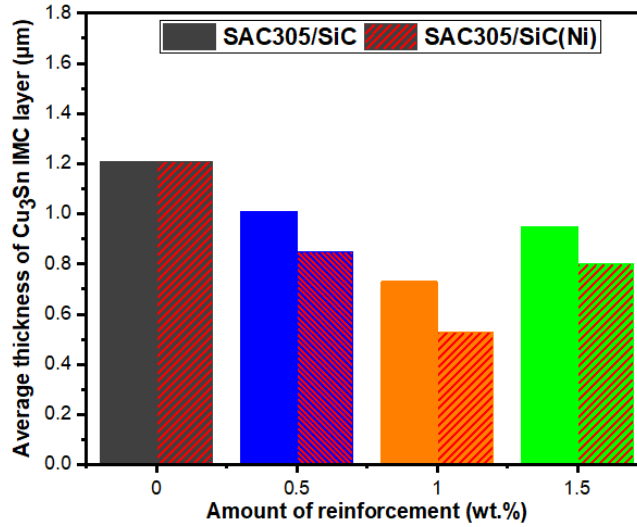


Figure 4.15 Variation of  $\text{Cu}_3\text{Sn}$  thickness in the SAC305 lead-free solder with the addition of SiC and SiC(Ni)

#### 4.3.3 Microhardness

To estimate the effect of thermal aging on the microhardness of SiC and Ni-coated SiC reinforced composite solder with various composition was examined. Specifically, the microhardness test was performed with a Vickers hardness tester at room temperature; the details of the process are shown in a schematic diagram (Figure 4.16).

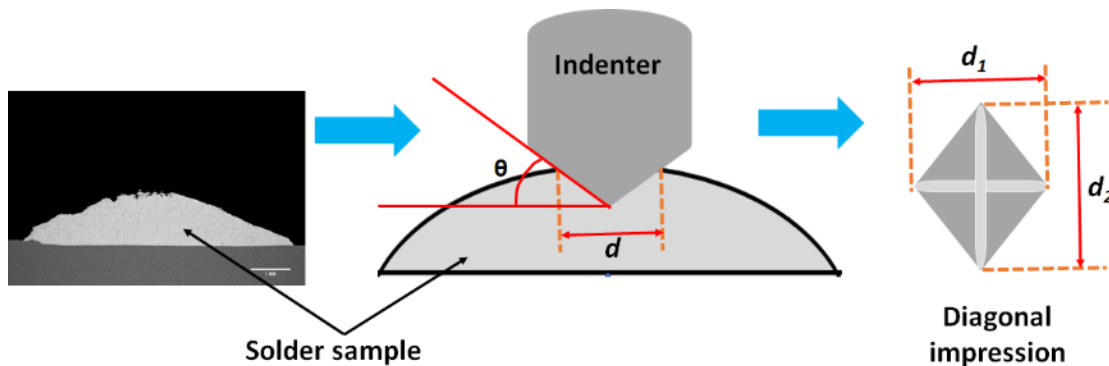


Figure 4.16 Schematic diagram of a microhardness test

During the hardness test, the applied load was 10g, while the dwell time was 10 seconds. For each solder sample, three points were tested by removing the minimum and maximum values. Using the size of the diagonals of the impression, the microhardness data of the different samples were calculated using Eq. (4.2) and Eq. (4.3):

$$HV = 1.854 \times \frac{F}{d^2} \quad Eq. (4.2)$$

$$d = \left( \frac{d_1 + d_2}{2} \right) \quad Eq. (4.3)$$

Where, HV is the Vickers hardness, F is the applied load (g) and  $d$  is the diameter of indentation ( $\mu\text{m}$ ) and it can be calculated by the mean value of  $d_1$  and  $d_2$ .

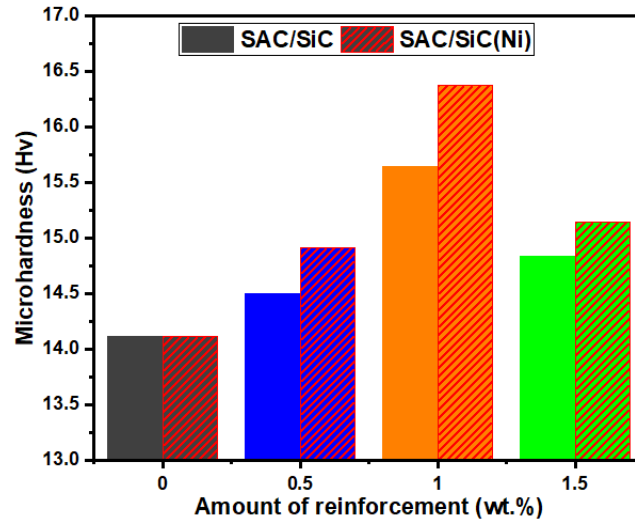


Figure 4.17 Microhardness of monolithic SAC305, SAC305/SiC, and SAC305/SiC(Ni) composite solders

The microhardness of monolithic SAC305, SAC305 and SAC305/Ni-coated SiC composite solder are shown in **Figure 4.17**. It is examined that the microhardness values of composite solders are increased as compared to that of the monolithic SAC305 solder. The higher values are 15.25 and 15.98Hv for SAC305/1.0%SiC and SAC305/1.0%SiC(%) composite solder. Compared to the monolithic SAC305 solder, these results show the ~10.8% and ~16.0% increment in the microhardness of composite solder with the addition of 1.0wt.%SiC and SiC(Ni). The reason for the improvement of microhardness is the finely distributed intermetallics ( $\text{Ag}_3\text{Sn}$  and  $\text{Cu}_6\text{Sn}_5$ ) in the composite solder [104]. The hard  $\text{Ag}_3\text{Sn}$  IMCs can resist indentation more strongly than the monolithic SAC305 solder. This improvement can be related to (1) The existence of the harder SiC and Ni-coated SiC and (2) Reinforcements act as an obstruction to the localized matrix deformation and dislocation movement due to the presence of reinforcement [45].

#### 4.4 Wetting behavior of composite solder

Wetting concerning composite solders plays an important role in understanding the spreading behavior of the solder as a function of temperature, time. Besides time and temperature, in a composite solder wetting is affected by flux composition, and surface roughness of solid [179]. Here, as stated earlier, SiC and SiC(Ni) was chosen as the reinforcement in the SAC solder matrix to obtain the composite. The wettability was evaluated by measuring the spreading area on copper substrates and wetting angles. Solder specimen (3 mm × 3 mm) is placed on the center of the Cu plate with flux and melted in the furnace at a 260°C for 30min. For good wetting of solders, a perfect metallurgical bond must be established at the interface between the solder (liquid) and the Cu (solid) substrate. Due to interfacial reaction, the IMCs grains or the intermetallic layers are composed at the surface. **Figure 4.18** shows the diagram of the (a) solder sample (b) solidified solder and (c) SEM micrograph of the solidified cross-section, however; **Figure 4.19** shows the schematic diagram of the spherical cap geometry for the calculation of the spread ratio, spread factor, and contact angle.

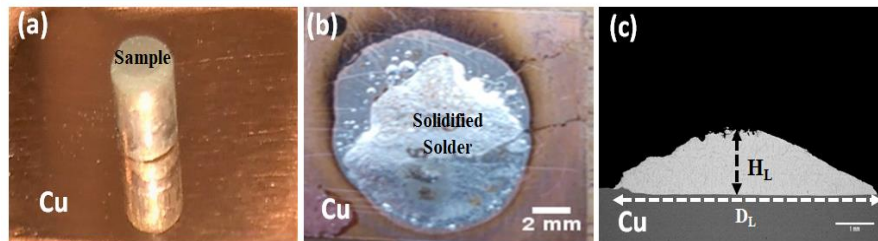


Figure 4.18 The diagram of the (a) solder sample (b) solidified solder (c) SEM micrograph of the cross-section

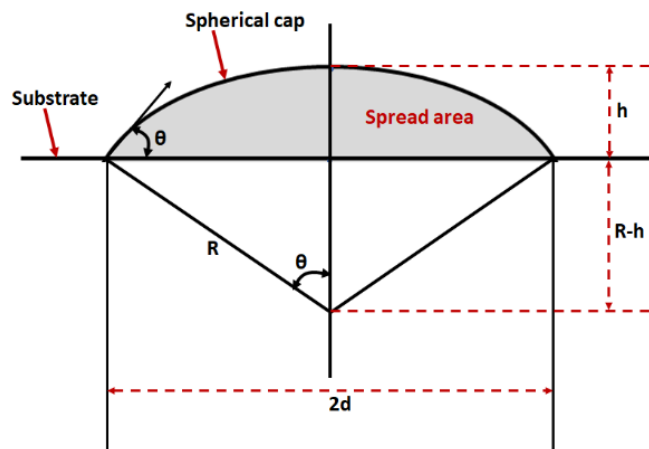


Figure 4.19 The schematic diagram of the spherical cap geometry for the calculation of the spread ratio, spread factor, and contact angle [180].

#### 4.4.1 Contact angle (wettability) of composite solder

The performance of the coating during operation depends not only on the specific characteristics of the coating (and substrate) materials, but also on the adhesion of the coating-substrate adhesion. Wettability promotes adhesion through physical, chemical and / or mechanical bonds that act at the coating-substrate interface. As the interface represents a region of compositional and structural discontinuities, it is inherently unstable and evolves during service, serving as a site for morphological, chemical, and structural transformations. Adhesion develops from physical (e.g., weak van der Waals) bonds, chemical interactions, and friction from irregular surface [179]. The contact angle of the solder on the substrate changed as a function of the amount of reinforcements. The contact angles were calculated by using the following equation **Eq. (4.4)** [180],

$$\sin \theta = \frac{2}{(d/h) + (h/d)} \quad \text{Eq. (4.4)}$$

The variation of contact angles of composite solders was shown in **Figure 4.20**. The largest contact angle was observed of monolithic SAC305 solder. Initially, the contact angle is decreased from 30.87° to 19.80° for 1%SiC and 16.70 for 1%SiC(Ni), however, an increasing trend was seen afterward. These results verify that the improved wetting performance of the solder matrix at a limited composition can be achieved by marginally increasing the quantity of SiC particles. Non-uniform segregation and increased viscosity of melted solder on Cu have to lead to de-wetting [45, 181].

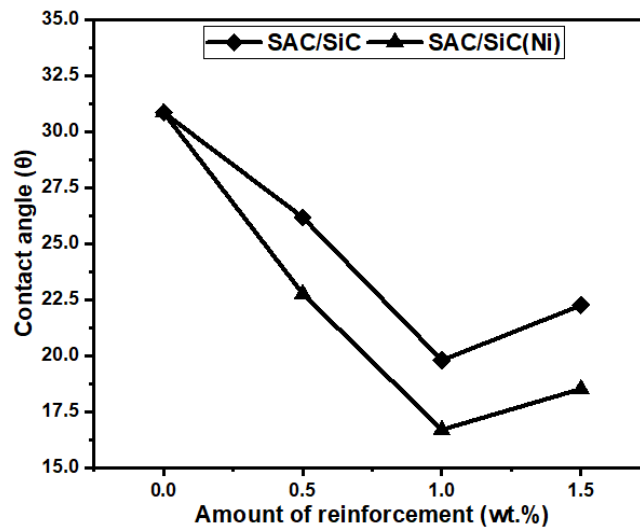


Figure 4.20 Contact angle variation of SAC305 solder with the addition of SiC and SiC(Ni) on Cu substrate

#### 4.4.2 Spread ratio and spread factor

Spread ratio ( $S_r$ ) is calculated by measuring the spherical area achieved by the melted solder specimen on the substrate. It is done by measuring the diameter ( $d$ ) and height ( $h$ ) of the cooled solder area on the substrate. Spread ratio is taken as the ratio of total plane area wetted by the molten solder on a solid substrate to the plane area of the original solder sample, which is expressed by **Eq. (4.5)** and **Eq. (4.6)** [180].

$$S_r = \frac{\text{Total plane area wetted by the molten solder on the solid substrate}}{\text{Plane area of the original spherical metal sample}} \quad \text{Eq. (4.5)}$$

$$S_r = \frac{4d^2/h^2}{[1 + 3d^2/h^2]^{2/3}} \quad \text{Eq. (4.6)}$$

Where,  $d$  is the diameter of the solder sample (mm) and  $h$  is the height (mm). Spread factor ( $S_f$ ) is calculated as the consequence of spread ratio and is given in **Eq. (4.7)** and **Eq. (4.8)**:

$$S_f = \frac{\text{Diametre of the original solder sample (d)} - \text{Height of the spreaded molten metal (h)}}{\text{Diametre of the original solder sample (d)}} \quad \text{Eq. (4.7)}$$

$$S_f = 1 - \frac{1}{[1 + 3d^2/h^2]^{1/3}} \quad \text{Eq. (4.8)}$$

**Figure 4.21** and **Figure 4.22** shows the variation of spread ratio ( $S_r$ ) and spread factor ( $S_f$ ) with the corresponding amount of reinforcements and it was observed that the spread ratio ( $S_r$ ) and spread factor ( $S_f$ ) of SAC305 solder increased at 1.0% with an addition of SiC and SiC(Ni). The lowest value obtained for the spread ratio and spread factor is 4.46 and 7.08 for monolithic SAC305 solder, whereas the maximum values were observed to be 6.12 and 7.84 for SAC305/1.0%SiC and 6.88 and 8.08 for SAC305/1.0%SiC(Ni) respectively.

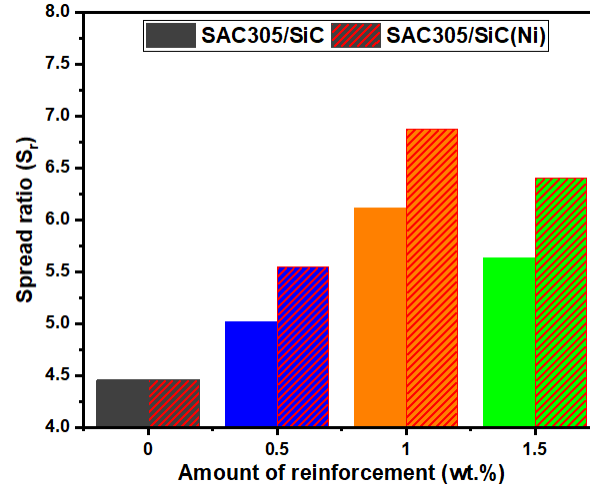


Figure 4.21 Spread ratio trend of SAC305 solder composites with the addition of SiC and SiC(Ni)

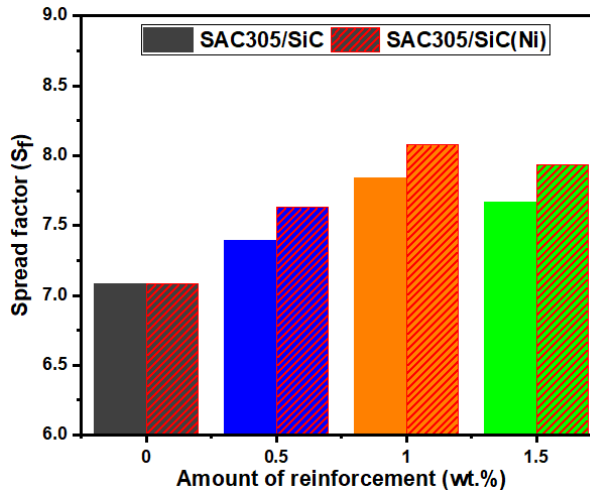


Figure 4.22 Spread factor trend of SAC305 solder composites with the addition of SiC and SiC(Ni)

It is noticed that SAC305/1.0%SiC and SAC305/1%SiC(Ni) has the maximum spreading ratio and spreading factor. The spreading ratio and spreading factor increases until 1.0% composition and then decreases. The higher amount of reinforcements interrupted the flow of the solder because it is increased the melt viscosity and decrease the spreading of the solders on the substrate [9, 45, 104, 181].

#### 4.5 Interfacial reactions between Sn–Ag–Cu solder and Cu substrate

SAC305/1%SiC composite solder is selected for examination of the thickness of the  $\text{Cu}_6\text{Sn}_5$  and  $\text{Cu}_3\text{Sn}$  at the different aged conditions and different times because this composition showed the



best results as already discussed in chapter 3. The SAC305/1.0%SiC solder was reflowed for different temperatures (240°C, 260°C, 280°C, 300°C) at time (30min, 60min, 90min, 120min) and same composite solder was aged at different temperature (140°C, 150°C, 160°C, 170°C) at time (25h, 50h, 75h, 100h). **Figure 4.23(a–b)** shows the morphology of the reflow and aged solder sample, however,  $\text{Ag}_3\text{Sn}$  grains are distributed on the  $\text{Cu}_6\text{Sn}_5$  layer and in the bulk solder area and it is frequently widespread in the  $\text{Cu}_6\text{Sn}_5$  surface layer with increasing aging time. **Figure 4.24** shows the morphology of the SAC305/1.0%SiC solder at the Cu substrate after various reflow temperature. The scallop-type  $\text{Cu}_6\text{Sn}_5$  and plate-like  $\text{Cu}_3\text{Sn}$  IMCs were observed at the Cu–Sn interface. Generally,  $\text{Cu}_6\text{Sn}_5$  and  $\text{Cu}_3\text{Sn}$  layers are formed in the Sn–based solder alloys at the Cu–Sn interface, and the thickness of these two layers are increased with increasing aging time.

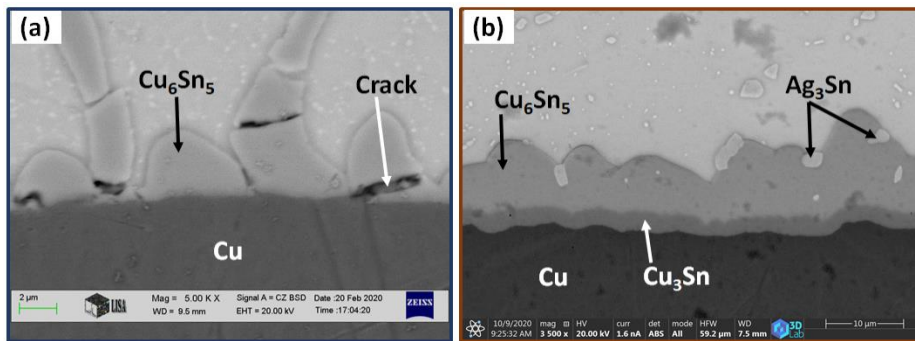


Figure 4.23 SEM Image of composite solder after (a) reflow process and (b) aging

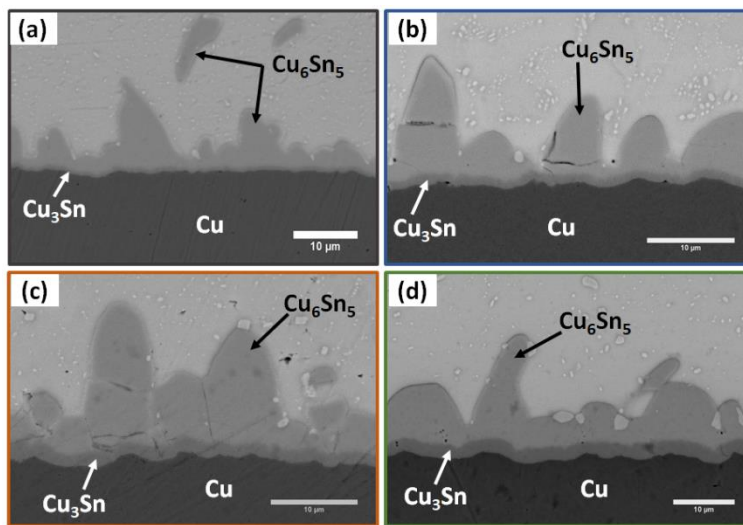


Figure 4.24 Morphology of SAC305/1%SiC composite solder at different reflow temperature (a) 240 °C (b) 260 °C (c) 280 °C (d) 300 °C

**Figure 4.25** shows the IMCs layer thickness of SAC305/1%SiC(Ni) composite solder after multiple reflow cycles. The diffusion rate is very quick at reflow temperature because the reflow process involves diffusion between modes of transport due to the melting of the solder particles.

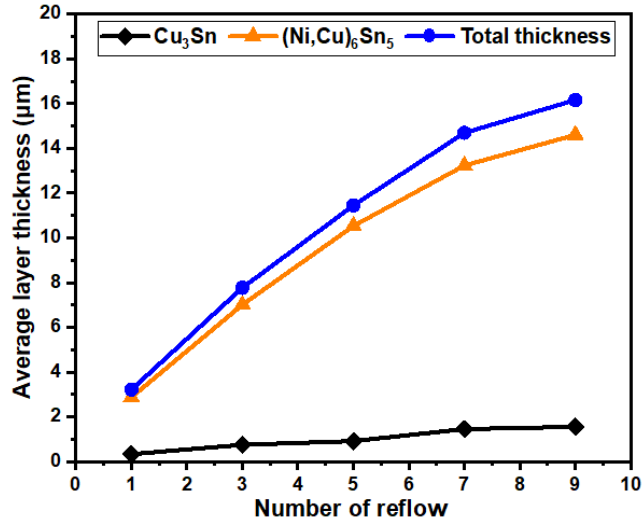


Figure 4.25 IMCs layer thickness of SAC305/1%SiC(Ni) composite solder as a function of reflow number

**Table 4.6** shows the effect of multiple reflows on the growth of the IMCs layer and its thickness increased very fast. The average thickness of  $\text{Cu}_6\text{Sn}_5$  and  $\text{Cu}_3\text{Sn}$  IMCs layer grows from  $\sim 6.46$  and  $\sim 0.64$   $\mu\text{m}$  after the first reflow cycle to a maximum of  $\sim 14.6$  and  $1.56$   $\mu\text{m}$  thickness after the ninth reflows.

Table 4.6 Average layer thickness of the SAC305/1.0%SiC(Ni) composite solder with various reflow cycle

Composite solder	Reflow temperature (°C)/Time (min)	Number of reflows	IMC thickness layer ( $\mu\text{m}$ )		
			$(\text{Ni,Cu})_6\text{Sn}_5$	$\text{Cu}_3\text{Sn}$	Total
SAC305/1.0%SiC(Ni)	260/30	1	2.77	0.33	3.10
		3	7.01	0.76	7.77
		5	10.53	0.92	11.45
		7	13.23	1.46	14.69
		9	14.6	1.56	16.16

The mean thickness of the IMCs layer in SAC305/1%SiC composite solder on Cu substrate at different reflow time and temperature are shown in **Table 4.7**. The thickness of the IMCs layer developed at the Cu–Sn interface was examined quantitatively as a function of aging time. To kinetics of the IMCs growth layer at the Sn/Cu interface, IMC growth was assumed to be controlled by volume diffusion, i.e., the growth rate is proportional to the square root of time. The IMC thickness as a function of time can be expressed by the Arrhenius **Eq. (4.9)**:

$$x_t = x_0 + Dt^n \quad \text{Eq. (4.9)}$$

Where,  $x_t$  = IMC layer thickness at time  $t$  ( $\mu\text{m}$ ),

$t$  = aging time (s)

$x_0$  = Initial IMC layer thickness after aging ( $\mu\text{m}$ ),

$D$  = Diffusion coefficient as a function of temperature ( $\mu\text{m}^2/\text{s}$ ), and  $n$  = Time exponent.

When plotting the thickness of the intermetallic layer ( $x_t$ ) against the square root of the aging time ( $t^{1/2}$ ) from **Eq. (4.10)**, the slope of the graph is equal to the square root of the diffusion coefficient ( $D^{1/2}$ ). The diffusion coefficient was determined from a linear regression analysis of  $x$  vs  $t^{1/2}$ , where the slope is  $D^{1/2}$ .

$$\ln(x_t - x_0) = \ln D - n \cdot \ln(t) \quad \text{Eq. (4.10)}$$

Where, the exponent  $n$  is equal to the slope of the  $\ln(x_t - x_0)$  vs  $\ln(t)$  curve. The value of  $n$  will be 1/2 when the IMC formation is controlled by the volume diffusion mechanism [182]. In this study, the value  $n$  under isothermal aging was 0.50. Kim et al. [183] reported for the value of  $n$  are 0.37, 0.34, and 0.32 for different temperature, however, Shen et al. [184] reported for isothermal aging, thermal cycling, and thermal shock has considered 0.51, 0.6, and 0.62, respectively. When, plotting the thickness of the IMC layer ( $x_t$ ) versus the aging time ( $t^{1/2}$ ), the slope of the graph is equal to the square root of the diffusion coefficient ( $D^{1/2}$ ). The thickness of the IMCs layer in SAC305/1%SiC composite solder on Cu substrate at different reflow time and temperature are shown in **Table 4.7**.

Table 4.7 Thickness of IMCs layer of the SAC305/1%SiC composite solder at different reflow time and temperature

Reflow temperature (°C)	Reflow time (min)	IMCs thickness ( $\mu\text{m}$ )		
		$\text{Cu}_6\text{Sn}_5$	$\text{Cu}_3\text{Sn}$	$\text{Cu}_6\text{Sn}_5 + \text{Cu}_3\text{Sn}$
240	30	3.07	0.43	3.50
	60	5.06	0.59	5.66
	90	6.49	0.83	7.34
	120	7.71	0.96	8.66
260	30	3.81	0.55	4.32
	60	6.53	1.08	7.62
	90	8.22	1.30	9.52
	120	9.76	1.51	11.34
280	30	5.82	1.01	6.83
	60	8.42	1.42	9.84
	90	10.08	1.76	11.84
	120	12.41	2.15	14.56
300	30	6.75	1.35	8.10
	60	9.95	1.84	11.79
	90	12.38	2.39	14.77
	120	14.63	2.60	17.23

Figure 4.26, Figure 4.27, and Figure 4.28 show the IMCs layer thickness ( $\text{Cu}_6\text{Sn}_5$ ,  $\text{Cu}_3\text{Sn}$ , and total thickness) are developed on the Cu–Sn interface at different reflow time and temperatures. The thickness of the IMCs layers is increased with an increase of reflow time and temperature.

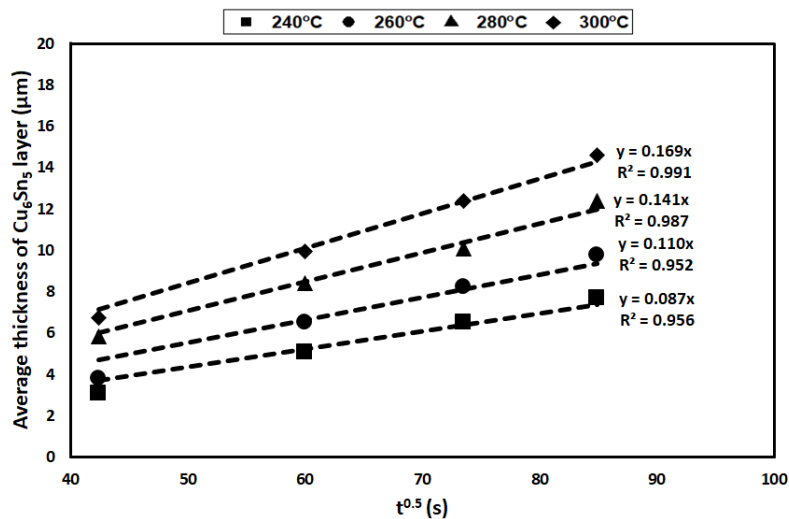


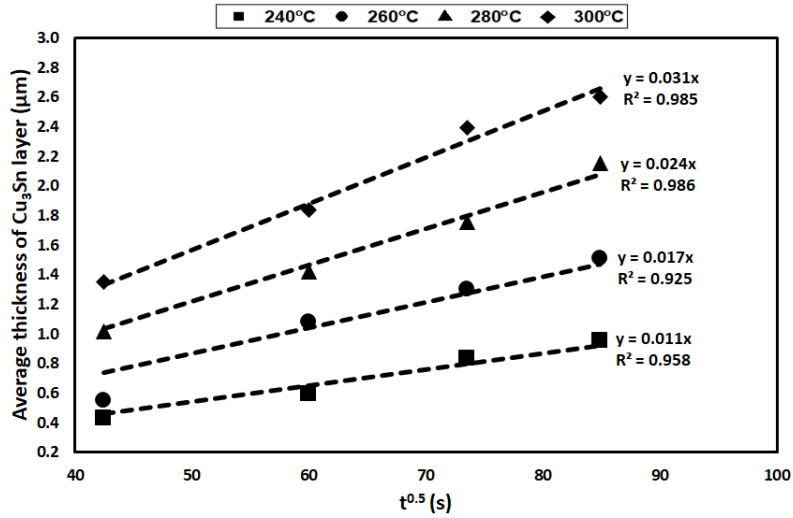
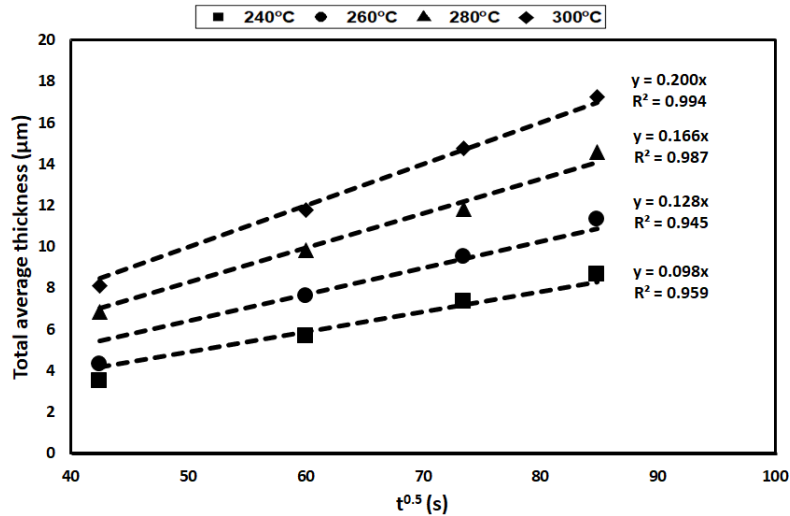
Figure 4.26 Average thickness of  $Cu_6Sn_5$  layer of SAC305/1%SiC composite solder at different reflow temperatureFigure 4.27 Average thickness of  $Cu_3Sn$  layer of SAC305/1%SiC composite solder at different reflow temperature

Figure 4.28 Total Average thickness layer in SAC305/1%SiC composite solder at different reflow temperature

The morphology of the SAC305/1%SiC composite solder after aging at different temperatures (140 °C, 150 °C, 160 °C, and 170 °C) is shown in **Figure 4.29** and the thickness of the IMCs layer at different aging time and temperature are shown in **Table 4.8**. The IMCs layer thickness is increased with an increase in time and temperature. **Figure 4.30**, **Figure 4.31**, and **Figure 4.32** show the IMCs layer thickness ( $Cu_6Sn_5$ ,  $Cu_3Sn$ , and total thickness) developed at the Cu–Sn interface as a function of  $t^{1/2}$  (aging time). The  $Cu_6Sn_5$ ,  $Cu_3Sn$ , and total thickness layers enhanced

linearly with the  $t^{1/2}$ . Moreover, the square root of the aging time shown that the enhanced IMCs layer thickness is a diffusion-driven process [185].

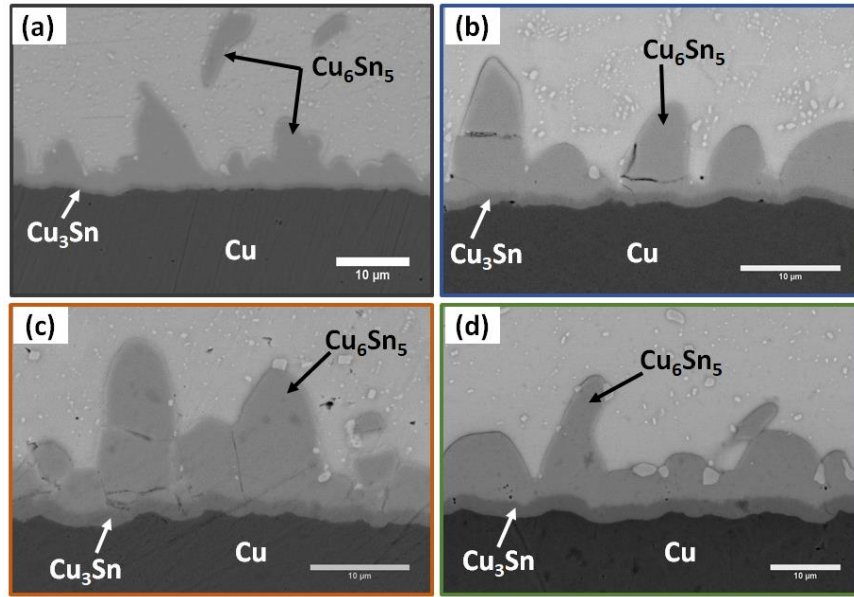


Figure 4.29 Morphology of SAC305/1%SiC composite solder after 100h aging at different temperature (a) 140 °C (b) 150 °C (c) 160 °C (d) 170 °C

Table 4.8 Thickness of IMCs layer of the SAC305/1%SiC composite at different aging time and temperature

Aging temperature (°C)	Aging time (h)	IMCs thickness (μm)		
		Cu <sub>6</sub> Sn <sub>5</sub>	Cu <sub>3</sub> Sn	Cu <sub>6</sub> Sn <sub>5</sub> +Cu <sub>3</sub> Sn
140	25	3.99	0.47	4.46
	50	4.59	0.58	5.17
	75	5.31	0.73	6.04
	100	5.84	0.84	6.69
150	25	4.43	0.72	5.14
	50	4.91	1.06	5.97
	75	5.49	1.10	6.59
	100	5.80	1.21	7.01
160	25	6.06	0.93	6.99
	50	6.14	1.45	7.59
	75	6.34	1.48	7.82
	100	7.58	1.77	9.35
170	25	6.79	1.08	7.87

	50	6.90	1.66	8.56
	75	7.62	1.69	9.31
	100	7.98	2.39	10.37

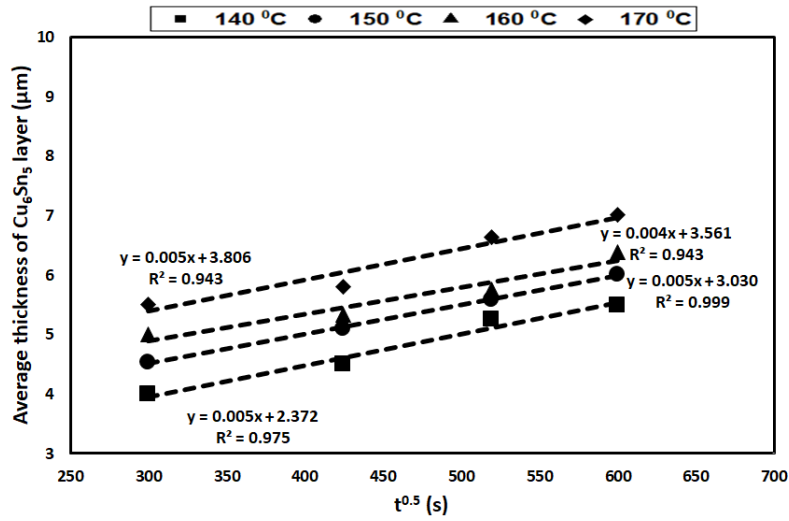


Figure 4.30 Average thickness of  $Cu_6Sn_5$  layer of SAC305/1%SiC composite solder at the different aging temperature

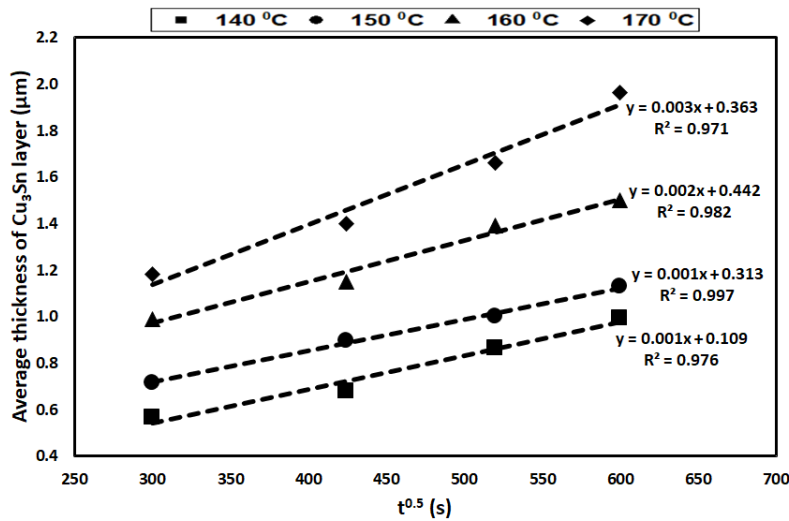


Figure 4.31 Average thickness of  $Cu_3Sn$  IMC layer of SAC305/1%SiC composite at the different aging temperature

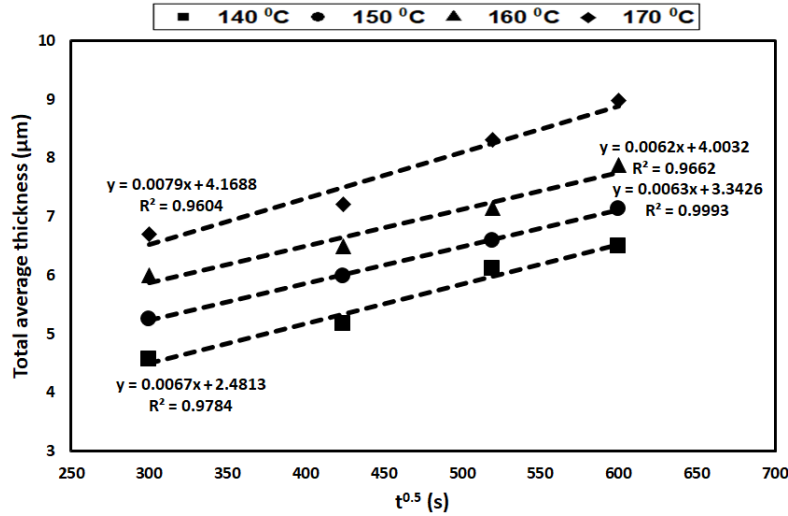


Figure 4.32 Total Average thickness layer in SAC305/1%SiC composite solder at the different aging temperature

The diffusion coefficient of the IMCs layer at the Cu–Sn interface is listed in **Table 4.9**. The diffusion coefficient of the IMC layers are varied with aging temperature and it is increased with increasing aging temperature. The diffusion coefficient of  $\text{Cu}_3\text{Sn}$  IMC was higher than the  $\text{Cu}_6\text{Sn}_5$  IMC at aging temperatures of 140 and 170°C, indicating that  $\text{Cu}_3\text{Sn}$  IMC increased rapidly at high temperatures.  $\text{Cu}_3\text{Sn}$  IMC enhanced slowly at low aging temperatures of 140°C, as shown in **Table 4.9**. The slopes of the curve can be considered as the diffusion coefficient of the IMC.

Table 4.9 Diffusion coefficient of intermetallic phases of SAC305/1%SiC composite solder at the different aging temperature

Temperature (°C)	Intermetallic phase	Slope, $D^{1/2}$ (m/s <sup>1/2</sup> )	D (m <sup>2</sup> /s)
140	$\text{Cu}_6\text{Sn}_5$	3.00E-09	9.00E-18
	$\text{Cu}_3\text{Sn}$	1.00E-09	1.00E-18
	$\text{Cu}_6\text{Sn}_5 + \text{Cu}_3\text{Sn}$	4.00E-09	1.60E-17
150	$\text{Cu}_6\text{Sn}_5$	4.00E-09	1.60E-17
	$\text{Cu}_3\text{Sn}$	2.00E-09	4.00E-18
	$\text{Cu}_6\text{Sn}_5 + \text{Cu}_3\text{Sn}$	6.00E-09	3.60E-17
160	$\text{Cu}_6\text{Sn}_5$	8.00E-09	6.40E-17
	$\text{Cu}_3\text{Sn}$	3.00E-09	9.00E-18
	$\text{Cu}_6\text{Sn}_5 + \text{Cu}_3\text{Sn}$	1.00E-08	1.00E-16
170	$\text{Cu}_6\text{Sn}_5$	9.00E-09	8.10E-17



	Cu <sub>3</sub> Sn	5.00E-09	2.50E-17
	Cu <sub>6</sub> Sn <sub>5</sub> + Cu <sub>3</sub> Sn	1.00E-08	1.00E-16

To the development of the IMCs layer thickness, the growth process of the IMC needs to be understood. In the diffusion between lead-free solder and Cu, the development of the IMCs occurs in two ways. First is the interdiffusion and the second is an interfacial reaction. From the Sn–Cu phase diagrams, Sn can react with Cu to form the IMCs layer, while there is no interaction between SiC and Cu because SiC is non-reactive reinforcement and it is gathered in the solder matrix. It is clear from the Sn–Cu phase diagram that Cu has a concentration bandgap in each phase of the IMCs and the Cu concentration gradient must be in the IMCs layer during the solder–Cu interface. Chen et al. [186] and Chung et al. [187] reported that Cu is dominant in the Sn–Cu inter-diffusion process and Cu diffuses towards the Sn with a higher rate because Cu atoms have a lower atomic radius (0.128 nm) than Sn atoms (0.141 nm). In the diffusion process, Cu gives sufficient Cu atoms for the origination of the IMCs. The Cu<sub>3</sub>Sn is developed by consuming Cu<sub>6</sub>Sn<sub>5</sub>, so kinetics IMCs are very important to solder reliability. The growth kinetics of IMC Cu<sub>6</sub>Sn<sub>5</sub> is almost identical to the kinetics of all IMCs [188]. The chemical reaction allows the atoms to enter the IMC; however, the diffusion process gives the atoms for the reaction. **Figure 4.33** shows the development process for IMCs in the solder–Cu interface.


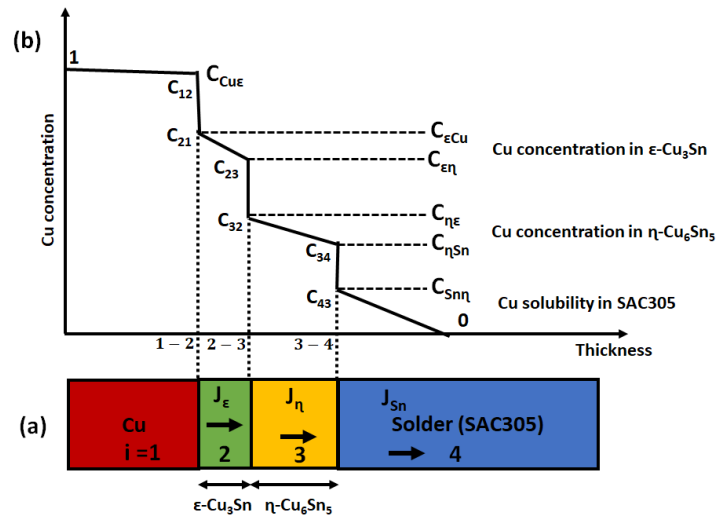


Figure 4.33 Schematic diagram of the development of Cu<sub>3</sub>Sn and Cu<sub>6</sub>Sn<sub>5</sub> layer between Cu and Sn during aging (1-2, 2-3 and 3-4)

The interfacial reaction starts at the Cu/Cu<sub>3</sub>Sn interface and local chemical equilibrium is recognized at  $C_{\epsilon Cu}$  (phase 1–2), as shown in **Figure 4.33**. Cu atoms come from the substrate and

enter into the  $\varepsilon$  phase by chemical reaction expressed by **Eq. (4.11)**. Some amount of them remain at the Cu/Cu<sub>3</sub>Sn interface and the others form the Cu diffusion flux ( $J_\varepsilon$ ), which is controlled by Cu concentration gradient in the  $\varepsilon$ -phase.



Some amount of  $J_\varepsilon$  reacts with Cu<sub>6</sub>Sn<sub>5</sub> phase to develop the Cu<sub>3</sub>Sn phase at the Cu<sub>3</sub>Sn/Cu<sub>6</sub>Sn<sub>5</sub> interface, which is demonstrated by **Eq. (4.12)** and the remaining amount of  $J_\varepsilon$  moves into the  $\eta$  phase to develop diffusion flux ( $J_\eta$ ) (phase 2–3).



Some amount of  $J_\eta$  moves at the Cu<sub>6</sub>Sn<sub>5</sub>/solder interface to develop the Cu<sub>6</sub>Sn<sub>5</sub> and the remaining amount dissolves in the solder, which is shown by **Eq. (4.13)**.



Shang et al. reported that the Cu<sub>3</sub>Sn phase develops through nucleation and growth at both sides of the interfaces (Cu<sub>6</sub>Sn<sub>5</sub>/Cu<sub>3</sub>Sn and Cu/Cu<sub>3</sub>Sn). The Cu can react with Cu<sub>6</sub>Sn<sub>5</sub> to form the Cu<sub>3</sub>Sn phase at the Cu<sub>3</sub>Sn/Cu<sub>6</sub>Sn<sub>5</sub> interface; however, Sn can react with Cu<sub>3</sub>Sn to form the Cu<sub>6</sub>Sn<sub>5</sub> phase. This is the reversible process and it is expressed by the following **Eq. (4.14) [189]**:



At the same time, Sn can diffuse across the volume or particle boundary to the Cu/Cu<sub>3</sub>Sn interface and react with Cu to form Cu<sub>3</sub>Sn. Laurila et al. [190] reported that Sn is the main diffusing species in the Cu<sub>6</sub>Sn<sub>5</sub> layer between 60 and 200°C. Both Cu and Sn diffuse into the Cu<sub>3</sub>Sn layer, but Cu diffusion is about three times faster than Sn. Therefore, the reaction of the Cu<sub>6</sub>Sn<sub>5</sub>/Cu<sub>3</sub>Sn interface should influence the growth of the Cu<sub>3</sub>Sn layer [190].

#### 4.5.1 Calculation of activation energy

The diffusion coefficient at different temperatures was often expressed by Arrhenius **Eq. (4.15)**:

$$D = D_0 e^{\left(\frac{-Q}{RT}\right)} \quad \text{Eq. (4.15)}$$

Where,  $D_0$  = Temperature-independent diffusion coefficient (m<sup>2</sup>/s),

$Q$  = Activation energy (kJ/mol),

$R$  = Universal gas constant (8.3145 J/K mol),

$T$  = Absolute temperature (K)

The activation energy of the intermetallic phase can be determined by (Eq. 4.15) and the diffusion coefficient can be indicated as Eq. (4.16):

$$\ln(D) = \ln(D_0) - \frac{Q}{R} \left( \frac{1}{T} \right) \quad \text{Eq. (4.16)}$$

Eq. 16 can be expressed as the linear equation  $y = mx + c$ , where,  $y = \ln(D)$ ,  $m = (-Q/R)$  and  $c = \ln(D_0)$ ; however,  $\ln(D)$  is dependent and  $(1/T)$  is independent variable. If the diffusion coefficient ( $D$ ) is plotted against the aging temperature ( $1/T$ ), the activation energy ( $Q$ ) can be computed from the slope of the graph and the diffusion coefficient ( $D_0$ ) can be determined from the intercept of the graph. Table 4.10 and Table 4.11 shows the diffusion coefficient and the activation energy of the intermetallic phase  $\text{Cu}_3\text{Sn}$ ,  $\text{Cu}_6\text{Sn}_5$ , and  $(\text{Cu}_6\text{Sn}_5 + \text{Cu}_3\text{Sn})$  after reflow and aging process.

Table 4.10 Diffusion coefficient and activation energies of intermetallic phases after reflow

Intermetallic phases	Activation energy, $Q$ (kJ/mol)	Diffusion coefficient, $D_0$ ( $\text{m}^2/\text{s}$ )
$\text{Cu}_6\text{Sn}_5$	54.57	$2.73\text{E}-09$
$\text{Cu}_3\text{Sn}$	86.06	$7.45\text{E}-08$
$\text{Cu}_3\text{Sn} + \text{Cu}_6\text{Sn}_5$	58.83	$9.51\text{E}-09$

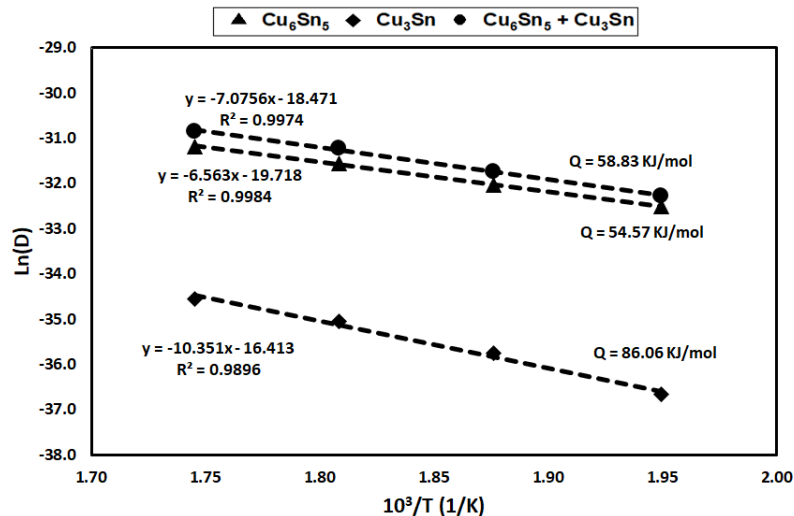


Figure 4.34 Arrhenius plot for the growth of the IMCs layer after the reflow process

Table 4.11 Diffusion coefficient and activation energies of intermetallic phases after aging

Intermetallic phases	Activation energy, Q (kJ/mol)	Diffusion coefficient, $D_0$ (m <sup>2</sup> /s)
Cu <sub>6</sub> Sn <sub>5</sub>	58.59	2.14E-10
Cu <sub>3</sub> Sn	91.74	4.52E-07
Cu <sub>3</sub> Sn + Cu <sub>6</sub> Sn <sub>5</sub>	68.62	7.46E-09

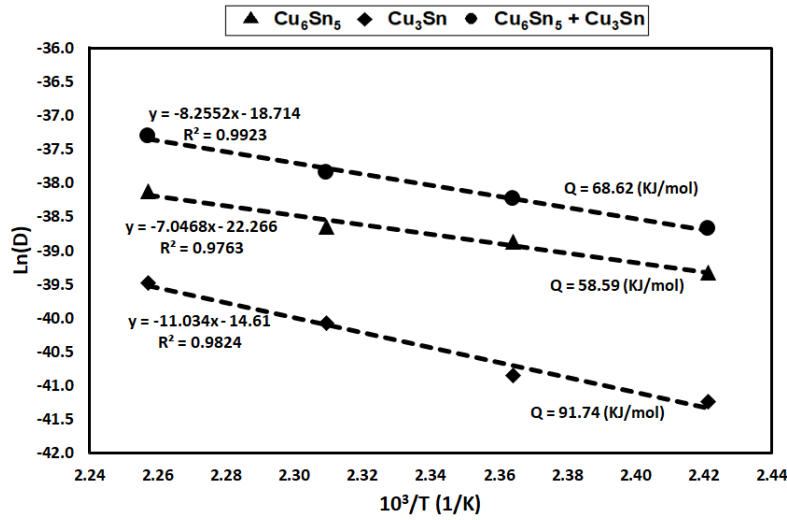


Figure 4.35 Arrhenius plot for the growth of the IMCs layer after the aging process

**Figure 4.34** and **Figure 4.35** shows the Arrhenius plots for the growth of the Cu<sub>6</sub>Sn<sub>5</sub>, Cu<sub>3</sub>Sn, and total thickness layers formed at the solder joint after reflow and aging. The activation energies are 54.57, 86.06, and 58.8371kJ/mol for reflow and 91.74, 58.59, and 68.62kJ/mol for aging respectively. The activation energy of the Cu<sub>6</sub>Sn<sub>5</sub> phase was created to be lower than that of the Cu<sub>3</sub>Sn phase. This states that the formation of the Cu<sub>6</sub>Sn<sub>5</sub> layer is more thermodynamically stable than the Cu<sub>3</sub>Sn phase; however, the activation energy of the total (Cu<sub>6</sub>Sn<sub>5</sub> + Cu<sub>3</sub>Sn) layer found to be between Cu<sub>6</sub>Sn<sub>5</sub> and Cu<sub>3</sub>Sn phases, which seems to be acceptable. Some researchers are reported the same trend with related literature [160, 185, 191]. **Table 4.12** shows the activation energies obtained by the other researchers and comparable with this study. This research shown that the activation energies are in acceptance with literature.

Table 4.12 Comparison of activation energies obtained here to those from other literature studies

Solder/substrate	Soldering method	Aging Temperature (K)	Aging Time (s)	IMC Phases	Activation energy (kJ/mol)	Reference
Sn-3.0Ag-0.5Cu-SiC/ Cu	Reflow	413-443	9.0E+04-3.6E+05	Cu <sub>3</sub> Sn	91.73	<b>Current work</b>
				Cu <sub>6</sub> Sn <sub>5</sub>	59.68	
				Cu <sub>3</sub> Sn + Cu <sub>6</sub> Sn <sub>5</sub>	64.71	
Sn-3.8Ag-0.7Cu/CSP/OSP	Reflow	373-423	0-3.6E+6	Cu <sub>3</sub> Sn	119.80	<b>[185]</b>
Sn-3.0Ag-0.5Cu/Cu	Reflow	373-443	0-2.4E+6	Cu <sub>3</sub> Sn + Cu <sub>6</sub> Sn <sub>5</sub>	75.1	<b>[185]</b>
Sn-3.0Ag-0.5Cu/Cu (THO)	Reflow	373-443	0-5.2E+6	Cu <sub>6</sub> Sn <sub>5</sub>	49.7	<b>[185]</b>
				Cu <sub>3</sub> Sn + Cu <sub>6</sub> Sn <sub>5</sub>	85.5	
Sn-3.0Ag-0.5Cu/Cu (THX)	Reflow	373-443	0-5.2E+6	Cu <sub>6</sub> Sn <sub>5</sub>	41.3	<b>[185]</b>
				Cu <sub>3</sub> Sn + Cu <sub>6</sub> Sn <sub>5</sub>	79.9	
Sn-3.5Ag	Dipping	343-443	0-3.6E+6	Cu <sub>6</sub> Sn <sub>5</sub>	58.59	<b>[191]</b>
				Cu <sub>3</sub> Sn + Cu <sub>6</sub> Sn <sub>5</sub>	75.16	
Sn-0.3Ag-0.7Cu/Cu	Dipping	373-443	0-3.6E+6	Cu <sub>3</sub> Sn	119.04	<b>[192]</b>
				Cu <sub>6</sub> Sn <sub>5</sub>	51.59	
				Cu <sub>3</sub> Sn + Cu <sub>6</sub> Sn <sub>5</sub>	80.65	
Sn-5Bi	Reflow	343-443	0-2.6E+6	Cu <sub>3</sub> Sn	90.50	<b>[193]</b>
				Cu <sub>6</sub> Sn <sub>5</sub>	98.35	
				Cu <sub>3</sub> Sn + Cu <sub>6</sub> Sn <sub>5</sub>	107.10	
Sn-3.0Ag-0.5Cu/CSP/OSP	Reflow	373-443	0-5.2E+6	Cu <sub>6</sub> Sn <sub>5</sub>	41.30	<b>[194]</b>
				Cu <sub>3</sub> Sn + Cu <sub>6</sub> Sn <sub>5</sub>	79.90	
Sn-3.8Ag-0.7Cu/Cu	Reflow	398-443	0-5.4E+6	Cu <sub>3</sub> Sn + Cu <sub>6</sub> Sn <sub>5</sub>	92.6	<b>[195]</b>
Sn-3.5Ag-0.7Cu/Cu	Reflow	393-463	0-3.6E+6	Cu <sub>3</sub> Sn + Cu <sub>6</sub> Sn <sub>5</sub>	88.2	<b>[196]</b>

#### 4.6 Summary

The solder joint microstructure is essential for the reliability of the solder joint and it is obtained through a metallurgical reaction. In this chapter, solder joint metallurgy, microstructure, wetting behavior and hardness evolution of two composite solders under thermal aging was comparatively studied. According to the experimental result, SiC and Ni-coated SiC reinforcements effectively suppress the growth of Cu<sub>6</sub>Sn<sub>5</sub> and Cu<sub>3</sub>Sn IMCs under thermal aging and wetting properties are

improved. In addition, Ni-coated SiC reinforcement improved the hardness of the SAC305 solder alloy to some extent. Fundamental concepts associated with IMCs formation and growth in solder joints have been presented in this chapter. These include diffusion, solid-state growth, and growth amongst others. The experimental procedure and methodology used for the study of IMCs layer formation and growth in SAC305 solder joint are presented in chapter 4.

## 5 CHAPTER 5: Claims

Based on the presented experimental results, the claims below are presented according to the sequence of different phenomena.

**Claim (1):** In the case of SiC-reinforced solder, composite samples prepared by ball milling and subsequently formed by PM method, experimental data are proved that the use of nickel-coated SiC reinforcement particles promotes homogeneous distribution of reinforcement particles, reduces the porosity area, and provides higher strength.

**(1.a)** Average neighbour's particle distance are described the agglomeration and dispersion of reinforcement particles in the matrix. The poor dispersion of the particles is due to the agglomeration of the particles in the matrix and may lead to the weakening of the mechanical properties. Skewness diagram revealed that the  $N_q$  (number of the reinforcing particles) distribution varies significantly with the reinforcement composition. Average neighbour's particle distance of both composite solders seen to decrease as the weight fraction of reinforcement increased. The experimental results confirmed that Ni-coated SiC has a lower skewness value and average neighbour's particle distance than the SiC i.e the distribution of Ni-coated SiC particles are more homogeneous than the SiC particles in the SAC305 solder.

**(1.b)** Ni-coated SiC reinforced composite solder has a lower porosity than SAC305/SiC composites because the reinforcement particles distributed homogeneously. As a result of this homogeneous distribution, the Ni-coated SiC was less clustered, thus a reduced amount of porosity formed around the clusters.

**(1.c)** According to the lower porosity content, the changes in the compressive strength of the composite solders were observed and the SAC305/SiC(Ni) solder composite has higher compressive strength than the SAC305/SiC.

**(1.d)** SiC decreases contact angle and increases the spread area because the SiC composites are probably decreasing the surface energy of the copper substrate. The application of the Ni coating further reinforces this tendency because Ni has a higher adsorption capacity and it is reduced the surface energy and growth velocity of the IMC. Added Ni-coated SiC particles accumulated at the interface between the molten solder and the flux during soldering; thereby lowering the interfacial surface energy.

**Claim (2):** Relative contact perimeter (RCP) is defined as a contact surface between metallic solder and ceramic reinforcement particles and this is a new parameter - which is not been applied in the literature. The increment of RCP in the SAC305 solder composites was observed experimentally measuring the change of reinforcement content. Experimental results are proven that Ni-coated SiC particles are improved the relative contact perimeter. This is an effective value to determine the extent of the contact surface, which determines the properties of the composite. The increment of RCP in the SAC305 solder composites was observed experimentally measuring the change of reinforcement content.

**(2.a)** Experimental results were proven that the RCP was increased in the Ni-coated SiC reinforced samples. Silicon carbide is a ceramic material with a covalent bond and has stable chemical properties. Ni is a metallic bonded material and it has good wetting characteristics with Sn-based solder because SAC305 solder has also metallic bonding. The SiC(Ni) particles are easily reacted with the SAC305 solder particles and form a strong metallic-metallic bond at the interface.

**Claim (3):** Thickness of the interfacial IMCs layer between the solder and Cu substrate shows the difference after the addition of SiC and Ni-coated SiC reinforcement to SAC305 solder. It can be used to simulate how the IMC layer changes during reflow and aging under the influence of time and temperature.

**(3.a)** The thickness of interfacial IMCs between solder and Cu substrate shows an obvious difference after the addition of SiC and Ni-coated SiC in the SAC305 solder. The reduction of the IMCs layer on the Sn-Cu interface was observed experimentally during the reflow process. These reinforcement particles reduce the surface energy and inhibit the growth of IMC layers.

During the reflowing process, the SiC and Ni-coated SiC particles are distributed in the liquid because it does not melt on the Cu surface due to the high melting temperature. The SiC and Ni-coated SiC particles can behave as a barrier to the diffusion of Cu atoms from the substrate. The results are proven that IMCs layer thickness decreased as the amount of SiC and Ni-coated SiC increases in the SAC305 solder.

**(3.b)** The experimental results are shown that as time (aging and reflow) and temperature increase, the thickness of interfacial IMCs ( $\text{Cu}_6\text{Sn}_5$  and  $\text{Cu}_3\text{Sn}$ ) are both increased. Ceramic particles enhanced the activation energy which reduced the reaction rate as it is well known that lower activation energy indicates a faster reaction rate. Although this phenomenon is also observed in composite solders, the growth rate of interfacial IMCs is inhibited after the addition of SiC and Ni-coated SiC reinforcement. The activation energy of  $\text{Cu}_6\text{Sn}_5$  was observed to be lower than that of  $\text{Cu}_3\text{Sn}$ . The activation energy of the ( $\text{Cu}_6\text{Sn}_5+\text{Cu}_3\text{Sn}$ ) lies in between  $\text{Cu}_6\text{Sn}_5$  and  $\text{Cu}_3\text{Sn}$  phases which appears reasonable. I proved that the IMCs layer thickness is dependent on time (reflow and aging) and temperature (reflow and aging). and this method relies on the calculation of activation energies by plotting the diffusion coefficient as the function of temperature (reflow and aging).



## Acknowledgements

I would like to take this opportunity to express my sincere gratitude and deep appreciation to my supervisors, Prof. Zoltán Gácsi and Dr. Gergely Gréta at the University of Miskolc, for their valuable guidance, continuous support, and constructive suggestions throughout all my Ph.D. study period.

I am grateful to my independent assessor, Prof. George Kaptay, Prof. Török Tamás, and Dr. Peter Bamuli, for his advice and discussions for the Ph.D. period. Heartfelt thanks are given to the Institute of Physical Metallurgy, Metal Forming, and Nanotechnology for providing me with all the necessary laboratory and a good work environment for carrying out my research.

Deep gratitude is also expressed to “Antal Kerpely Doctoral School of Material Science and Technology” and Prof. Valeria Mertinger in the faculty of Materials Science for providing an opportunity to research the university of Miskolc. My gratitude extends to the I would like to thank Dr. Kovacs Arpad, Dr. Daniel Koncz-Horvath, and Dr. Anna Sycheva for their kind cooperation and scheduling of the SEM investigation.

A special thanks to Mrs. Aniko Markus and Mrs. Napsugar Bodnar for helping with both pre- and post-experimental sample preparation throughout my Ph.D. I show my appreciation to Mr. Dheeraj Varanasi, Dr. Tamas Miko, Zoltan David Gyoker, Dávid Angel, Tamás Bubonyi, Filep Ádám, Dr. Márton Benke, Dr. Zsolt Veres, Daniel Pethő, Mr. Tabish Aftab, and Mr. Raghawendra Pratap Singh Sisodia for their invaluable support. I would like to thanks Mrs. Judit Szabo, Mrs. Agnesz Solczi, Dr. Sveda Maria, Mrs. Nora Orosz-Forizs, and Mrs. Stumpf Eva for their continued and valuable support in the administrative work at the university. Finally, I would like to thank all my colleagues both Hungarian and International for helping, interacting, and supporting my thesis period.

I would like to show my appreciation for the Tempus Public Foundation and Stipendium Hungaricum scholarship program for selecting and providing financial assistance for my wonderful journey in Hungary and Europe. I would like to special thanks to my supervisor Prof. Zoltán Gácsi for providing me a part of nano-GINOP2.3.2-15-2016-00027 “Sustainable operation of the workshop of excellence for the research and development of crystalline and amorphous nanostructured materials” project implemented in the framework of the Szechenyi 2020 program. The realization of this project is supported by the European Union.

Finally, I am grateful for my wife (Mrs. Mamta Pal), daughter (Miss Samridhi Pal), who was a constant support system in my life. A special thanks to, Mrs. Neetu Bajaj and Dr. Vineet Bajaj who constantly support my Ph.D. duration and helped me in all kinds of supports.

## References:

- [1] Chang, Y. W., S. H. Chiu, Chih Chen, and D. J. Yao. "Effect of Si-die dimensions on electromigration failure time of flip-chip solder joints." *Materials Chemistry and Physics* 127, no. 1-2 (2011): 85-90.
- [2] Li, Y. I., Kyoung-sik Moon, and C. P. Wong. "Electronics without lead." *Science* 308, no. 5727 (2005): 1419-1420.
- [3] Vianco, Paul T., and Darrel R. Frear. "Issues in the replacement of lead-bearing solders." *JOM* 45, no. 7 (1993): 14-19.
- [4] Abtew, Mulugeta, and Guna Selvaduray. "Lead-free solders in microelectronics." *Materials Science and Engineering: R: Reports* 27, no. 5-6 (2000): 95-141.
- [5] Omaç, F., D. Ozyurek, and M. Erer. "Investigation of the wetting properties of ternary Lead-Free solder alloys on copper substrate." *Acta Physica Polonocia-A* 131, no. 1 (2017): 165-167.
- [6] Sharma, Ashutosh, Ashok K. Srivastava, and Byungmin Ahn. "Microstructure, Wetting, and Tensile Behaviors of Sn-Ag Alloy Reinforced with Copper-Coated Carbon Nanofibers Produced by the Melting and Casting Route." *Metallurgical and Materials Transactions A* 50, no. 11 (2019): 5384-5394.
- [7] Erer, Ahmet Mustafa. "Wetting behaviors and interfacial properties of SAC300, SAC305 and SAC0307 ternary Pb-Free solder alloys." *Technological Applied Sciences* 12, no. 4 (2017): 163-169.
- [8] Zhang, Peng, Songbai Xue, Jianhao Wang, Peng Xue, Sujuan Zhong, and Weimin Long. "Effect of nanoparticles addition on the microstructure and properties of lead-free solders: a review." *Applied Sciences* 9, no. 10 (2019): 2044.
- [9] Gain, Asit Kumar, Yan Cheong Chan, and Winco KC Yung. "Microstructure, thermal analysis and hardness of a Sn–Ag–Cu–1wt% nano-TiO<sub>2</sub> composite solder on flexible ball grid array substrates." *Microelectronics Reliability* 51, no. 5 (2011): 975-984.
- [10] Harrison, M. R., J. H. Vincent, and H. A. H. Steen. "Lead-free reflow soldering for electronics assembly." *Soldering & Surface Mount Technology* 13, No. 3 (2001) 21-38.
- [11] Amagai, Masazumi. "Mechanical reliability in electronic packaging." *Microelectronics Reliability* 42, no. 4-5 (2002): 607-627.
- [12] El-Daly, A. A., and A. E. Hammad. "Development of high strength Sn–0.7Cu solders with the addition of small amount of Ag and In." *Journal of Alloys and Compounds* 509, no. 34 (2011): 8554-8560.
- [13] Sugauma, Katsuaki. "Advances in lead-free electronics soldering." *Current Opinion in Solid State and Materials Science* 5, no. 1 (2001): 55-64.
- [14] Lau, John, Walter Dauksher, Joe Smetana, Rob Horsley, Dongkai Shangguan, Todd Castello, Irv Menis, Dave Love, and Bob Sullivan. "Design for lead-free solder joint reliability of high-density packages."

- Soldering & surface mount technology* 16 No. 1 (2004): 12-26.
- [15] Sozhamannan, G. G., and S. Balasivanandha Prabu. "Influence of interface compounds on interface bonding characteristics of aluminium and silicon carbide." *Materials characterization* 60, no. 9 (2009): 986-990.
- [16] Shangguan, Dongkai, Achyuta Achari, and Wells Green. "Application of lead-free eutectic Sn-Ag solder in no-clean thick film electronic modules." *IEEE Transactions on Components, Packaging, and Manufacturing Technology: Part B* 17, no. 4 (1994): 603-611.
- [17] Shangguan, Dongkai. "Leading the Lead-free transition." *Circuits Assembly, March* (2004).
- [18] Fawzy, A., S. A. Fayek, M. Sobhy, E. Nassr, M. M. Mousa, and G. Saad. "Effect of ZnO nanoparticles addition on thermal, microstructure and tensile properties of Sn-3.5Ag-0.5Cu (SAC355) solder alloy." *Journal of Materials Science: Materials in Electronics* 24, no. 9 (2013): 3210-3218.
- [19] Gain, Asit Kumar, and Y. C. Chan. "Growth mechanism of intermetallic compounds and damping properties of Sn-Ag-Cu-1 wt% nano-ZrO<sub>2</sub> composite solders." *Microelectronics Reliability* 54, no. 5 (2014): 945-955.
- [20] Wang, L., D. Q. Yu, S. Q. Han, H. T. Ma, and H. P. Xie. "The evaluation of the new composite lead free solders with the novel fabricating process." In *Proceedings of 2004 International Conference on the Business of Electronic Product Reliability and Liability (IEEE Cat. No. 04EX809)*, pp. 50-56. IEEE, 2004.
- [21] Chuang, T. H., M. W. Wu, S. Y. Chang, S. F. Ping, and L. C. Tsao. "Strengthening mechanism of nano-Al<sub>2</sub>O<sub>3</sub> particles reinforced Sn-3.5Ag-0.5Cu lead-free solder." *Journal of Materials Science: Materials in Electronics* 22, no. 8 (2011): 1021-1027.
- [22] Tsao, L. C., R. W. Wu, Te-Hsien Cheng, Kuo-Huan Fan, and R. S. Chen. "Effects of nano-Al<sub>2</sub>O<sub>3</sub> particles on microstructure and mechanical properties of Sn-3.5Ag-0.5Cu composite solder ball grid array joints on Sn/Cu pads." *Materials & Design* 50 (2013): 774-781.
- [23] Tsao, L. C., S. Y. Chang, C. I. Lee, W. H. Sun, and C. H. Huang. "Effects of nano-Al<sub>2</sub>O<sub>3</sub> additions on microstructure development and hardness of Sn-3.5Ag-0.5Cu solder." *Materials & Design* 31, no. 10 (2010): 4831-4835.
- [24] Wang, X., Y. C. Liu, C. Wei, H. X. Gao, P. Jiang, and L. M. Yu. "Strengthening mechanism of SiC-particulate reinforced Sn-3.7Ag-0.9Zn lead-free solder." *Journal of Alloys and Compounds* 480, no. 2 (2009): 662-665.
- [25] Tsao, L. C., and S. Y. Chang. "Effects of Nano-TiO<sub>2</sub> additions on thermal analysis, microstructure and tensile properties of Sn-3.5Ag-0.25Cu solder." *Materials & Design* 31, no. 2 (2010): 990-993.
- [26] Ramli, M. I. I., Norainiza Saud, MAA Mohd Salleh, Mohd Nazree Derman, and R. Mohd Said. "Effect

- of TiO<sub>2</sub> additions on Sn-0.7Cu-0.05Ni lead-free composite solder." *Microelectronics Reliability* 65 (2016): 255-264.
- [27] Wen, Yanni, Xiuchen Zhao, Zhuo Chen, Yue Gu, Yong Wang, Zhiwei Chen, and Xinyuan Wang. "Reliability enhancement of Sn-1.0Ag-0.5Cu nano-composite solders by adding multiple sizes of TiO<sub>2</sub> nanoparticles." *Journal of Alloys and Compounds* 696 (2017): 799-807.
- [28] El-Daly, A. A., A. Fawzy, S. F. Mansour, and M. J. Younis. "Novel SiC nanoparticles-containing Sn-1.0Ag-0.5Cu solder with good drop impact performance." *Materials Science and Engineering: A* 578 (2013): 62-71.
- [29] El-Daly, A. A., A. Fawzy, S. F. Mansour, and M. J. Younis. "Thermal analysis and mechanical properties of Sn-1.0Ag-0.5Cu solder alloy after modification with SiC nano-sized particles." *Journal of Materials Science: Materials in Electronics* 24, no. 8 (2013): 2976-2988.
- [30] Ani, Fakhrozi Che, Azman Jalar, Abdullah Aziz Saad, Chu Yee Khor, Roslina Ismail, Zuraihana Bachok, Mohamad Aizat Abas, and Norinsan Kamil Othman. "SAC-xTiO<sub>2</sub> nano-reinforced lead-free solder joint characterizations in ultra-fine package assembly." *Soldering & Surface Mount Technology* 30 No. 1 (2018): 1-13.
- [31] Babaghorbani, P., S. M. L. Nai, and M. Gupta. "Development of lead-free Sn-3.5Ag/SnO<sub>2</sub> nanocomposite solders." *Journal of Materials Science: Materials in Electronics* 20, no. 6 (2009): 571-576.
- [32] Nai, S. M. L., J. V. M. Kuma, M. E. Alam, X. L. Zhong, P. Babaghorbani, and M. Gupta. "Using microwave-assisted powder metallurgy route and nano-size reinforcements to develop high-strength solder composites." *Journal of Materials Engineering and Performance* 19, no. 3 (2010): 335-341.
- [33] Liu, Ping, Pei Yao, and Jim Liu. "Effect of SiC nanoparticle additions on microstructure and microhardness of Sn-Ag-Cu solder alloy." *Journal of Electronic Materials* 37, no. 6 (2008): 874-879.
- [34] Kumar, K. Mohan, V. Kripesh, and Andrew AO Tay. "Single-wall carbon nanotube (SWCNT) functionalized Sn-Ag-Cu lead-free composite solders." *Journal of Alloys and Compounds* 450, no. 1-2 (2008): 229-237.
- [35] Zhong, X., and Manoj Gupta. "High Strength Lead-Free Composite Solder Materials using Nano Al<sub>2</sub>O<sub>3</sub> as Reinforcement." *Advanced engineering materials* 7, no. 11 (2005): 1049-1054.
- [36] Shen, J., Y. C. Liu, Y. J. Han, Y. M. Tian, and H. X. Gao. "Strengthening effects of ZrO<sub>2</sub> nanoparticles on the microstructure and microhardness of Sn-3.5Ag lead-free solder." *Journal of electronic materials* 35, no. 8 (2006): 1672-1679.

- [37] Fouzder, Tama, Asit Kumar Gain, Yan Cheong Chan, Ahmed Sharif, and Winco KC Yung. "Effect of nano  $\text{Al}_2\text{O}_3$  additions on the microstructure, hardness and shear strength of eutectic Sn–9Zn solder on Au/Ni metallized Cu pads." *Microelectronics Reliability* 50, no. 12 (2010): 2051-2058.
- [38] Wang, Yong, Xiuchen Zhao, Xiaochen Xie, Yue Gu, and Ying Liu. "Effects of nano- $\text{SiO}_2$  particles addition on the microstructure, wettability, joint shear force and the interfacial IMC growth of Sn-3.0-Ag-0.5Cu solder." *Journal of Materials Science: Materials in Electronics* 26, no. 12 (2015): 9387-9395.
- [39] Peng, Hao, Guang Chen, Liping Mo, Y. C. Chan, Fengshun Wu, and Hui Liu. "An investigation on the ZnO retained ratio, microstructural evolution, and mechanical properties of ZnO doped Sn-30-Ag-0.5Cu composite solder joints." *Journal of Materials Science: Materials in Electronics* 27, no. 9 (2016): 9083-9093.
- [40] Qu, Min, TianZe Cao, Yan Cui, ZhiWei Jiao, and FengBin Liu. "Effect of ZnO micron-particles on properties and intermetallic compound layers of a Sn-3.0-Ag-0.5Cu solder." *Japanese Journal of Applied Physics* 58 (2019): SHHA04-7.
- [41] Fouzder, Tama, Y. C. Chan, and Daniel K. Chan. "Influence of cerium oxide ( $\text{CeO}_2$ ) nanoparticles on the microstructure and hardness of tin–silver–copper (Sn–Ag–Cu) solders on silver (Ag) surface-finished copper (Cu) substrates." *Journal of Materials Science: Materials in Electronics* 25, no. 12 (2014): 5375-5387.
- [42] Fouzder, Tama, Ismathullakhan Shafiq, Y. C. Chan, A. Sharif, and Winco KC Yung. "Influence of  $\text{SrTiO}_3$  nano-particles on the microstructure and shear strength of Sn–Ag–Cu solder on Au/Ni metallized Cu pads." *Journal of Alloys and Compounds* 509, no. 5 (2011): 1885-1892.
- [43] Tang, Y., G. Y. Li, and Y. C. Pan. "Influence of  $\text{TiO}_2$  nanoparticles on IMC growth in Sn–3.0 Ag–0.5 Cu–x $\text{TiO}_2$  solder joints in reflow process." *Journal of Alloys and Compounds* 554 (2013): 195-203.
- [44] Chen, Guang, Hao Peng, Vadim V. Silberschmidt, Y. C. Chan, Changqing Liu, and Fengshun Wu. "Performance of Sn–3.0Ag–0.5Cu composite solder with TiC reinforcement: physical properties, solderability and microstructural evolution under isothermal ageing." *Journal of Alloys and Compounds* 685 (2016): 680-689.
- [45] Sharma, Ashutosh, B. G. Baek, and Jae Pil Jung. "Influence of  $\text{La}_2\text{O}_3$  nanoparticle additions on microstructure, wetting, and tensile characteristics of Sn–Ag–Cu alloy." *Materials & Design* 87 (2015): 370-379.
- [46] Chellvarajoo, Srivalli, and M. Z. Abdullah. "Microstructure and mechanical properties of Pb-free Sn–3.0Ag–0.5Cu solder pastes added with NiO nanoparticles after reflow soldering process." *Materials*

- & *Design* 90 (2016): 499-507.
- [47] Chellvarajoo, Srivalli, M. Z. Abdullah, and Z. Samsudin. "Effects of Fe<sub>2</sub>NiO<sub>4</sub> nanoparticles addition into lead free Sn–3.0Ag–0.5Cu solder pastes on microstructure and mechanical properties after reflow soldering process." *Materials & Design* 67 (2015): 197-208.
- [48] El-Daly, A. A., W. M. Desoky, T. A. Elmosalami, M. G. El-Shaarawy, and A. M. Abdraboh. "Microstructural modifications and properties of SiC nanoparticles-reinforced Sn–3.0Ag–0.5Cu solder alloy." *Materials & Design* 65 (2015): 1196-1204.
- [49] Chen, Guang, Fengshun Wu, Changqing Liu, Vadim V. Silberschmidt, and Y. C. Chan. "Microstructures and properties of new Sn–Ag–Cu lead-free solder reinforced with Ni-coated graphene nanosheets." *Journal of Alloys and Compounds* 656 (2016): 500-509.
- [50] Wang, Z. X., I. Dutta, and B. S. Majumdar. "Thermomechanical response of a lead-free solder reinforced with a shape memory alloy." *Scripta materialia* 54, no. 4 (2006): 627-632.
- [51] Nai, S. M. L., J. Wei, and M. Gupta. "Influence of ceramic reinforcements on the wettability and mechanical properties of novel lead-free solder composites." *Thin Solid Films* 504, no. 1-2 (2006): 401-404.
- [52] Nai, S. M. L., J. Wei, and M. Gupta. "Lead-free solder reinforced with multiwalled carbon nanotubes." *Journal of electronic materials* 35, no. 7 (2006): 1518-1522.
- [53] Nai, Sharon ML, Jun Wei, and Manoj Gupta. "Development of lead-free solder composites containing nanosized hybrid (ZrO<sub>2</sub>+ 8 mol.% Y<sub>2</sub>O<sub>3</sub>) particulates." In *Solid state phenomena*, 111(2006): 59-62.
- [54] Zhong, X. L., and M. Gupta. "Development of lead-free Sn–0.7Cu/Al<sub>2</sub>O<sub>3</sub> nanocomposite solders with superior strength." *Journal of Physics D: Applied Physics* 41, no. 9 (2008): 095403.
- [55] Izzati Z.N., Al-Bakri A. M., Salleh M. A. A. M., Ahmad R., Mortar N. A. M., Ramasamy S., "Microstructure and Mechanical Properties of Geopolymer Ceramic Reinforced Sn-0.7Cu Solder" *Materials Science and Engineering* 864 (2020) 012041.
- [56] Liu, Xiaoying, Mingliang Huang, Chi Man Lawrence Wu, and Lai Wang. "Effect of Y<sub>2</sub>O<sub>3</sub> particles on microstructure formation and shear properties of Sn-58Bi solder." *Journal of Materials Science: Materials in Electronics* 21, no. 10 (2010): 1046-1054.
- [57] Sharma, Ashutosh, Sumit Bhattacharya, Siddhartha Das, and Karabi Das. "Fabrication of Sn-Ag/CeO<sub>2</sub> electro-composite solder by pulse electrodeposition." *Metallurgical and Materials Transactions A* 44, no. 12 (2013): 5587-5601.
- [58] Zhao, Zhenyu, Lei Liu, Hyun Seok Choi, Jian Cai, Qian Wang, Yuming Wang, and Guisheng Zou. "Effect of nano-Al<sub>2</sub>O<sub>3</sub> reinforcement on the microstructure and reliability of Sn–3.0Ag–0.5Cu solder joints."

- Microelectronics Reliability* 60 (2016): 126-134.
- [59] Gu, Yue, Xiuchen Zhao, Yi Li, Ying Liu, Yong Wang, and Zhenyu Li. "Effect of nano-Fe<sub>2</sub>O<sub>3</sub> additions on wettability and interfacial intermetallic growth of low-Ag content Sn–Ag–Cu solders on Cu substrates." *Journal of Alloys and Compounds* 627 (2015): 39-47.
- [60] Dele-Afolabi, T. T., MA Azmah Hanim, O. J. Ojo-Kupoluyi, and R. Calin. "Impact of different isothermal aging conditions on the IMC layer growth and shear strength of MWCNT-reinforced Sn–5Sb solder composites on Cu substrate." *Journal of Alloys and Compounds* 808 (2019): 151714.
- [61] Sun, Huayu, Y. C. Chan, and Fengshun Wu. "Effect of CNTs and Ni coated CNTs on the mechanical performance of Sn-57.6Bi-0.4Ag BGA solder joints." *Materials Science and Engineering: A* 656 (2016): 249-255.
- [62] Ma, Dongliang, and Ping Wu. "Improved microstructure and mechanical properties for Sn-58Bi-0.7Zn solder joint by addition of graphene nanosheets." *Journal of Alloys and Compounds* 671 (2016): 127-136.
- [63] Yang, Ming, Hongjun Ji, Shuai Wang, Yong-Ho Ko, Chang-Woo Lee, Jianxin Wu, and Mingyu Li. "Effects of Ag content on the interfacial reactions between liquid Sn–Ag–Cu solders and Cu substrates during soldering." *Journal of Alloys and Compounds* 679 (2016): 18-25.
- [64] Das, Sazol Kumar, A. Sharif, Yan Cheong Chan, Ning Bew Wong, and W. K. C. Yung. "Influence of small amount of Al and Cu on the microstructure, microhardness and tensile properties of Sn–9Zn binary eutectic solder alloy." *Journal of alloys and compounds* 481, no. 1-2 (2009): 167-172.
- [65] Ali, Bakhtiar, Mohd Faizul Mohd Sabri, Iswadi Jauhari, and Nazatul Liana Sukiman. "Impact toughness, hardness and shear strength of Fe and Bi added Sn-1Ag-0.5Cu lead-free solders." *Microelectronics Reliability* 63 (2016): 224-230.
- [66] Tao, Q. B., L. Benabou, L. Vivet, V. N. Le, and F. B. Ouezdou. "Effect of Ni and Sb additions and testing conditions on the mechanical properties and microstructures of lead-free solder joints." *Materials Science and Engineering: A* 669 (2016): 403-416.
- [67] Tao, Q. B., L. Benabou, V. N. Le, H. Hwang, and D. B. Luu. "Viscoplastic characterization and post-rupture microanalysis of a novel lead-free solder with small additions of Bi, Sb and Ni." *Journal of Alloys and Compounds* 694 (2017): 892-904.
- [68] Ma, Z. L., S. A. Belyakov, and C. M. Gourlay. "Effects of cobalt on the nucleation and grain refinement of Sn-3Ag-0.5Cu solders." *Journal of Alloys and Compounds* 682 (2016): 326-337.
- [69] Zhang, Liang, Ji-guang Han, Yong-huan Guo, and Cheng-wen He. "Effect of rare earth Ce on the fatigue life of Sn-Ag-Cu solder joints in WLCSP device using FEM and experiments." *Materials Science*

- and Engineering: A* 597 (2014): 219-224.
- [70] Gao, Lili, Songbai Xue, Liang Zhang, Zhong Sheng, Feng Ji, Wei Dai, Sheng-lin Yu, and Guang Zeng. "Effect of alloying elements on properties and microstructures of Sn-Ag-Cu solders." *Microelectronic Engineering* 87, no. 11 (2010): 2025-2034.
- [71] Yang, Zhongbao, Wei Zhou, and Ping Wu. "Effects of Ni-coated carbon nanotubes addition on the electromigration of Sn-Ag-Cu solder joints." *Journal of alloys and compounds* 581 (2013): 202-205.
- [72] Xu, Lianyong, Xi Chen, Hongyang Jing, Lixia Wang, Jun Wei, and Yongdian Han. "Design and performance of Ag nanoparticle-modified graphene/Sn-Ag-Cu lead-free solders." *Materials Science and Engineering: A* 667 (2016): 87-96.
- [73] Liu, Johan, Cristina Andersson, Yulai Gao, and Qijie Zhai. "Recent development of nano-solder paste for electronics interconnect applications." *10th Electronics Packaging Technology Conference, IEEE*, (2008): 84-93.
- [74] Ma, Limin, Yong Zuo, Sihan Liu, Fu Guo, Andre Lee, and K. N. Subramanian. "Whisker growth behaviors in POSS-silanol modified Sn-3.0-Ag-0.5Cu composite solders." *Journal of Alloys and Compounds* 657 (2016): 400-407.
- [75] Al-Aqeeli, N., K. Abdullahi, A. S. Hakeem, C. Suryanarayana, T. Laoui, and S. Nouari. "Synthesis, characterisation and mechanical properties of SiC reinforced Al based nanocomposites processed by MA and SPS." *Powder Metallurgy* 56, no. 2 (2013): 149-157.
- [76] El-Daly, A. A., M. Abdelhameed, M. Hashish, and A. M. Eid. "Synthesis of Al/SiC nanocomposite and evaluation of its mechanical properties using pulse echo overlap method." *Journal of Alloys and Compounds* 542 (2012): 51-58.
- [77] Woo, K. D., and D. L. Zhang. "Fabrication of Al-7wt%Si-0.4 wt% Mg/SiC nanocomposite powders and bulk nanocomposites by high energy ball milling and powder metallurgy." *Current Applied Physics* 4, no. 2-4 (2004): 175-178.
- [78] Tsao, L. C. "An investigation of microstructure and mechanical properties of novel Sn-3.5Ag-0.5Cu-XTiO<sub>2</sub> composite solders as functions of alloy composition and cooling rate." *Materials Science and Engineering: A* 529 (2011): 41-48.
- [79] Mokhtari, Omid, Ali Roshanghias, Roya Ashayer, Hireen R. Kotadia, Farzad Khomamizadeh, Amir H. Kokabi, Michael P. Clode, Mark Miodownik, and Samjid H. Mannan. "Disabling of nanoparticle effects at increased temperature in nanocomposite solders." *Journal of electronic materials* 41, no. 7 (2012): 1907-1914.
- [80] Yang, Zhongbao, Wei Zhou, and Ping Wu. "Effects of Ni-coated carbon nanotubes addition on the



- microstructure and mechanical properties of Sn–Ag–Cu solder alloys." *Materials Science and Engineering: A* 590 (2014): 295-300.
- [81] Yang, Zhongbao, Wei Zhou, and Ping Wu. "Effects of Ni-coated carbon nanotubes addition on the microstructure and mechanical properties of Sn–Ag–Cu solder alloys." *Materials Science and Engineering: A* 590 (2014): 295-300.
- [82] Fathian, Zahra, Ali Maleki, and Behzad Niroumand. "Synthesis and characterization of ceramic nanoparticles reinforced lead-free solder." *Ceramics International* 43, no. 6 (2017): 5302-5310.
- [83] Suryanarayana, C., and Nasser Al-Aqeeli. "Mechanically alloyed nanocomposites." *Progress in Materials Science* 58, no. 4 (2013): 383-502.
- [84] Suryanarayana, Cury. "Mechanical alloying and milling." *Progress in materials science* 46, no. 1-2 (2001): 1-184.
- [85] Suryanarayana, C., E. Ivanov, and V. V. Boldyrev. "The science and technology of mechanical alloying." *Materials Science and Engineering: A* 304 (2001): 151-158.
- [86] Upadhyaya, Anish, and Guneet Sethi. "Effect of heating mode on the densification and microstructural homogenization response of premixed bronze." *Scripta materialia* 56, no. 6 (2007): 469-472.
- [87] Gupta, M., and W. L. E. Wong. "Enhancing overall mechanical performance of metallic materials using two-directional microwave assisted rapid sintering." *Scripta Materialia* 52, no. 6 (2005): 479-483.
- [88] Wong, Wai Leong Eugene, S. Karthik, and Manoj Gupta. "Development of high performance Mg–Al<sub>2</sub>O<sub>3</sub> composites containing Al<sub>2</sub>O<sub>3</sub> in submicron length scale using microwave assisted rapid sintering." *Materials Science and technology* 21, no. 9 (2005): 1063-1070.
- [89] Mavoori, H., and S. Jin. "New, creep-resistant, low melting point solders with ultrafine oxide dispersions." *Journal of Electronic Materials* 27, no. 11 (1998): 1216-1222.
- [90] Shi, Yaowu, Jianping Liu, Yanfu Yan, Zhidong Xia, Yongping Lei, Fu Guo, and Xiaoyan Li. "Creep properties of composite solders reinforced with nano-and microsized particles." *Journal of electronic materials* 37, no. 4 (2008): 507-514.
- [91] Issa, Hasan Kaser, Aboozar Taherizadeh, Ali Maleki, and Abbas Ghaei. "Development of an aluminum/amorphous nano-SiO<sub>2</sub> composite using powder metallurgy and hot extrusion processes." *Ceramics International* 43, no. 17 (2017): 14582-14592.
- [92] Shen, J., Y. C. Liu, and H. X. Gao. "In situ nanoparticulate-reinforced lead-free Sn–Ag composite prepared by rapid solidification." *Journal of Materials Science: Materials in Electronics* 18, no. 4 (2007): 463-468.

- [93] Hwang, Seong-Yong, Joo-Won Lee, and Zin-Hyoung Lee. "Microstructure of a lead-free composite solder produced by an in-situ process." *Journal of electronic materials* 31, no. 11 (2002): 1304-1308.
- [94] Kumar, Girish, and K. Narayan Prabhu. "Review of non-reactive and reactive wetting of liquids on surfaces." *Advances in colloid and interface science* 133, no. 2 (2007): 61-89.
- [95] Vaynman, S., and M. E. Fine. "Development of fluxes for lead-free solders containing zinc." *Scripta materialia* 41, no. 12 (1999): 1269 –1271.
- [96] Bernardin, John D., Issam Mudawar, Christopher B. Walsh, and Elias I. Franses. "Contact angle temperature dependence for water droplets on practical aluminum surfaces." *International journal of heat and mass transfer* 40, no. 5 (1997): 1017-1033.
- [97] Lopez, V. H., and A. R. Kennedy. "Flux-assisted wetting and spreading of Al on TiC." *Journal of colloid and interface science* 298, no. 1 (2006): 356-362.
- [98] Lin, D. C., G. X. Wang, T. S. Srivatsan, Meslet Al-Hajri, and M. Petraroli. "Influence of titanium dioxide nanopowder addition on microstructural development and hardness of tin–lead solder." *Materials Letters* 57, no. 21 (2003): 3193-3198.
- [99] Nai, S. M. L., J. Wei, and M. Gupta. "Effect of carbon nanotubes on the shear strength and electrical resistivity of a lead-free solder." *Journal of Electronic Materials* 37, no. 4 (2008): 515-522.
- [100] Callister Jr, William D., and David G. Rethwisch. *Fundamentals of materials science and engineering: an integrated approach*. John Wiley & Sons, 2020.
- [101] Lin, D., G. X. Wang, T. S. Srivatsan, Meslet Al-Hajri, and M. Petraroli. "The influence of copper nanopowders on microstructure and hardness of lead–tin solder." *Materials Letters* 53, no. 4-5 (2002): 333-338.
- [102] Zhang, Shenghong, and Quanfang Chen. "Fabrication of MWCNT incorporated Sn–Bi composite." *Composites Part B: Engineering* 58 (2014): 275-278.
- [103] Shi, Yaowu, Jianping Liu, Zhidong Xia, Yongping Lei, Fu Guo, and Xiaoyan Li. "Creep property of composite solders reinforced by nano-sized particles." *Journal of Materials Science: Materials in Electronics* 19, no. 4 (2008): 349-356.
- [104] Sharma, Ashutosh, Heung-Rak Sohn, and Jae Pil Jung. "Effect of graphene nanoplatelets on wetting, microstructure, and tensile characteristics of Sn-3.0Ag-0.5Cu (SAC) alloy." *Metallurgical and Materials Transactions A* 47, no. 1 (2016): 494-503.
- [105] Lee, J.-H., D.-J. Park, J.-N. Heo, Y.-H. Lee, and D.-H. Shin. "Reflow characteristics of Sn-Ag matrix in-situ composite solders." *Scripta materialia* 42, no. 8 (2000): 827-831.
- [106] Nai, S. M. L., J. Wei, and M. Gupta. "Improving the performance of lead-free solder reinforced with

- multi-walled carbon nanotubes." *Materials Science and Engineering: A* 423, no. 1-2 (2006): 166-169.
- [107] Salleh, MAA Mohd, S. D. McDonald, C. M. Gourlay, H. Yasuda, and Kazuhiro Nogita. "Suppression of  $\text{Cu}_6\text{Sn}_5$  in  $\text{TiO}_2$  reinforced solder joints after multiple reflow cycles." *Materials & Design* 108 (2016): 418-428.
- [108] Zhao, Xiuchen, Yanni Wen, Yi Li, Ying Liu, and Yong Wang. "Effect of  $\gamma\text{-Fe}_2\text{O}_3$  nanoparticles size on the properties of Sn-1.0Ag-0.5Cu nano-composite solders and joints." *Journal of Alloys and Compounds* 662 (2016): 272-282.
- [109] Eid, E. A., A. N. Fouda, and El-Shazly M. Duraia. "Effect of adding 0.5wt% ZnO nanoparticles, temperature and strain rate on tensile properties of Sn-5.0wt%Sb-0.5wt%Cu (SSC505) lead free solder alloy." *Materials Science and Engineering: A* 657 (2016): 104-114.
- [110] Xu, Sha, Yan Cheong Chan, Kaili Zhang, and K. C. Yung. "Interfacial intermetallic growth and mechanical properties of carbon nanotubes reinforced Sn-3.5Ag-0.5Cu solder joint under current stressing." *Journal of alloys and compounds* 595 (2014): 92-102.
- [111] Han, Y. D., H. Y. Jing, S. M. L. Nai, L. Y. Xu, Cher Ming Tan, and Jun Wei. "Effect of Ni-coated carbon nanotubes on interfacial intermetallic layer growth." In *2009 11th Electronics Packaging Technology Conference, IEEE, (2009)* 292-295.
- [112] Chellvarajoo, Srivalli, M. Z. Abdullah, and C. Y. Khor. "Effects of diamond nanoparticles reinforcement into lead-free Sn-3.0Ag-0.5Cu solder pastes on microstructure and mechanical properties after reflow soldering process." *Materials & Design* 82 (2015): 206-215.
- [113] Zhang, Liang, and King-Ning Tu. "Structure and properties of lead-free solders bearing micro and nano particles." *Materials Science and Engineering: R: Reports* 82 (2014): 1-32.
- [114] Amagai, Masazumi. "A study of nanoparticles in Sn-Ag based lead free solders." *Microelectronics Reliability* 48, no. 1 (2008): 1-16.
- [115] Yu, D. Q., L. Wang, C. M. L. Wu, and C. M. T. Law. "The formation of nano- $\text{Ag}_3\text{Sn}$  particles on the intermetallic compounds during wetting reaction." *Journal of Alloys and Compounds* 389, no. 1-2 (2005): 153-158.
- [116] El-Daly, A. A., A. E. Hammad, A. Fawzy, and D. A. Nasrallah. "Microstructure, mechanical properties, and deformation behavior of Sn-1.0Ag-0.5Cu solder after Ni and Sb additions." *Materials & Design* 43 (2013): 40-49.
- [117] Gain, Asit Kumar, and Liangchi Zhang. "The effects of  $\text{TiO}_2$  nanoparticles addition on the thermal shock resistance, shear strength and IMC layer growth of SAC305 alloy." *Materialia* 3 (2018): 64-73.

- [118] Schaefer, Matt, Raymond A. Fournelle, and Jin Liang. "Theory for intermetallic phase growth between Cu and liquid Sn-Pb solder based on grain boundary diffusion control." *Journal of Electronic Materials* 27, no. 11 (1998): 1167-1176.
- [119] Wu, Zhong, Lei Liu, Bin Shen, Yating Wu, Yida Deng, Cheng Zhong, and Wenbin Hu. "Mechanical behavior of  $\alpha$ -Al<sub>2</sub>O<sub>3</sub>-coated SiC particle reinforced nickel matrix composites." *Journal of alloys and compounds* 570 (2013): 81-85.
- [120] Kolečák, Roman, Michal Chachula, Pavol Šebo, and Monika Kolečáková. "Wettability and shear strength of active Sn<sub>2</sub>Ti solder on Al<sub>2</sub>O<sub>3</sub> ceramics." *Soldering & surface mount technology* 23 (2011): 224–228.
- [121] Tang, Y., G. Y. Li, and Y. C. Pan. "Effects of TiO<sub>2</sub> nanoparticles addition on microstructure, microhardness and tensile properties of Sn–3.0Ag–0.5Cu–xTiO<sub>2</sub> composite solder." *Materials & Design* 55 (2014): 574-582.
- [122] Lee, Choong-Jae, Kyung Deuk Min, Hyun Joon Park, and Seung-Boo Jung. "Mechanical properties of Sn-58wt%Bi solder containing Ag-decorated MWCNT with thermal aging tests." *Journal of Alloys and Compounds* 820 (2020): 153077.
- [123] Han, Y. D., S. M. L. Nai, H. Y. Jing, L. Y. Xu, C. M. Tan, and J. Wei. "Development of a Sn–Ag–Cu solder reinforced with Ni-coated carbon nanotubes." *Journal of Materials Science: Materials in Electronics* 22, no. 3 (2011): 315-322.
- [124] Han, Y. D., H. Y. Jing, S. M. L. Nai, L. Y. Xu, Cher Ming Tan, and J. Wei. "Creep mitigation in Sn–Ag–Cu composite solder with Ni-coated carbon nanotubes." *Journal of Materials Science: Materials in Electronics* 23, no. 5 (2012): 1108-1115.
- [125] Chen, Guang, Fengshun Wu, Changqing Liu, Vadim V. Silberschmidt, and Y. C. Chan. "Microstructures and properties of new Sn–Ag–Cu lead-free solder reinforced with Ni-coated graphene nanosheets." *Journal of Alloys and Compounds* 656 (2016): 500-509.
- [126] Park, Bum-Geun, Woo-Ram Myung, Choong-Jae Lee, and Seung-Boo Jung. "Mechanical, electrical, and thermal reliability of Sn-58wt.% Bi solder joints with Ag-decorated MWCNT for LED package component during aging treatment." *Composites Part B: Engineering* 182 (2020): 107617.
- [127] Chantaramanee, S., S. Wisutmethangoon, L. Sikong, and T. Plookphol. "Development of a lead-free composite solder from Sn–Ag–Cu and Ag-coated carbon nanotubes." *Journal of Materials Science: Materials in Electronics* 24, no. 10 (2013): 3707-3715.
- [128] Khodabakhshi, F., R. Sayyadi, and N. Shahamat Javid. "Lead free Sn-Ag-Cu solders reinforced by Ni-coated graphene nanosheets prepared by mechanical alloying: Microstructural evolution and

- mechanical durability." *Materials Science and Engineering: A* 702 (2017): 371-385.
- [129] Martin, John Wilson. *Precipitation hardening: theory and applications*. Butterworth-Heinemann, 2012.
- [130] Mughrabi, Haël. "Introductory Chapter: Microstructure and Mechanical Properties." *Materials Science and Technology* (2006).
- [131] Yu, Chi-Yang, Joseph Lee, Wen-Lin Chen, and Jenq-Gong Duh. "Enhancement of the impact toughness in Sn–Ag–Cu/Cu solder joints via modifying the microstructure of solder alloy." *Materials Letters* 119 (2014): 20-23.
- [132] Hu, Xiaowu, Tao Xu, Leon M. Keer, Yulong Li, and Xiongxin Jiang. "Microstructure evolution and shear fracture behavior of aged Sn-3.0Ag-0.5Cu/Cu solder joints." *Materials Science and Engineering: A* 673 (2016): 167-177.
- [133] Tu, Xiaoxuan, Danqing Yi, Jing Wu, and Bin Wang. "Influence of Ce addition on Sn-3.0Ag-0.5Cu solder joints: thermal behavior, microstructure and mechanical properties." *Journal of alloys and compounds* 698 (2017): 317-328.
- [134] Wu, Jie, Song-bai Xue, Jing-wen Wang, Shuang Liu, Yi-long Han, and Liu-jue Wang. "Recent progress of Sn–Ag–Cu lead-free solders bearing alloy elements and nanoparticles in electronic packaging." *Journal of Materials Science: Materials in Electronics* 27, no. 12 (2016): 12729-12763.
- [135] Yu, D. Q., H. P. Xie, and L. Wang. "Investigation of interfacial microstructure and wetting property of newly developed Sn–Zn–Cu solders with Cu substrate." *Journal of Alloys and Compounds* 385, no. 1-2 (2004): 119-125.
- [136] Zaimi, N. S., Mohd Arif Anuar Mohd Salleh, Mohd Mustafa Abdullah Al Bakri, Rita Mohd Said, and Norainiza Saud. "Influence of Non-Metallic Particles Addition on Wettability, Intermetallic Compound Formation and Microhardness of Sn-0.7Cu Lead Free Solder Paste." *Solid State Phenomena*, 280 (2018) 169-174.
- [137] Said, Rita Mohd, Norainiza Saud, Mohd Arif Anuar Mohd Salleh, Mohd Nazree Derman, Mohd Izrul Izwan Ramli, and Norhayanti Mohd Nasir. "Effect of SiC Particles Addition on the Wettability and Intermetallic Compound Layer Formation of Sn-Cu-Ni (SN100C) Solder Paste." *Applied Mechanics and Materials*, 754 (2015) 546-550.
- [138] Vaezi, M. R., S. K. Sadrnezhaad, and L. Nikzad. "Electrodeposition of Ni–SiC nano-composite coatings and evaluation of wear and corrosion resistance and electroplating characteristics." *Colloids and Surfaces A: Physicochemical and Engineering Aspects* 315, no. 1-3 (2008): 176-182.
- [139] Pal, Manoj Kumar, Gréta Gergely, Dániel Koncz-Horváth, and Zoltán Gácsi. "Characterization of the

- interface between ceramics reinforcement and lead-free solder matrix." *Surfaces and Interfaces* (2020): 100576.
- [140] Pavlatou, E. A., M. Stroumbouli, P. Gyftou, and N. Spyrellis. "Hardening effect induced by incorporation of SiC particles in nickel electrodeposits." *Journal of Applied Electrochemistry* 36, no. 4 (2006): 385-394.
- [141] Zimmerman, A. F., G. Palumbo, K. T. Aust, and U. Erb. "Mechanical properties of nickel silicon carbide nanocomposites." *Materials Science and Engineering: A* 328, no. 1-2 (2002): 137-146.
- [142] Gyökér, Zoltán, Gréta Gergely, Dániel Koncz Horváth, Eszter Bodnár, and Zoltán Gácsi. "Role of reinforcement surface treatment on the Sn-3.0Ag-0.5Cu microelectronic joints." *Applied Surface Science* 475 (2019): 982-985.
- [143] Czagány, M., and P. Baumli. "Effect of surfactants on the behavior of the Ni-P bath and on the formation of electroless Ni-P-TiC composite coatings." *Surface and Coatings Technology* 361 (2019): 42-49.
- [144] Pázmán, J., Z. Gacsi, V. Madai, and J. Toth. "Electroless nickel plating with different pre-treatments on silicon carbide particles." *ATOMKI Annual Report* (2009): 54.
- [145] Kretz, F., Zoltán Gácsi, Jenő Kovács, and T. Pieczonka. "The electroless deposition of nickel on SiC particles for aluminum matrix composites." *Surface and Coatings Technology* 180 (2004): 575-579.
- [146] Ahmad, Z. "Coatings." *Principles of Corrosion Engineering and Corrosion Control* (2006): 382-437.
- [147] Jiaqiang, Gao, Liu Lei, Wu Yating, Shen Bin, and Hu Wenbin. "Electroless Ni-P-SiC composite coatings with superfine particles." *Surface and Coatings Technology* 200, no. 20-21 (2006): 5836-5842.
- [148] Arik, Halil. "Effect of mechanical alloying process on mechanical properties of  $\alpha$ -Si<sub>3</sub>N<sub>4</sub> reinforced aluminum-based composite materials." *Materials & Design* 29, no. 9 (2008): 1856-1861.
- [149] German, R. M. "Thermodynamics of sintering." In *Sintering of advanced materials*, pp. 3-32. Woodhead Publishing, 2010.
- [150] Gu, Huandi. "Interfacial reaction of Sn-based solder joint in the package system." (2014).
- [151] Pal, Manoj Kumar, Gréta Gergely, Dániel Koncz-Horváth, and Zoltán Gácsi. "Investigation of the electroless nickel plated sic particles in sac305 solder matrix." *Powder Metallurgy and Metal Ceramics* (2020): 1-9.
- [152] Kumar, Manoj Pal, G. Gergely, D. Koncz-Horvath, and Z. Gacsi. "Influence of ceramic particles on the microstructure and mechanical properties of SAC305 lead-free soldering material." *Archives of Metallurgy and Materials* 64 (2019).

- [153] Thakur, Sanjay Kumar, and Brij Kumar Dhindaw. "The influence of interfacial characteristics between SiCp and Mg/Al metal matrix on wear, coefficient of friction and microhardness." *Wear* 247, no. 2 (2001): 191-201.
- [154] Karnezis, P. A., G. Durrant, and B. Cantor. "Characterization of reinforcement distribution in cast Al-alloy/SiCp composites." *Materials Characterization* 40, no. 2 (1998): 97-109.
- [155] Igathinathane, C., L. O. Pordesimo, E. P. Columbus, W. D. Batchelor, and S. R. Methuku. "Shape identification and particles size distribution from basic shape parameters using ImageJ." *Computers and electronics in agriculture* 63, no. 2 (2008): 168-182.
- [156] Pal, Manoj Kumar, Gréta Gergely, Dániel Koncz-Horváth, and Zoltán Gácsi. "Distribution and Microstructure Analysis of Ceramic Particles in the Lead-Free Solder Matrix." *Crystal Research and Technology* (2020): 2000123.
- [157] Kang, T. Y., Y. Y. Xiu, C. Z. Liu, L. Hui, J. J. Wang, and W. P. Tong. "Bismuth segregation enhances intermetallic compound growth in SnBi/Cu microelectronic interconnect." *Journal of Alloys and Compounds* 509, no. 5 (2011): 1785-1789.
- [158] Tu, King-Ning. "Cu/Sn interfacial reactions: thin-film case versus bulk case." *Materials Chemistry and Physics* 46, no. 2-3 (1996): 217-223.
- [159] Vianco, Paul T., Paul F. Hlava, and Alice C. Kilgo. "Intermetallic compound layer formation between copper and hot-dipped 100In, 50In-50Sn, 100Sn, and 63Sn-37Pb coatings." *Journal of electronic materials* 23, no. 7 (1994): 583-594.
- [160] Flanders, D. R., E. G. Jacobs, and R. F. Pinizzotto. "Activation energies of intermetallic growth of Sn-Ag eutectic solder on copper substrates." *Journal of Electronic Materials* 26, no. 7 (1997): 883-887.
- [161] Choi, S., T. R. Bieler, J. P. Lucas, and K. N. Subramanian. "Characterization of the growth of intermetallic interfacial layers of Sn-Ag and Sn-Pb eutectic solders and their composite solders on Cu substrate during isothermal long-term aging." *Journal of Electronic Materials* 28, no. 11 (1999): 1209-1215.
- [162] Gong, Jicheng, Changqing Liu, Paul P. Conway, and Vadim V. Silberschmidt. "Initial formation of CuSn intermetallic compounds between molten SnAgCu solder and Cu substrate." *Scripta Materialia* 60, no. 5 (2009): 333-335.
- [163] Kang, T. Y., Y. Y. Xiu, L. Hui, J. J. Wang, W. P. Tong, and C. Z. Liu. "Effect of bismuth on intermetallic compound growth in lead free solder/Cu microelectronic interconnect." *Journal of Materials Science & Technology* 27, no. 8 (2011): 741-745.
- [164] Raeder, C. H., L. E. Felton, V. A. Tanzi, and D. B. Knorr. "The effect of aging on microstructure, room

- temperature deformation, and fracture of Sn-Bi/Cu solder joints." *Journal of Electronic Materials* 23, no. 7 (1994): 611-617.
- [165] Pang, H. L. J., K. H. Tan, X. Q. Shi, and Z. P. Wang. "Microstructure and intermetallic growth effects on shear and fatigue strength of solder joints subjected to thermal cycling aging." *Materials Science and Engineering: A* 307, no. 1-2 (2001): 42-50.
- [166] Chang, Kuo-Chin, and Kuo-Ning Chiang. "Aging study on interfacial microstructure and solder-ball shear strength of a wafer-level chip-size package with Au/Ni metallization on a Cu pad." *Journal of electronic materials* 33, no. 11 (2004): 1373-1380.
- [167] Gao, F., T. Takemoto, and H. Nishikawa. "Effects of Co and Ni addition on reactive diffusion between Sn-3.5 Ag solder and Cu during soldering and annealing." *Materials Science and Engineering: A* 420, no. 1-2 (2006): 39-46.
- [168] Nogita, Kazuhiro, D. Mu, S. D. McDonald, J. Read, and Y. Q. Wu. "Effect of Ni on phase stability and thermal expansion of  $\text{Cu}_{6-x}\text{Ni}_x\text{Sn}_5$  (X= 0, 0.5, 1, 1.5 and 2)." *Intermetallics* 26 (2012): 78-85.
- [169] Nogita, Kazuhiro, and Tetsuro Nishimura. "Nickel-stabilized hexagonal  $(\text{Cu,Ni})_6\text{Sn}_5$  in Sn-Cu-Ni lead-free solder alloys." *Scripta Materialia* 59, no. 2 (2008): 191-194.
- [170] El-Daly, A. A., A. M. El-Taher, and T. R. Dalloul. "Enhanced ductility and mechanical strength of Ni-doped Sn-3.0Ag-0.5Cu lead-free solders." *Materials & Design* 55 (2014): 309-318.
- [171] Yin, Zuozhu, Mei Lin, Qi Li, and Xiaochun Lv. "Effects of Ni Nanoparticles on the Growth Rate of Intermetallic Compounds (IMCs) Between Sn-3.0Ag-0.5Cu(SAC305) Solder and Cu-2.0Be Substrate." *Journal of Electronic Materials* 49, no. 11 (2020): 6721-6726.
- [172] Gain, Asit Kumar, and Y. C. Chan. "Growth mechanism of intermetallic compounds and damping properties of Sn-Ag-Cu-1 wt% nano-ZrO<sub>2</sub> composite solders." *Microelectronics Reliability* 54, no. 5 (2014): 945-955.
- [173] Nai, S. M. L., J. Wei, and M. Gupta. "Interfacial intermetallic growth and shear strength of lead-free composite solder joints." *Journal of Alloys and Compounds* 473, no. 1-2 (2009): 100-106.
- [174] Tsao, L. C. "Evolution of nano-Ag<sub>3</sub>Sn particle formation on Cu-Sn intermetallic compounds of Sn<sub>3</sub>.5Ag<sub>0</sub>.5Cu composite solder/Cu during soldering." *Journal of Alloys and Compounds* 509, no. 5 (2011): 2326-2333.
- [175] Leong, J. C., L. C. Tsao, C. J. Fang, and C. P. Chu. "Effect of nano-TiO<sub>2</sub> addition on the microstructure and bonding strengths of Sn-3.5Ag-0.5Cu composite solder BGA packages with immersion Sn surface finish." *Journal of Materials Science: Materials in Electronics* 22, no. 9 (2011): 1443-1449.
- [176] Tsao, L. C., M. W. Wu, and S. Y. Chang. "Effect of TiO<sub>2</sub> nanoparticles on the microstructure and



- bonding strengths of Sn-0.7Cu composite solder BGA packages with immersion Sn surface finish." *Journal of Materials Science: Materials in Electronics* 23, no. 3 (2012): 681-687.
- [177] MAA, Mohd Salleh, AM Mustafa Al Bakri, H. Kamarudin, M. Bnhussain, and Flora Somidin. "Solderability of Sn-0.7Cu/Si<sub>3</sub>N<sub>4</sub> lead-free composite solder on Cu-substrate." *Physics Procedia* 22 (2011): 299-304.
- [178] Kao, Szu-Tsung, Yung-Chi Lin, and Jenq-Gong Duh. "Controlling intermetallic compound growth in SnAgCu/Ni-P solder joints by nanosized Cu 6 Sn 5 addition." *Journal of electronic materials* 35, no. 3 (2006): 486-493.
- [179] Asthana, Rajiv, and Natalia Sobczak. "Wettability, spreading, and interfacial phenomena in high-temperature coatings." *JOM-52*, no. 1 (2000): 1-19.
- [180] Humpston, Giles, and David M. Jacobson, eds. *Principles of soldering*. ASM international, 2004.
- [181] Pal, Manoj Kumar, Gréta Gergely, Dániel Koncz-Horváth, and Zoltán Gácsi. "Investigation of microstructure and wetting behavior of Sn–3.0 Ag–0.5 Cu (SAC305) lead-free solder with additions of 1.0 wt% SiC on copper substrate." *Intermetallics* 128: 106991.
- [182] Osamura, K., S. Ochiai, S. Kondo, M. Namatame, and M. Nosaki. "Influence of third elements on growth of Nb<sub>3</sub>Sn compounds and on global pinning force." *Journal of materials science* 21, no. 5 (1986): 1509-1516.
- [183] Kim, H. K., and King-Ning Tu. "Kinetic analysis of the soldering reaction between eutectic SnPb alloy and Cu accompanied by ripening." *Physical review B* 53, no. 23 (1996): 16027.
- [184] Shen, Jun, Yan Cheong Chan, and S. Y. Liu. "Growth mechanism of Ni<sub>3</sub>Sn<sub>4</sub> in a Sn/Ni liquid/solid interfacial reaction." *Acta Materialia* 57, no. 17 (2009): 5196-5206.
- [185] Yoon, Jeong-Won, Bo-In Noh, Young-Ho Lee, Hyo-Soo Lee, and Seung-Boo Jung. "Effects of isothermal aging and temperature–humidity treatment of substrate on joint reliability of Sn–3.0 Ag–0.5 Cu/OSP-finished Cu CSP solder joint." *Microelectronics Reliability* 48, no. 11-12 (2008): 1864-1874.
- [186] Chen, L. D., M. L. Huang, and S. M. Zhou. "Effect of electromigration on intermetallic compound formation in line-type Cu/Sn/Cu interconnect." *Journal of Alloys and Compounds* 504, no. 2 (2010): 535-541.
- [187] Chung, C. Key, Jenq-Gong Duh, and C. R. Kao. "Direct evidence for a Cu-enriched region at the boundary between Cu<sub>6</sub>Sn<sub>5</sub> and Cu<sub>3</sub>Sn during Cu/Sn reaction." *Scripta Materialia* 63, no. 2 (2010): 258-260.
- [188] Liu, C. Z., and W. Zhang. "Bismuth redistribution induced by intermetallic compound growth in

- SnBi/Cu microelectronic interconnect." *Journal of materials science* 44, no. 1 (2009): 149-153.
- [189] Yang, Ming, Mingyu Li, and Chunqing Wang. "Interfacial reactions of eutectic Sn-3.5Ag and pure tin solders with Cu substrates during liquid-state soldering." *Intermetallics* 25 (2012): 86-94.
- [190] Laurila, T., V\_ Vuorinen, and J. K. Kivilahti. "Interfacial reactions between lead-free solders and common base materials." *Materials Science and Engineering: R: Reports* 49, no. 1-2 (2005): 1-60.
- [191] Prakash, K. H., and T. Sritharan. "Interface reaction between copper and molten tin–lead solders." *Acta materialia* 49, no. 13 (2001): 2481-2489.
- [192] Mookam, Niwat, and Kannachai Kanlayasiri. "Evolution of intermetallic compounds between Sn-0.3Ag-0.7Cu low-silver lead-free solder and Cu substrate during thermal aging." *Journal of Materials Science & Technology* 28, no. 1 (2012): 53-59.
- [193] Vianco, Paul T., Jerome A. Rejent, and Paul F. Hlava. "Solid-state intermetallic compound layer growth between copper and 95.5Sn-3.9Ag-0.6Cu solder." *Journal of electronic materials* 33, no. 9 (2004): 991-1004.
- [194] Li, J. F., P. A. Agyakwa, and C. M. Johnson. "Interfacial reaction in Cu/Sn/Cu system during the transient liquid phase soldering process." *Acta Materialia* 59, no. 3 (2011): 1198-1211.
- [195] Lee, T. Y., W. J. Choi, King-Ning Tu, J. W. Jang, S. M. Kuo, J. K. Lin, D. R. Frear, K. Zeng, and J. K. Kivilahti. "Morphology, kinetics, and thermodynamics of solid-state aging of eutectic SnPb and Pb-free solders (Sn–3.5 Ag, Sn–3.8 Ag–0.7 Cu and Sn–0.7 Cu) on Cu." *Journal of Materials Research* 17, no. 2 (2002): 291-301.
- [196] LI, Guo-yuan, and Xun-qing SHI. "Effects of bismuth on growth of intermetallic compounds in Sn-Ag-Cu Pb-free solder joints." *Transactions of Nonferrous Metals Society of China* 16 (2006): s739-s743.

## Author publications

### Journal papers

1. **Pal, M. K.**, Gergely, G., Horváth, D. K., & Gácsi, Z, Microstructural investigations and mechanical properties of pure lead-free (Sn–3.0Ag–0.5Cu and Sn–4.0Ag–0.5Cu) solder alloy. **Metallurgical and Materials Engineering**, 24 (1) (2018), 27–36.
2. **Pal, M. K.**, Gergely, G., Horváth, D. K., & Gácsi, Z., influence of ceramic particles on the microstructure and mechanical properties of SAC305 lead-free soldering material, **Arch. Metall. Mater.** 64 (2) (2019), 603–606.
3. Koncz-Horvath, D., Molnar, A., Gergely, G., **Pal, M. K.**, & Gacsi, Z., Examination the effect of thermal shock test on SAC solder joints fabricated by THRS and multi-wave soldering techniques. **Resolution and Discovery**, 4(1) (2019), 1–6.
4. **Pal, M. K.**, Gergely, G., Horváth, D. K., & Gácsi, Z., Investigation of the electroless nickel plated SiC particles in SAC305 solder matrix, **Powder metallurgy and metal ceramics**, 58(9–10) (2020), 529–537.
5. **Pal, M. K.**, Gergely, G., Horváth, D. K., & Gácsi, Z., Characterization of the interface between ceramics reinforcement and lead-free solder matrix, **Surfaces and Interfaces**, 20(3) (2020), 100576.
6. **Pal, M. K.**, Gergely, G., Horváth, D. K., & Gácsi, Z., Distribution and microstructure analysis of ceramic particles in the lead-free solder matrix, **Crystal Research and Technology**, 55(10) (2020), 2000123.
7. **Pal, M. K.**, Gergely, G., Horváth, D. K., & Gácsi, Z., Investigation of microstructure and wetting behavior of Sn-3.0Ag-0.5Cu (SAC305) lead-free solder with additions of 1.0 wt. % SiC on copper substrate, **Intermetallics**, 128 (2021) 106991.

### Conference presentations

1. **Pal, M. K.**, Gergely, G., Horváth, D. K., & Gácsi, Z., Comparison of different SAC solders, XXI. Tavaszi Szél Konferencia 2018 május 03. – 2018. május 6, Széchenyi István Egyetem, Győr, Hungary (**Oral**).

2. **Pal, M. K.**, Gergely, G., Horváth, D. K., & Gácsi, Z., Fabrication of solder material by powder metallurgy route, XXI. Tavaszi Szél Konferencia 2018 május 03. – 2018. május 6, Széchenyi István Egyetem, Győr, Hungary **(Oral)**.
3. **Pal, M. K.**, Gergely, G., Horváth, D. K., & Gácsi, Z., Investigating the microstructural and mechanical properties of pure lead-free soldering materials (SAC305 & SAC405), XVI.PhD–2018, Conference organized by Professors for European Hungary Association, Budapest **(Oral)**.
4. **Pal, M. K.**, Gergely, G., Horváth, D. K., & Gácsi, Z., Influence of ceramic nanoparticles on the microstructure and Mechanical Properties of SAC305 & SAC405, 15th International Symposium on Novel and Nano Materials, July 1(Sun.)-July 6(Fri.), 2018, Tivoli Oriente, Lisbon, Portugal **(Oral)**.
5. **Pal, M. K.**, Gergely, G., Horváth, D. K., & Gácsi, Z., Preparation of Ni-coated SiC ceramic powders by electroless plating method, 7th International Scientific Conference on Advances in Mechanical Engineering (ISCAME), 7-8 November 2019, Debrecen, Hungary **(Oral)**.
6. **Pal, M. K.**, Gergely, G., Horváth, D. K., & Gácsi, Z., Investigation of the electroless Nickel-plated SiC particles in SAC305 solder matrix, 11<sup>th</sup> international conference on materials science & engineering, 13-16 March 2019, Organised by Transylvania University Brasov, Romania **(Oral)**.